

Kinetic analysis of color changes in cellulose during heat treatment

Miyuki Matsuo · Kenji Umemura · Shuichi Kawai

Received: 5 July 2011 / Accepted: 24 October 2011 / Published online: 21 December 2011
© The Japan Wood Research Society 2011

Abstract This paper deals with the kinetics of the color changes of cellulose during heat treatment. The color of cellulose heated at 90–180°C was measured by a spectrophotometer and expressed by CIELAB color parameters. The values of L^* decreased and those of a^* , b^* and ΔE^*_{ab} increased at all the treatment temperatures. Several kinetic models, namely, the zero-order, first-order, second-order and autocatalytic model, were applied to the changes in the color values. Furthermore, the results of kinetic analysis using the best-fit model were compared to the results obtained from conventional kinetic models. It was suggested that the kinetic analysis using the best-fit model was the better way to accurately predict color changes during heat treatment. The values of apparent activation energy calculated from the changes of L^* , a^* , b^* and ΔE^*_{ab} were 125, 124, 118 and 120 kJ/mol, respectively. These values were similar to the reported values calculated from other chemical or mechanical properties.

Keywords Cellulose · Heat treatment · Color · Kinetic analysis

Introduction

Cellulose is the major component of ligno-cellulosic materials such as paper, textile and wood, and the chemical and mechanical degradation of cellulose has a great influence on the degradation of ligno-cellulosic materials. Kinetic study has been of great importance not only for understanding the degradation mechanism but also for predicting the degradation of chemical and mechanical properties. Numerous kinetic studies on cellulose have been reported using thermally and hygrothermally treated cellulose, mainly focusing on the degradation of electrical insulation paper in electrical power transformers [1, 2] and the degradation of acidic paper, which has been widely used from the 18th century and has caused catastrophic degradation of books and documents [3–5].

The degradation of cellulose has been widely elucidated by weight decrease, degree of polymerization (DP), mechanical properties, crystallinity and morphological characteristics. In addition, the color difference and the yellowing index are also used [6, 7]. In the field of paper and textile science, the change in color of cellulose is important not only from an aesthetic point of view but also as a possible index of the degradation of materials [8]. Several investigations have reported a correlation between color parameters and either DP or mechanical properties [9–11]. Color measurement is non-destructive and only requires a small area, unlike the measurements of chemical and mechanical properties. Therefore, color measurement is also suitable when the aesthetic aspects of measuring objects are important and destructive tests are unacceptable, for example, for the investigation of culturally significant properties or the quality monitoring in industrial processing.

A part of this work was presented at the International Conference of COST Action IE0601, “Wood Science for Conservation of Cultural Heritage”, 2009, and the 61st annual meeting of the Japan Wood Research Society, 2011.

M. Matsuo (✉) · K. Umemura · S. Kawai
Research Institute for Sustainable Humanosphere,
Kyoto University, Gokasho, Uji, Kyoto 611-0011, Japan
e-mail: matsuomiyuki@rish.kyoto-u.ac.jp

Table 1 The basic information of the cellulose sample and the average initial color values with their standard deviations in parentheses

Trade name	Ash content (%)	Basis weight (g/m ²)	Degree of polymerization	L_0^*	a_0^*	b_0^*
Whatman No.1	<0.06 ^a	87 ^a	500–5000 ^b	98.11 (0.01)	−0.02 (0.01)	2.31 (0.06)

^a Based on the company's information

^b Based on the literature [15–18]

The color of cellulose turns brown or yellow during heat treatment [11, 12]. However, the mechanism of this change has not been clarified yet and only a few reports were found in kinetic analysis based on the color changes of cellulose [13].

This study examines the color changes of cellulose during heat treatment to elucidate and predict desirable/undesirable color changes of ligno-cellulosic materials. For an accurate analysis, we have applied several kinetic models and a best-fit model employing a kinetic approach based on the time–temperature superposition (TTSP) method.

Materials and methods

Materials

Whatman No.1 cellulose filter paper was used as a cellulose sample. The basic information of the samples is summarized in Table 1. Specimens of approximately 20 × 40 mm were dried in an air-circulating oven and then in a vacuum oven at 60°C for 24 h each. The low drying temperature was set to avoid undesirable reactions of cellulose. Each dried specimen was heated in an air-circulating oven at 4 temperature levels from 90 to 180°C for a duration ranging from an hour to approximately 1.8 years. Table 2 shows the treatment times of the specimens at each treatment temperature. They were planned under the assumption that a 10°C increase of the reaction temperature halves the reaction time to obtain a similar intensity of reaction among the treatment of different temperatures [14]. The treatment at 90°C is now in process with the planned treatment time shown in parentheses in Table 2.

Color measurement

The color of the specimens was measured with a spectrophotometer (KONICA MINOLTA CM-2600d) under a D65 light source and an observed angle of 10°. The sensor head of the spectrophotometer was 8 mm in diameter. The size of paper specimens was sufficiently large relative to the sensor head. The CIELAB color parameters (L^* , a^* and b^*) were used to express the color changes. The differences in parameters ΔL^* , Δa^* and Δb^* and the total color

Table 2 Treatment temperatures and times of cellulose samples

	90°C	120°C	150°C	180°C
Treatment time (h)		64	8	1
	768			
			16	2
	1560	192	24	3
	2560	320	40	
	3584	448	56	7
	6144		96	
	9216			
	12288	1536	192	24
	15580	3096	384	48
	(24576)	5450	672	
	(43008)	7680	960	120
	(61440)		1280	
				240
			2304	288
			2768	336

The treatment at 90°C is now in process with the planned treatment time in parentheses

differences ΔE_{ab}^* were calculated using the following formulas: [19, 20]

$$\begin{aligned}\Delta L^* &= L^* - L_0^* \\ \Delta a^* &= a^* - a_0^* \\ \Delta b^* &= b^* - b_0^*\end{aligned}\quad (1)$$

$$\Delta E_{ab}^* = \sqrt{\Delta L^{*2} + \Delta a^{*2} + \Delta b^{*2}} \quad (2)$$

where L^* is the lightness and a^* and b^* are the color coordinates under any testing condition, respectively, and L_0^* , a_0^* and b_0^* are the corresponding reference values obtained as the average of untreated specimens shown in Table 1, respectively. The color values of 3 specimens were averaged and the standard deviations were also calculated. The average of the coefficients of variation for each treatment condition were 0.23, 2.70, 1.38 and 1.89% for L^* , a^* , b^* and ΔE_{ab}^* , respectively. Since the variation in the color values was negligibly small, the error bars displaying standard deviations were not drawn in the following figures.

The specimen preparation and the color measurement were always performed using rubber gloves.

Weight reduction

The sample amount for each condition was approximately 3 g, which was measured before and after heat treatment under the dry condition. The weight reductions were calculated based on the following equation:

$$\text{Weight reduction} = 100 \times \frac{W_0 - W_t}{W_0} (\%) \tag{3}$$

where W_0 and W_t are the dry weight of cellulose before treatment and at treatment time t , respectively.

Kinetic analysis for color changes of cellulose

Numerous reports have discussed the applicability of kinetic models, especially with respect to the degree of polymerization and some mechanical properties [21, 22]. However, there have been few reports dealing with the kinetic analysis of color properties [13].

The rate of change of a material property P at time t can be represented by:

$$\frac{dP}{dt} = \pm kP^n \tag{4}$$

where n is the order of reaction.

By integrating Eq. (4), the zero-order (Eq. 5), first-order (Eq. 6) and second-order (Eq. 7) kinetic models can be derived as:

$$P = P_0 \pm kt \tag{5}$$

$$P = P_0 \exp(\pm kt) \tag{6}$$

$$P = \frac{P_0}{1 \pm ktP_0} \tag{7}$$

where P is the color value at a treatment time t , P_0 the initial value of color, and k the rate constant of the chemical reaction. Many cellulose degradation kinetics have been based on these reaction models. Zervos et al. [13] reported that a kinetic model based on autocatalysis (Eq. 8) fitted well the changes of L^* and b^* during the heat treatment in sealed vessels:

$$P = P_0 \pm C(2^{kt} - 1) \tag{8}$$

where C is constant.

In general, it is known that a chemical reaction can be described by the Arrhenius equation:

$$k = A \exp\left(-\frac{E_a}{RT}\right) \tag{9}$$

where A is the frequency factor, E_a the apparent activation energy, R the gas constant, and T the absolute temperature of the reaction. The apparent activation energy is then obtained from the slope of the Arrhenius plot, which is the logarithm of k versus the reciprocal of T [23].

To determine the activation energy more accurately, a TTSP method has been proposed [24–27]. An Arrhenius approach applying the TTSP method is briefly described below. When the measured material property is plotted as a function of logarithmic treatment time at different temperatures, the shift distance used to superpose the plotted curves to the curves at a fixed reference temperature T_{ref} along the logarithmic time axis is called the time–temperature shift factor a_T , and is given as:

$$a_T = \frac{t_T}{t_{ref}} \tag{10}$$

where t_{ref} is the test time at T_{ref} , and t_T is the time required to give the same response at the test temperature T . Combining Eqs. (9) and (10) gives:

$$a_T = \exp\left[\frac{E_a}{R} \left(\frac{1}{T} - \frac{1}{T_{ref}}\right)\right] \tag{11}$$

where both T and T_{ref} are absolute temperatures. Plotting $\ln(a_T)$ versus $1/T$ is another way to calculate E_a .

Data analysis was performed using the FlexPro 8 software package (Weisang GmbH, Germany). All parameters of the model functions and the values of a_T were estimated using a non-linear iterative curve-fitting method. The coefficient of determination (R^2) and the root mean square error (RMSE) were used as the criteria to express the fitting of the tested models to the experimental data:

$$R^2 = \frac{\sum_{i=1}^N (\hat{Y}_i - \bar{Y})^2}{\sum_{i=1}^N (Y_i - \bar{Y})^2} \tag{12}$$

$$\text{RMSE} = \sqrt{\frac{\sum_{i=1}^N (Y_i - \hat{Y}_i)^2}{N}} \tag{13}$$

where \hat{Y}_i and Y_i are the measured and modeled values, respectively, \bar{Y} is the average of the measured data and N is the total number of observations. The higher the value of R^2 and the lower the value of RMSE, the better the model fits the data.

Results and discussion

Color changes of cellulose during heat treatment

As shown in the representative specimen presented in Fig. 1, the color of cellulose turned brown and dark with increasing treatment time. Figure 2 shows the changes of the color parameters according to the duration and temperature of treatment. The decrease in L^* at all temperatures indicates that the specimens became darker with increasing treatment time. The increases in a^* and b^* indicate that the specimens became more red and yellow.

Fig. 1 Cellulose specimens treated at 180°C with the treatment time (h)


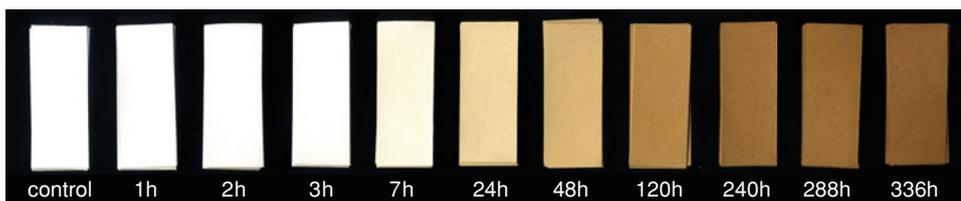


Fig. 2 Changes in L^* , a^* , b^* , and ΔE^*_{ab} during heat treatment as a function of time

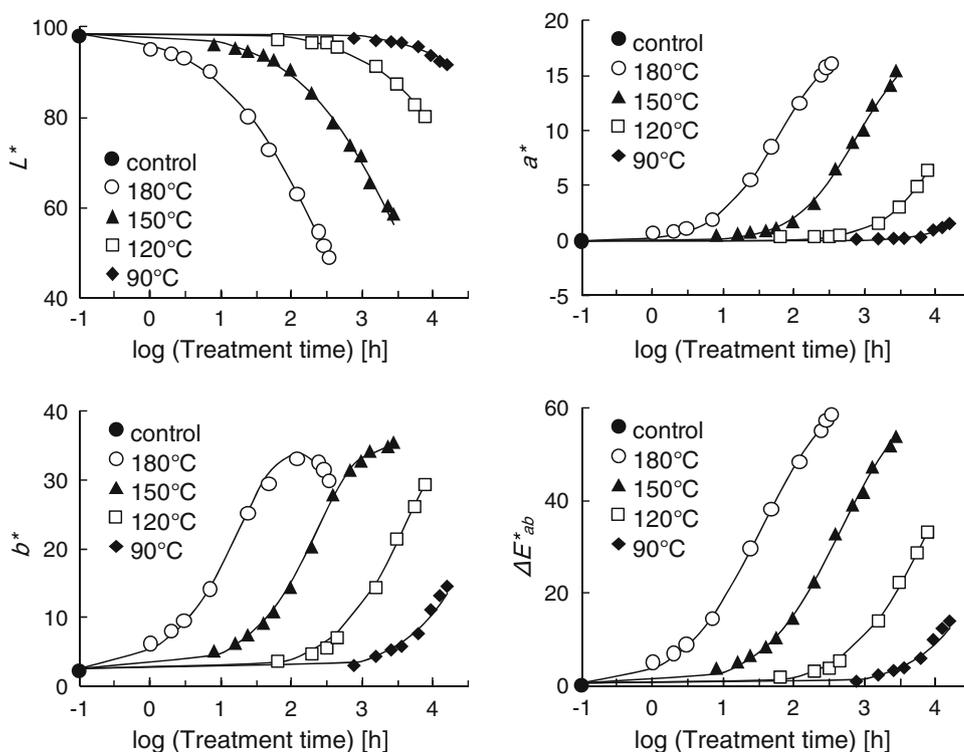

These results corresponded to the increase in ΔE^*_{ab} . Similar behavior irrespective of treatment temperatures suggested that the same reaction processes might cause the color changes, irrespective of temperatures.

Kinetic analysis of the color changes of cellulose

Several kinetic models were applied to the experimental data. In addition, in an analysis independent of these models, the function giving the best fit was selected. Since a similar behavior was observed irrespective of treatment temperatures, the data from the 180°C treatment were used to determine the best-fit model.

Judging from the values of R^2 and RMSE, the autocatalytic model fit the color changes well in all color parameters, while the zero-, first- and second-order kinetic models did not fit the color parameters well except in the case of L^* .

As the function giving the best fit for all color parameters, the NIST Hahn1 model was selected:

$$P = \frac{C_0 + C_1t + C_2t^2 + C_3t^3}{1 + C_4t + C_5t^2 + C_6t^3} \tag{14}$$

where C_i ($i = 0, \dots, 6$) is constant. However, it should be noted that we only used this function to numerically analyze the color changes. Thus, the function might have no meaning in terms of the reaction mechanism. The obtained values of R^2 and RMSE for each model are summarized in Table 3.

From the results obtained above, the Arrhenius plots were described using the autocatalytic model and the best-fit model. Figure 3 shows the autocatalytic model fitted to the changes in ΔE^*_{ab} at each temperature. High values of R^2 were obtained for all treatment temperatures ($R^2 > 0.988$). However, in spite of the high values of R^2 , the experimental data deviated from the saturation of sigmoidal curve characteristic with the autocatalytic model as shown in Fig. 3, and the autocatalytic reaction is not likely to occur in the ventilated conditions as in the studies like ours [22, 28]. Using the rate constant k of each color parameter at each temperature calculated according to

Table 3 Comparison of coefficients of determination (R^2) and root mean square errors (RMSE) of regression curves among several kinetic models and a best-fit model to changes in the color values during the treatment at 180°C

	Zero-order		First-order		Second-order		Autocatalytic		Best fit ^a	
	R^2	RMSE	R^2	RMSE	R^2	RMSE	R^2	RMSE	R^2	RMSE
L^*	0.8846	6.201	0.9226	5.174	0.9533	4.068	0.9892	1.901	<u>0.9999</u>	<u>0.138</u>
a^*	0.8665	2.325	0.7206	3.190	0.5660	3.824	<u>0.9970</u>	<u>0.351</u>	<u>0.9998</u>	<u>0.088</u>
b^*	0.5408	7.816	0.4369	8.403	0.3541	8.837	<u>0.9924</u>	1.005	<u>0.9996</u>	<u>0.226</u>
ΔE^*_{ab}	0.7942	9.987	0.6683	12.141	0.5433	13.782	0.9878	2.429	<u>0.9999</u>	<u>0.205</u>

Underlined values are above 0.9900 in R^2 and below 1.000 in RMSE

^a Equation (14) was used as a best-fit model

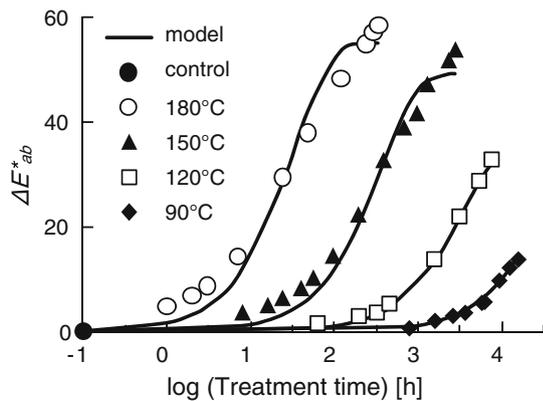


Fig. 3 Change in ΔE^*_{ab} and its model: autocatalytic model fitted to each temperature

Eq. (8), the activation energy E_a was calculated from Eq. (9). The values of E_a ranged from 101 to 125 kJ/mol, as shown in Table 4. Figure 4 shows the data superposed to the best-fit model using a_T at each treatment temperature. The regression and the superposition fit the data set extremely well ($R^2 > 0.998$). The activation energy E_a was calculated according to Eq. (11) and the values of E_a ranged from 118 to 125 kJ/mol. The values of E_a for L^* and ΔE^*_{ab} calculated from the autocatalytic model were approximately 20 kJ/mol smaller than those calculated from the best-fit model. This may be because the experimental data were a little outside the range of autocatalytic model under the present experimental conditions, as mentioned above. Therefore, it is better to use the best-fit model with the TTSP method to accurately predict the color changes during heat treatment.

Figure 5 shows the Arrhenius plots of ΔE^*_{ab} and their linear regression line as an example using the best-fit model. The regression lines for Arrhenius plots showed a good linearity for all color parameters ($R^2 > 0.987$), suggesting that kinetic analysis can be applied to cellulose color properties and the prediction of color changes. The results also suggested that the color changes during heat treatment at the temperatures ranging from 90 to 180°C can be explained as the same reaction mechanism, presumably

Table 4 Comparison of apparent activation energies (E_a) calculated from the Arrhenius equation

	E_a (kJ/mol)	
	Autocatalytic	Best fit ^a (TTSP)
L^*	106	125
a^*	125	124
b^*	113	118
ΔE^*_{ab}	101	120

^a Equation (14) was used as a best-fit model

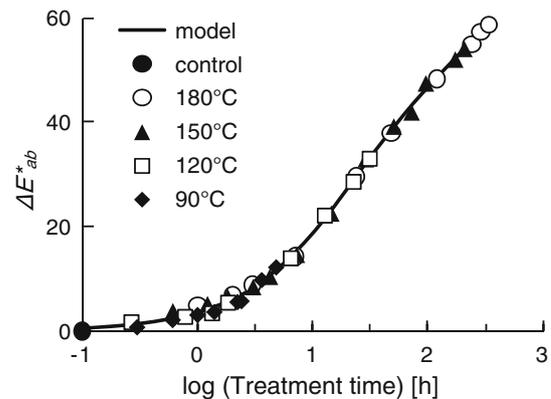


Fig. 4 Change in ΔE^*_{ab} and its model: best-fit model and superposed data using a_T at each temperature

thermal oxidation, which occurs in the presence of oxygen and the absence of moisture. The values of E_a calculated from the color parameters were similar to the reported values obtained from the other properties of cellulose, such as the degree of polymerization and mechanical properties [14, 21, 24, 29]. However, these reported values have wide variation and are still controversial [21].

Figure 6 shows the weight reduction as a function of time. The weight was reduced with increasing time at 120, 150, and 180°C and slightly reduced at 90°C. As shown in the representative case in Fig. 7, the color changed

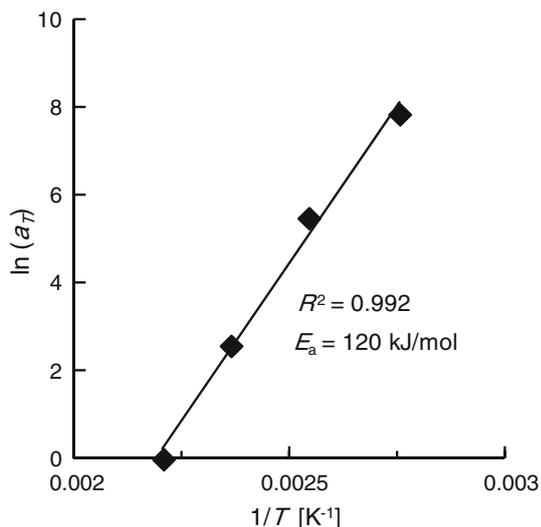


Fig. 5 Arrhenius plots of the change in ΔE^*_{ab} using the best-fit model (Eq. 14) and TTSP method

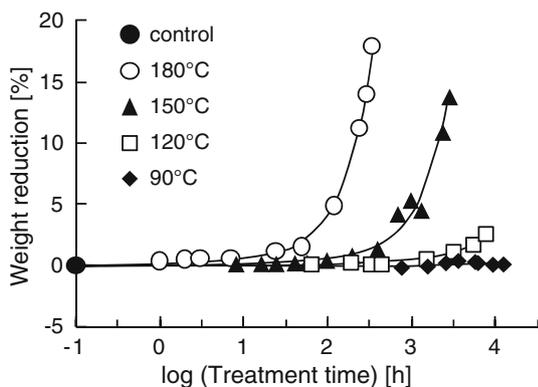


Fig. 6 Weight reduction during heat treatment as a function of time

drastically before the remarkable weight reduction started, indicating that the color changes of cellulose are mainly due to the denaturation of cellulose and/or a slight amount of decomposition products of cellulose rather than the major decomposition of cellulose. The factors responsible for the color changes of cellulose were estimated to be carbonyl groups in the cellulose chains and the formation of colored low-molecular substances such as furan-type compounds [10, 30]. Łojewski et al. [9] reported that the increase of ΔE^*_{ab} had a significant linear relationship with the amount of furfural formed during heat treatment of cellulose at 90°C. Matsuoka et al. [31, 32] concluded that colored substances were formed at the reducing ends of cellulose during heat treatment at 60–280°C. These results suggested that the color changes were due to the denaturation of the reducing ends, the formation of furan-type compounds, or a combination of both these effects. The results obtained from this study will contribute to a better understanding of the degradation of cellulose and provide

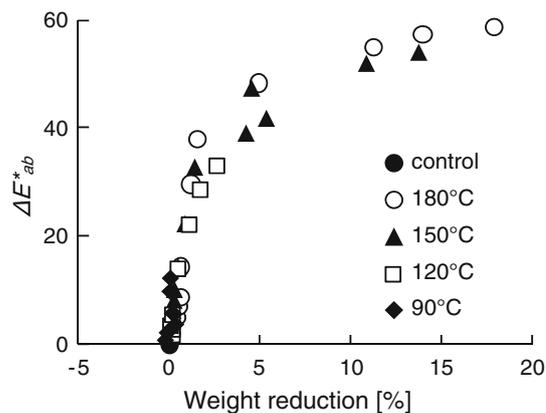


Fig. 7 The relationship between ΔE^*_{ab} and weight reduction

further evidence of the effectiveness of color parameters as an index of cellulose degradation.

The contributions of cellulose to color changes of ligno-cellulosic materials were estimated by comparing them to color changes of hinoki (*Chamaecyparis obtusa* Endl.) wood which was treated and analyzed in almost the same conditions and procedures with the present study [33]. The values of L^* decreased and a^* , b^* and ΔE^*_{ab} increased both in cellulose and wood. But in the later reaction stages of hinoki wood, the values of a^* and b^* started to decrease. The increase and subsequent decrease of a^* and b^* were also observed in the other wood species [34, 35]. The changes in L^* and ΔE^*_{ab} of hinoki wood were similar degree to those of cellulose. These results show that cellulose is a major component that contributes to color changes of wood, however, other wood components such as extractives, lignin, hemicelluloses and minor components also have effects on color changes of wood, especially on the chromatic characteristics. The successful kinetic analysis indicated that the thermal oxidation might cause the color changes of wood as well as cellulose, irrespective of treatment temperatures. The values of activation energy calculated from each color parameters of wood were lower than those of cellulose in all color parameters. The lower activation energy may be due to wood components other than cellulose. While color changes of ligno-cellulosic materials are due to the multiple and/or interactive effect of their components, the color changes of cellulose certainly contributes to that of ligno-cellulosic materials.

Conclusions

Color changes of cellulose heated at 90–180°C were measured and expressed by CIELAB color parameters. The value of L^* decreased and the values of a^* , b^* and ΔE^*_{ab} increased during heat treatment at all the temperatures.

Among the several kinetic models applied to the experimental data, the autocatalytic model best explained the changes in all color parameters. However, according to the fitting of the autocatalytic model and a review of the results in the literature, it is concluded that color changes during heating could not be explained by an autocatalytic reaction. To accurately predict the color changes during heat treatment, it was better to use the best-fit model with the TTSP method. The Arrhenius plot showed good linearity in the best-fit model, implying that the color changes might be induced by the same mechanism at the temperature range from 90 to 180°C. The apparent activation energies calculated from color parameters using the TTSP method ranged from 118 to 125 kJ/mol, which are similar to the reported values obtained from other chemical and mechanical properties of lingo-cellulose materials.

Acknowledgments This work was supported by Grants-in-Aid for Scientific Research (A) (No. 20248020) and for JSPS Fellows (No. 21-2994).

References

- Ali M, Emsley AM, Herman H, Heywood RJ (2001) Spectroscopic studies of the ageing of cellulosic paper. *Polymer* 42:2893–2900
- Emsley AM, Stevens GC (1994) Kinetics and mechanisms of the low-temperature degradation of cellulose. *Cellulose* 1:26–56
- Erhardt D, Tumosa CS (2005) Chemical degradation of cellulose in paper over 500 years. *Restaurator* 26:151–158
- Zou X, Uesaka T, Gurnagul N (1996) Prediction of paper permanence by accelerated aging I. Kinetic analysis of the aging process. *Cellulose* 3:243–267
- Zou X, Uesaka T, Gurnagul N (1996) Prediction of paper permanence by accelerated aging II. Comparison of the predictions with natural aging results. *Cellulose* 3:269–279
- Zou X, Gurnagul N, Uesaka T, Bouchard J (1994) Accelerated aging of papers of pure cellulose—mechanism of cellulose degradation and paper embrittlement. *Polym Degrad Stabil* 43:393–402
- Müller M, Murphy B, Burghammer M, Riekel C, Pantos E, Gunneweg J (2007) Ageing of native cellulose fibres under archaeological conditions: textiles from the Dead Sea region studied using synchrotron X-ray microdiffraction. *Appl Phys A Mater* 89:877–881
- Zervos S, Moropoulou A (2006) Methodology and criteria for the evaluation of paper conservation interventions: a literature review. *Restaurator* 27:219–274
- Łojewski T, Sawoszczuk T, Łagan JM, Zięba K, Baranski A, Łojewska J (2010) Furfural as a marker of cellulose degradation. A quantitative approach. *Appl Phys A Mater* 100:873–884
- Vives JMG, Escoda JRM, Guerra RA, Hernandez LA (2001) A method for the non-destructive analysis of paper based on reflectance and viscosity. *Restaurator* 22:187–207
- Yatagai M, Zeronian SH (1994) Effect of ultraviolet light and heat on the properties of cotton cellulose. *Cellulose* 1:205–214
- Shimazu F, Sterling C (1966) Effect of wet and dry heat on structure of cellulose. *J Food Sci* 31:548–551
- Zervos S, Moropoulou A (2005) Cotton cellulose ageing in sealed vessels. Kinetic model of autocatalytic depolymerization. *Cellulose* 12:485–496
- Stamm AJ (1956) Thermal degradation of wood and cellulose. *Ind Eng Chem* 48:413–417
- Isogai A (2003) Science of cellulose (in Japanese). Asakura Publishing Co. Ltd., Tokyo
- Selli E, Beltrame PL, Testa G, Bonfatti AM, Rossi E, Seves A (1998) Kinetic studies on the accelerated aging of cellulosic materials. *Angew Makromol Chem* 257:63–69
- Kolar J, Strlič M, Marinček M (2002) IR pulsed laser light interaction with soiled cellulose and paper. *Appl Phys A Mater* 75:673–676
- Zhang YHP, Lynd LR (2005) Determination of the number-average degree of polymerization of cellodextrins and cellulose with application to enzymatic hydrolysis. *Biomacromolecules* 6:1510–1515
- Japanese Industrial Standard Committee (2008) JIS Z 8729 Colour specification-CIELAB and CIELUV colour spaces (in Japanese)
- Japanese Industrial Standard Committee (2009) JIS Z 8730, Colour specification-Colour differences of object colours (in Japanese)
- Ding HZ, Wang ZD (2008) On the degradation evolution equations of cellulose. *Cellulose* 15:205–224
- Calvini P, Gorassini A, Merlani AL (2008) On the kinetics of cellulose degradation: looking beyond the pseudo zero order rate equation. *Cellulose* 15:193–203
- Atkins P, Paula J (2010) Atkins' physical chemistry, 9th edn. Oxford University Press, New York
- Ding HZ, Wang ZD (2007) Time-temperature superposition method for predicting the permanence of paper by extrapolating accelerated ageing data to ambient conditions. *Cellulose* 14:171–181
- Gillen KT, Clough RL (1989) Time-temperature-dose rate superposition: a methodology for extrapolating accelerated radiation aging data to low-dose rate conditions. *Polym Degrad Stabil* 24:137–168
- Wise J, Gillen KT, Clough RL (1995) An ultrasensitive technique for testing the Arrhenius extrapolation assumption for thermally aged elastomers. *Polym Degrad Stabil* 49:403–418
- Gillen KT, Celina M (2001) The wear-out approach for predicting the remaining lifetime of materials. *Polym Degrad Stabil* 71:15–30
- Barański A (2002) Ageing kinetics of cellulose and paper. *Restaurator* 23:77–88
- Agrawal RK (1985) On the use of the Arrhenius equation to describe cellulose and wood pyrolysis. *Thermochim Acta* 91:343–349
- Łojewska J, Missori M, Lubańska A, Grimaldi P, Zięba K, Proniewicz LM, Castellano AC (2007) Carbonyl groups development on degraded cellulose. Correlation between spectroscopic and chemical results. *Appl Phys A Mater* 89:883–887
- Matsuoka S, Kawamoto H, Saka S (2011) Thermal glycosylation and degradation reactions occurring at the reducing ends of cellulose during low-temperature pyrolysis. *Carbohydr Res* 346:272–279
- Matsuoka S, Kawamoto H, Saka S (2011) Reducing end-group of cellulose as a reactive site for thermal discoloration. *Polym Degrad Stabil* 96:1242–1247
- Matsuo M, Yokoyama M, Umemura K, Gril J, Yano K, Kawai S (2010) Color changes in wood during heating: kinetic analysis by applying a time-temperature superposition method. *Appl Phys A* 99:47–52
- Bekhta P, Niemi P (2003) Effect of high temperature on the change in color, dimensional stability and mechanical properties of spruce wood. *Holzforschung* 57:539–546
- González-Peña MM, Hale MDC (2009) Colour in thermally modified wood of beech, Norway spruce and Scots pine. Part 1: colour evolution and colour changes. *Holzforschung* 63:385–393