

# Viscosity and thermal conductivity of MgO–EG nanofluids

## Experimental results and theoretical models predictions

Gawel Żyła<sup>1</sup> 

Received: 29 September 2016/Accepted: 25 January 2017/Published online: 18 February 2017  
© The Author(s) 2017. This article is published with open access at Springerlink.com

**Abstract** Nanofluids are a group of novel engineering materials that are increasingly being used, particularly in the processes of heat exchange. One of the most promising materials in this group is magnesium oxide–ethylene glycol (MgO–EG) nanofluid. The literature informs that this material is characterized by an significant increase in thermal conductivity with low dynamic viscosity increase. The aim of this paper is to provide experimental data on the dynamic viscosity and thermal conductivity of nanofluids containing MgO nanoparticles with 20 nm average size and ethylene glycol as base fluid. To determine dynamic viscosity and thermal conductivity of samples, a HAAKE MARS 2 rheometer (Thermo Electron Corporation, Karlsruhe, Germany) and KD2 Pro Thermal Properties Analyzer (Decagon Devices Inc., Pullman, Washington, USA) were used. Additionally, a comparison of the experimental results and the predictions of theoretical models was presented. It was presented that the vast majority of theoretical models does not describe in a correct way both viscosity and thermal conductivity. It was also shown that the enhancement of this basic physical properties might be described with good result with second degree polynomials. Finally, evaluation of the heat transfer performance was presented.

**Keywords** Nanofluid · Thermal conductivity · Viscosity · MgO · Ethylene glycol

## Introduction

Nanofluids, suspensions of nanoparticles in a liquid base, are an interesting group of materials which, due to the increased thermal conductivity, are used in various industries [1–3], especially in energy sector [4–6] and the automotive industry [7, 8].

The increase in thermal conductivity of nanofluids containing various types of nanoparticles was intensively studied [9–25]. However, when planning the practical use of nanofluids, it should be taken into account that with increasing concentration of the nanoparticles in a liquid its viscosity increases [19, 20, 26]. In some cases, an increase in viscosity may also be associated with a change of liquid from Newtonian to non-Newtonian [27–33]. It was also demonstrated that the addition of nanoparticles changes the electrical properties of ethylene glycol [34–37].

Xie et al. [38] pointed out that MgO nanofluids present higher thermal conductivity among ethylene glycol-based nanofluids containing oxide nanoparticles and low viscosity. These properties make MgO–EG nanofluids particularly interesting from the point of view of future applications. Adio et al. [39] present results of their work on experimental investigation and model development for effective viscosity of magnesium oxide–ethylene glycol nanofluids. They used dimensional analysis, FCM-ANFIS and GA-PNN techniques to prepare model of viscosity depend on temperature and volume fraction of nanoparticles. Other properties of this material, which are extensively studied, are the pH and electrical conductivity. Adio et al. [40] present results of experimental investigation into the pH and electrical conductivity of MgO–ethylene glycol nanofluids containing nanoparticles with various diameters, and in other paper, they presented factors affecting this properties [41]. Thermal transport

---

✉ Gawel Żyła  
gzyla@prz.edu.pl

<sup>1</sup> Department of Physics and Medical Engineering, Rzeszow University of Technology, al. Powstancow Warszawy 9, 35-959 Rzeszow, Poland

properties of MgO–EG nanofluids was the object of study to Yu et al. [42]. Attempt to modeling, the thermal conductivity of MgO–EG nanofluids was conducted by Esfe et al. [43]. They used artificial neural network and presented new model of thermal conductivity enhancement depending on temperature, volume fraction, and particle diameter.

Not only ethylene glycol seems to be an interesting base fluid for MgO nanoparticles. Shoghl et al. [44] present results of experimental studies on electrical conductivity, viscosity, and density of MgO–water nanofluids. Menlik et al. [45] described the possibility of use MgO–water nanofluids in heat pipe. Esfe et al. [46], and Davarnejad and Jamshidzadeh [47] present results of experimental studies and CFD modeling of heat transfer in MgO–water nanofluids under turbulent flow.

MgO nanoparticles can also be used in the advanced heat transfer systems. For example, Manikandan and Rajan [48] describe the opportunities and benefits from use the MgO nanoparticles suspended in Therminol 55. The development of increasingly simple and effective methods of obtaining MgO nanoparticles [49] in various media gives hope for wider use of these materials in industrial processes.

This paper presents the results of experimental research on viscosity and thermal conductivity of MgO–EG nanofluids and also compares the experimental data with the theoretical models used to describe this basic thermo-physical properties of nanofluids.


## Materials and methods

### MgO nanoparticles

The nanoparticles used in the study are a commercially available MgO nanopowder produced by PlasmaChem GmbH (Berlin, Germany) with >99% purity. The particle average size declared by the manufacturer is 20 nm, and specific surface ca.  $50 \text{ m}^2 \text{ g}^{-1}$ . The thermal conductivity of MgO was determined by Hofmeister [50], and it is  $50.1 \text{ W m}^{-1} \text{ K}^{-1}$  at temperature 298 K. Scanning electron microscope (SEM) picture of dry MgO nanoparticles was taken using a VEGA3 microscope (TESCAN Brno, s.r.o., Brno, Czech Republic). Figure 1 presents SEM image of nanoparticles used to prepare nanofluids. SEM picture presents that particle size corresponding with supplier information.

### Sample preparation

Nanofluids were prepared using two-step method through the dispersion of nanoparticles in a base fluid—ethylene glycol (POCH, Avantor Performance Materials Poland,

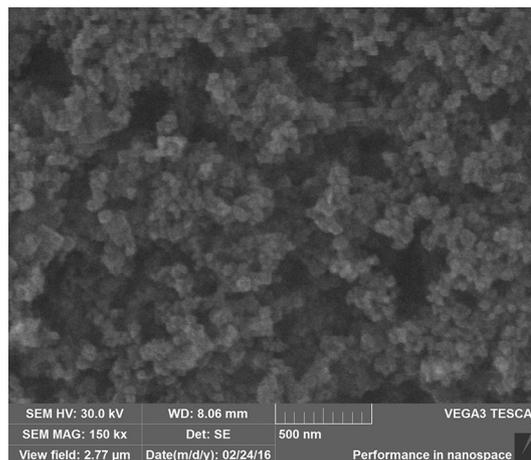

**Fig. 1** SEM image of dry MgO nanoparticles

Gliwice, Poland). Samples were prepared in different mass concentration from 0 to 20% with 5% step. Then, after taking into account the density of nanoparticles ( $3.58 \text{ g cm}^{-3}$  [51]) and base fluid, ethylene glycol ( $1.114 \text{ g cm}^{-3}$  [52]) mass concentrations were recalculated to volumetric fractions.

Nanoparticle dispersion process was assisted by mechanical stirring for 30 min in Genius 3 Vortex (IKA, Staufen, Germany), and the sonication for 200 min in ultrasound wave bath Emmi 60 HC (EMAG, Moerfelden-Walldorf, Germany). All samples were prepared at room temperature not exceeding 298.15 K, and due to the possibility of agglomeration and sedimentation of nanoparticles in suspension, all measurements were performed immediately after sonication. Provenance and purities of the used materials are listed in Table 1.

### Dynamic viscosity measuring system

HAAKE MARS 2 rheometer (Thermo Electron Corporation, Karlsruhe, Germany), with the minimum measurable torque of  $0.5 \mu\text{Nm}$ , was used to determine dynamic viscosity of nanofluids. Temperature was stabilized with use of a Peltier element coupled with a Phoenix 2 thermostat (Thermo Electron Corporation, Karlsruhe, Germany). Double cone measurement geometry with 60 mm diameter and cone angle  $1^\circ$  was used. Dynamic viscosity of samples was measured in the range of shear rates from 100 to  $1000 \text{ s}^{-1}$  at a constant temperature of 298.15 K. In addition, to ensure the stability of the measurement conditions, measuring geometry was isolated from the environment by glass rings. All rheological measurements were performed immediately after preparation of samples.

Viscosity of pure ethylene glycol determined in this system was  $16.9 \text{ mPa s}$  with 5% relative standard uncertainty as presented in Ref. [26]. This result correspond with

**Table 1** Provenance and purity of the used materials

Product	Provenance	Mass fraction purity
Ethylene glycol	Avantor performance materials Poland	>0.99
MgO nanopowder	PlasmaChem GmbH	>0.99

results presented by Bohne et al. [53], which reported that viscosity of ethylene glycol at 298.15 K is 16.63 mPa s with 5% uncertainty.

### Thermal conductivity measuring system

KD2 Pro thermal properties analyzer (Decagon Devices Inc., Pullman, Washington, USA) was used to determine thermal conductivity of nanofluids. Detailed description of the calibration process of this measuring system was presented in Ref. [26]. This device uses the transient line heat source method to measure thermal conductivity, resistivity, diffusivity, and specific heat of liquid samples. The dependence of thermal conductivity of MgO–EG nanofluids on the volume fraction of nanoparticles was measured at constant temperature of 298.15 K, stabilized in a water bath MLL 547 (AJL Electronic, Cracow, Poland). After preparation of the samples, the probe was putted inside, and material was thermostated to a temperature of 298.15 K. After 15 min and reaching a predetermined temperature of the sample material was hold another 15 min with probe inside at constant temperature in order to avoid temperature gradients within the sample. The measurement started exactly 30 min after preparation of the sample. The thermal conductivity values presented in this paper were determined as the average of ten measurements, and the time between successive measurements was 15 min, which corresponds to the recommendations of the manufacturer of equipment. All measurements of thermal conductivity were performed immediately after preparation of samples.

## Results and discussion

### Viscosity

Figure 2 presents dependence of viscosity on share rate for MgO–EG nanofluids with various volume fractions of nanoparticles. It might be noticed that the dynamic viscosity is considered constant in the examined range of shear rates. Therefore, it can qualify this nanofluids as Newtonian materials. The increase in the volume fraction of nanoparticles increases the viscosity of the suspension,

but does not change its nature. It can therefore be assumed that the viscosity of nanofluids is constant and designate it as the average of these measurements. The viscosity and the viscosity enhancement of nanofluids relative to the base fluid are listed in Table 2 and presented in Fig. 3.

On the beginning of XX century, Einstein [54] presented first theoretical prediction of viscosity of suspensions. This model was introduced for spherical particles in low volume fractions and has form of:

$$\frac{\eta_{nf}}{\eta_{bf}} = 1 + 2.5\varphi_v, \quad (1)$$

where  $\eta_{nf}$  and  $\eta_{bf}$  are dynamic viscosities of nanofluid and base fluids, respectively, and  $\varphi_v$  is volume fraction.

Einstein's model was the starting point to create other models. Among the most widely used is model presented in 1952. Brinkman presented an expression for the viscosity of suspensions of finite fraction by considering the effect of the addition of one solute-molecule to an existing solution [55]:

$$\frac{\eta_{nf}}{\eta_{bf}} = \frac{1}{(1 - \varphi_v)^{2.5}}. \quad (2)$$

Batchelor [56] took under consideration the hydrodynamic interaction between particles in a statistically homogeneous suspensions and proposed equation:

$$\frac{\eta_{nf}}{\eta_{bf}} = 1 + 2.5\varphi_v + 6.2\varphi_v^2. \quad (3)$$

Coricione [57] presented empirical correlating equation for predicting dynamic viscosity of nanofluids in form:


$$\frac{\eta_{nf}}{\eta_{bf}} = \frac{1}{1 - 34.87(d_p/d_f)^{-0.3}\varphi_v^{1.03}}, \quad (4)$$

where  $d_{bf}$  is the equivalent diameter of a base fluid molecule:

$$d_{bf} = 0.1 \left( \frac{6M}{N\pi\rho_{bf}} \right)^{\frac{1}{3}}, \quad (5)$$

where  $M$  is molecular weight of base fluid and  $N$  is Avogadro number.

On the other hand, it was already presented that nanoparticles in nanofluids form aggregates. When assume that hydrodynamic forces are too weak to break aggregates and aggregates form spherical flow units, the viscosity ratio

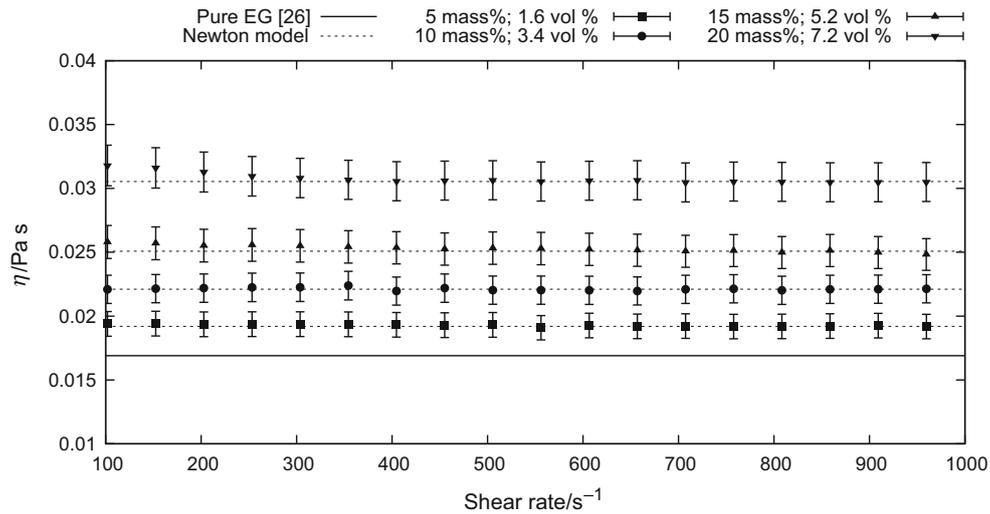

**Fig. 2** Dynamic viscosity curves of MgO-EG nanofluids at 298.15 [K]. Symbols represent measuring points, lines – the theoretical model fits

**Table 2** Experimental values of the viscosity,  $\eta_{nf}$ , of MgO-EG nanofluids at temperature  $T = 298.15$  K for various mass fractions  $\varphi_m$ , and volume fractions  $\varphi_v$

$\varphi_m$	$\varphi_v$	$\eta_{nf}/\text{Pa s}$	$\eta_{nf}/\eta_{bf}$
0.00	0.000	0.01690	1.0000
0.05	0.016	0.01920	1.1361
0.10	0.034	0.02211	1.3083
0.15	0.052	0.02508	1.4840
0.20	0.072	0.03054	1.8071

The estimated standard uncertainty  $u_r(\eta) = 5\%$  and  $u(T) = 0.10\text{K}$

might be modeled with modified Krieger–Dougherty equation:

$$\frac{\eta_{nf}}{\eta_{bf}} = \left( 1 - \frac{\varphi_v}{\varphi_c} \left( \frac{d_a}{d_p} \right)^{3-D} \right)^{-[\eta]\varphi_c}, \tag{6}$$

where  $\varphi_c$  is critical particle packing fraction with the value approximately 0.605,  $D$  is so called fractal index with the value in the range from 1.8 to 2.5 [58],  $[\eta]$  is the intrinsic viscosity with the value of 2.5 for spherical particles,  $d_a$  is effective radius of aggregates, and  $d_p$  is radius of particle. Equation (6) for nanofluids reduces to:

$$\frac{\eta_{nf}}{\eta_{bf}} = \left( 1 - \frac{\varphi_v}{0.605} \left( \frac{d_a}{d_p} \right)^{1.2} \right)^{-1.5125}, \tag{7}$$

as presented in details in Refs. [58–60]. Fitting Eq. (7) to experimental data presented in Table 2 shows that  $d_a/d_p = 2.3$ .

It might be noticed that for volume fraction lower than 0.04 Batchelor model (3) might be modified with effective volume fraction:

$$\varphi_a = \varphi_v \left( \frac{d_a}{d_p} \right)^{3-D}, \tag{8}$$

to the form:

$$\frac{\eta_{nf}}{\eta_{bf}} = 1 + 2.5\varphi_v \left( \frac{d_a}{d_p} \right)^{3-D} + 6.2 \left( \varphi_v \left( \frac{d_a}{d_p} \right)^{3-D} \right)^2. \tag{9}$$

After substituting all values of parameters equation (9) reduces to:

$$\frac{\eta_{nf}}{\eta_{bf}} = 1 + 6.79\varphi_v + 45.76\varphi_v^2. \tag{10}$$

As shown in Fig. 3, this fitting works good in the volume fraction of particles less than 0.04.

Chow [61] proposed variable degree volume fraction polynomial to model the  $\eta_{nf}/\eta_{bf}$  ratio for suspensions of equal size spherical particles in form of:


$$\frac{\eta_{nf}}{\eta_{bf}} = 1 + \sum_{i=1}^N C_i \varphi_v^i, \tag{11}$$

where  $N$  is polynomial degree, and  $C_i$  are the correlation coefficients. To properly model the experimental data, a second degree polynomial was employed:

$$\frac{\eta_{nf}}{\eta_{bf}} = 1 + 6.62\varphi_v + 61.60\varphi_v^2. \tag{12}$$

Fitting parameters were calculated using OriginPro 9.1 (OriginLab Corporation, Northampton, USA) with coefficient of determination  $R^2 = 0.9998$ .

**Fig. 3 a** Dependence of viscosity of MgO–EG nanofluids on volume fraction of particles, and **b** viscosity enhancement of MgO–EG nanofluid at 298.15 K. Symbols represent measuring points, lines—theoretical models

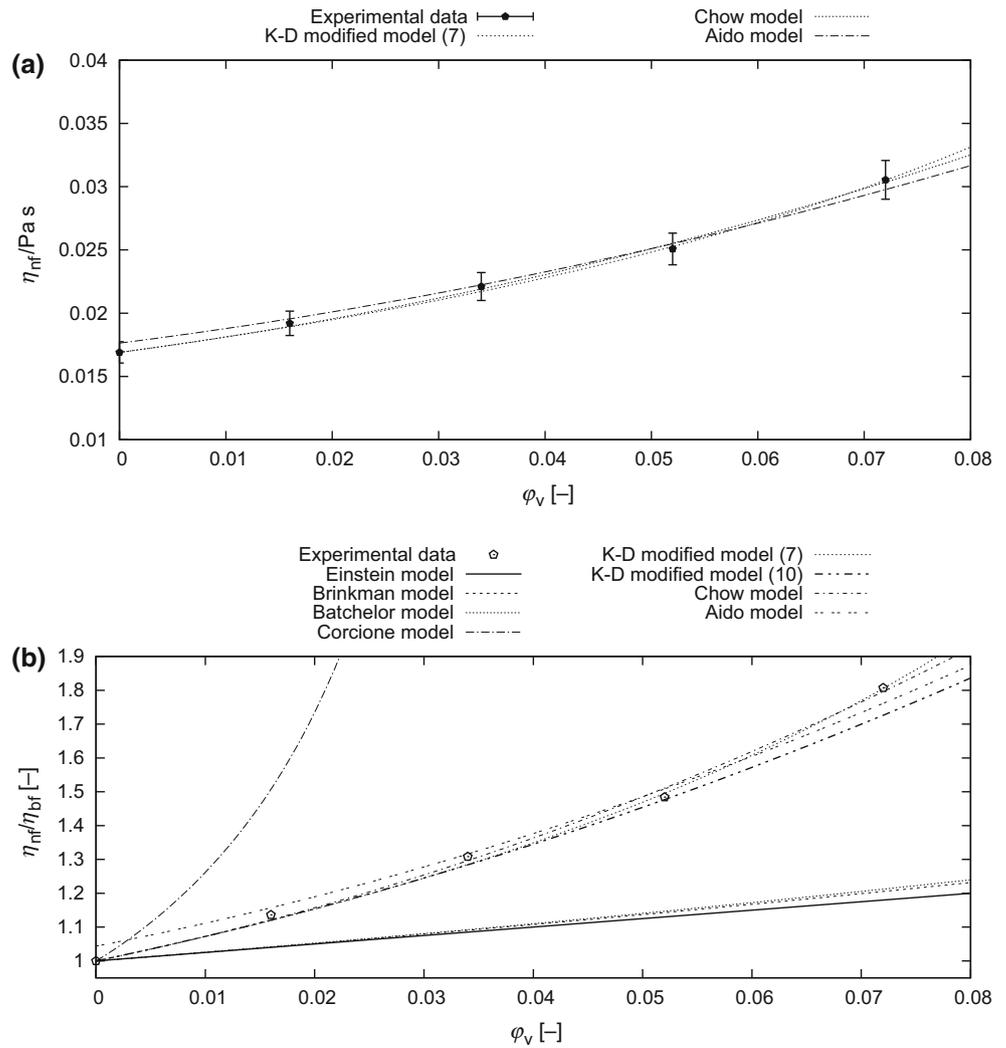

Adio et al. [39] proposed another model introduced specially for MgO–EG nanofluids on the basis of nonlinear regression modeling:

$$\begin{aligned} \frac{\eta_{nf}}{\eta_{bf}} = & 1 + a_0\varphi_v + a_1\left(\frac{T'}{T'_0}\right)\varphi_v + a_2\left(\frac{d_p}{h}\right)\varphi_v \\ & + a_3\left(\left(\frac{d_p}{h}\right)\varphi_v\right)^2 + a_4\left(\left(\frac{T'}{T'_0}\right)\varphi_v\right)^2 \\ & + a_5\varphi_v^2 + a_6\left(\frac{T'}{T'_0}\right)^2\varphi_v^{1/3}, \end{aligned} \quad (13)$$

where  $a_0$ – $a_6$  are empirical constants given as  $a_0 = 7.0764$ ,  $a_1 = -0.1246$ ,  $a_2 = -0.0346$ ,  $a_3 = -0.0024$ ,  $a_4 = -1.2357$ ,  $a_5 = 53.6946$  and  $a_6 = 0.0436$ ,  $T'$  is working temperature in Celsius degrees,  $T'_0$  is reference temperature in Celsius degrees taken as 20 °C,  $h$  is thickness of the capping layer (nanolayer) taken as 1 nm. They assumed that this correlation is valid for volume fraction of MgO nanoparticles  $\leq 5\%$ , temperature between 20–70 °C and particle size between 21 and 125 nm.


Figure 3 presented both measuring points, and theoretical models fits. It may be noticed that only the modified K-D (7), Chow (12) and Adio (13) models correctly describes MgO–EG nanofluid in examined volume fraction range.

**Thermal conductivity**

Figure 4 presents results of ten subsequent measurements of thermal conductivity, and the average calculated based on them. These results show that MgO–EG nanofluids were stable several hours after preparation.

The results of experimental studies are summarized in Table 3. Additionally, there is a column that presents thermal conductivity enhancement in this material. The obtained results show that the thermal conductivity increases with increasing fraction of nanoparticles in suspensions.

Figure 5 present dependence of thermal conductivity on volume fraction of particles of MgO–EG nanofluids at constant temperature 298.15 K.

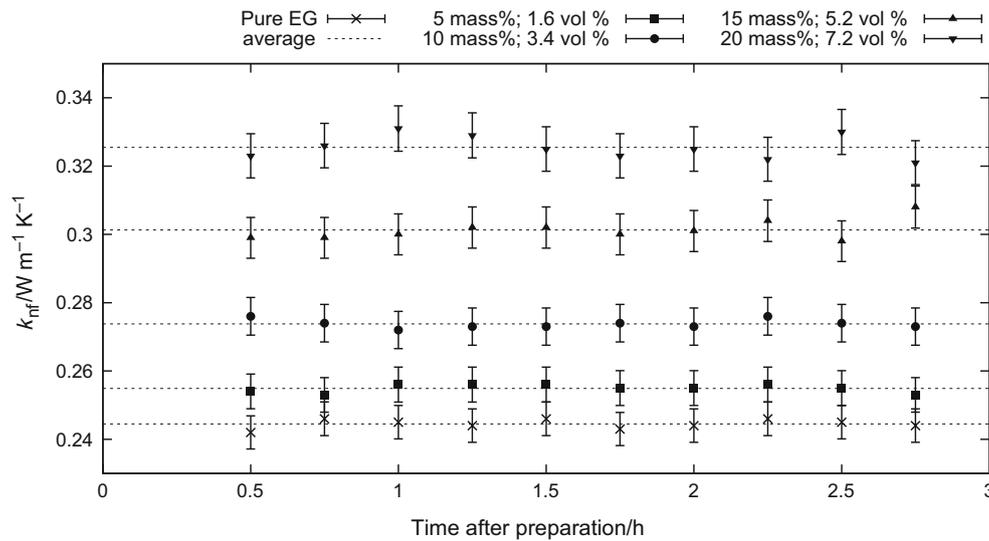

**Fig. 4** Time dependence of thermal conductivity for various volume fractions of nanoparticles

**Table 3** Experimental values of the thermal conductivity,  $k_{nf}$ , of MgO–EG nanofluids at temperature  $T = 298.15K$  for various mass fractions  $\varphi_m$ , and volume fractions  $\varphi_v$

$\varphi_m$	$\varphi_v$	$k_{nf}$ W m <sup>-1</sup> K <sup>-1</sup>	$k_{nf}/k_0$
0.00	0.000	0.2445	1.0000
0.05	0.016	0.2549	1.0425
0.10	0.034	0.2738	1.1198
0.15	0.052	0.3013	1.2323
0.20	0.072	0.3255	1.3313

The estimated standard uncertainty  $u_r(k_{nf}) = 2\%$  and  $u(T) = 0.10K$

Historically the first theoretical model describing thermal conductivity of suspension of large spherical particles was introduced by Maxwell [62]:

$$\frac{k_{nf}}{k_{bf}} = \frac{k_p + 2k_{bf} + 2(k_p - k_{bf})\varphi_v}{k_p + 2k_{bf} - (k_p - k_{bf})\varphi_v}, \tag{14}$$

where  $k_{nf}$ ,  $k_{bf}$ , and  $k_p$  are thermal conductivities of nanofluid, base fluid, and particles, respectively.

Another commonly used model was introduced by Jeffrey [63]. This model was also introduced for suspensions of spherical particles in low fractions, and it assumes that the increase in thermal conductivity is accurate to  $\varphi_v^2$ :

$$\frac{k_{nf}}{k_{bf}} = 1 + 3\beta\varphi_v + \left(3\beta^2 + \frac{3\beta^3}{4} + \frac{9\beta^3}{16} \frac{\gamma + 2}{2\gamma + 3} + \frac{3\beta^4}{64} + \dots\right)\varphi_v^2, \tag{15}$$

where  $\beta = \frac{\gamma-1}{\gamma+2}$ , and  $\gamma = \frac{k_p}{k_{bf}}$ .

Yamada and Ota [64] introduced a similar model in form of:

$$\frac{k_{nf}}{k_{bf}} = \frac{1 + K\alpha + K(1 - \alpha)\varphi_v}{1 + K\alpha - (1 - \alpha)\varphi_v}, \tag{16}$$

where  $\alpha = \frac{k_{bf}}{k_p}$  and  $K$  factor depends on shape of particles. For spherical particles  $K = 2\varphi_v^{-0.2}$ , and for cylindrical particles  $K = 2\varphi_v^{0.2}(a/b)$ , and  $2a$  and  $b$  are the length and radius of cylindrical particle, respectively.

Another modification of Maxwell model dedicated for carbon nanotubes based composites was presented by Xue [65]

$$\frac{k_{nf}}{k_{bf}} = \frac{1 - \varphi_v + 2\varphi_v \frac{k_p}{k_p - k_{bf}} \ln \frac{k_p + k_{bf}}{2k_{bf}}}{1 - \varphi_v + 2\varphi_v \frac{k_{bf}}{k_p - k_{bf}} \ln \frac{k_p + k_{bf}}{2k_{bf}}}. \tag{17}$$

This model relates the thermal conductivity enhancement only with volume fraction, and other factors like geometry of particles were neglected.


Turian et al. [66] presented model based on experimental results for thermal conductivities of suspensions of particulate coals in water, in fuel oil and in other liquids:

$$\frac{k_{nf}}{k_{bf}} = \frac{k_p^{\varphi_v} k_{bf}^{1-\varphi_v}}{k_{bf}}. \tag{18}$$

Esfe et al. [43] used artificial neural network to predict thermal conductivity enhancement in MgO–EG nanofluids. They introduced empirical correlation to calculate the thermal conductivity ratio for MgO–EG nanofluids. The correlation as a function of volume fraction, temperature, and particle diameter can be written as follows:

$$\frac{k_{nf}}{k_{bf}} = A + (B \cdot T') + (C \cdot \varphi_v) + (D \cdot d_p) + (E \cdot (T'^2)) + (F \cdot (\varphi_v^2)) + (G \cdot d_p^2). \tag{19}$$

**Fig. 5 a** Dependence of thermal conductivity of MgO–EG nanofluids on volume fraction of particles, and **b** Thermal conductivity enhancement of MgO–EG nanofluid at 298.15 K. Symbols represent measuring points, lines— theoretical models

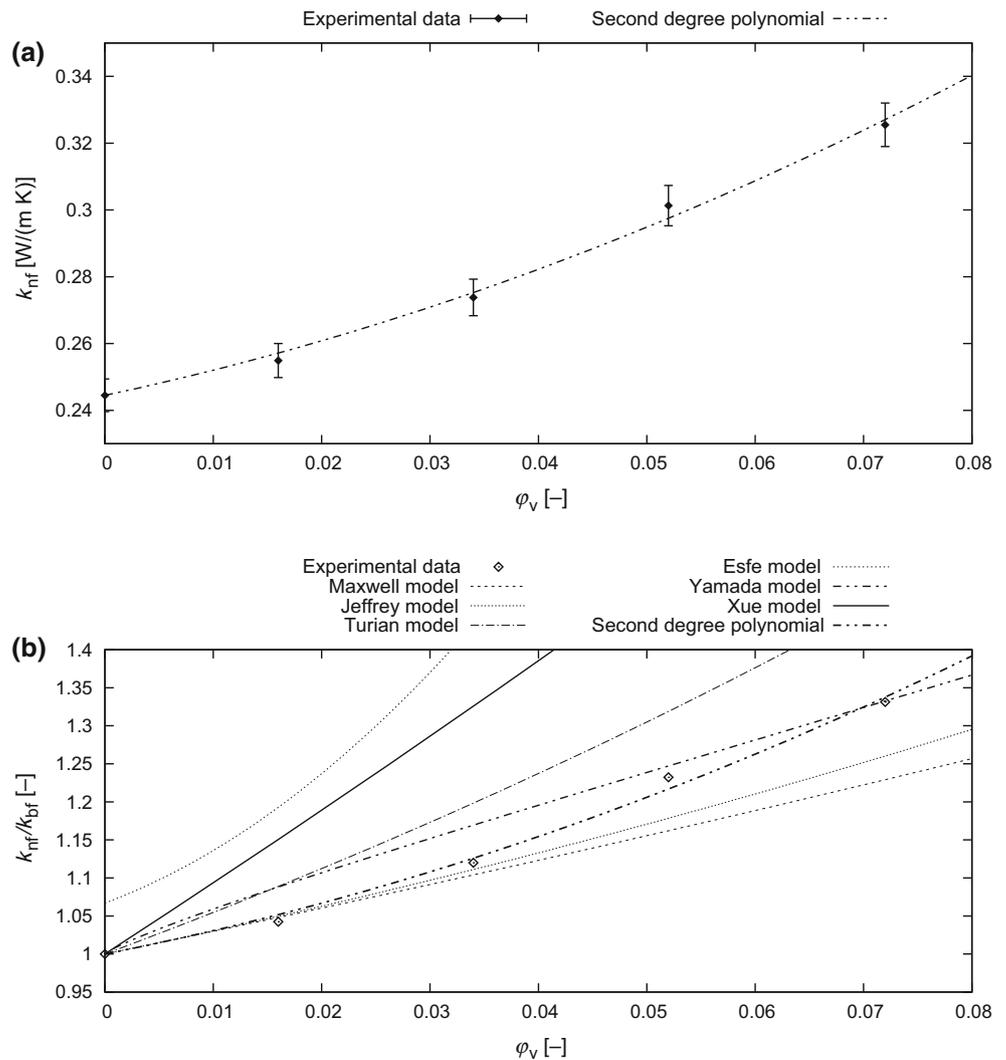

This model was proposed for volume fractions less than 5%, the temperature range between 25 and 55 °C, and particle size between 20 and 60 nm. Constants of proposed correlation were calculated by them as:  $A = 1.1461, B = 0.0052, C = 5.3056, D = -0.0159, E = -7.09 \cdot 10^{-5}, F = 160, G = 3.83 \cdot 10^{-4}$ .

Also, as in the case of an increase in viscosity, thermal conductivity enhancement can be described using a second degree polynomial:

$$\frac{k_{nf}}{k_{bf}} = 1 + 2.82\phi_v + 25.97\phi_v^2 \tag{20}$$

Fitting parameters were calculated using OriginPro 9.1,  $R^2 = 0.9999$ .

Figure 5b presents experimental results and theoretical models for thermal conductivity enhancement depending on volume fraction. As presented on Fig. 5a, only Eq. (20) models thermal conductivity of MgO–EG nanofluids correctly.

**Evaluation of heat transfer performance: an engineering approach**


Based on viscosity and thermal conductivity enhancement, it is possible to perform evaluation of heat transfer performance. When consider using nanofluids in laminar flow, it might be compared on the base of ratio of enhancement in viscosity and thermal conductivity as presented by Prasher et al. [67]:

$$\frac{C_\eta}{C_k} = \frac{(\eta_{nf} - \eta_{bf})/\eta_{bf}}{(k_{nf} - k_{bf})/k_{bf}} \tag{21}$$

When this ratio is less than 4, nanofluid might be consider as beneficial for use in energy transport systems.

Benefits from use particular nanofluid for heat transfer performance in turbulent flow might be evaluated on the base of the Mouromtseff number [68]:

$$Mo = \frac{\rho^{0.8} k^{0.67} c_p^{0.33}}{\eta^{0.47}} \tag{22}$$

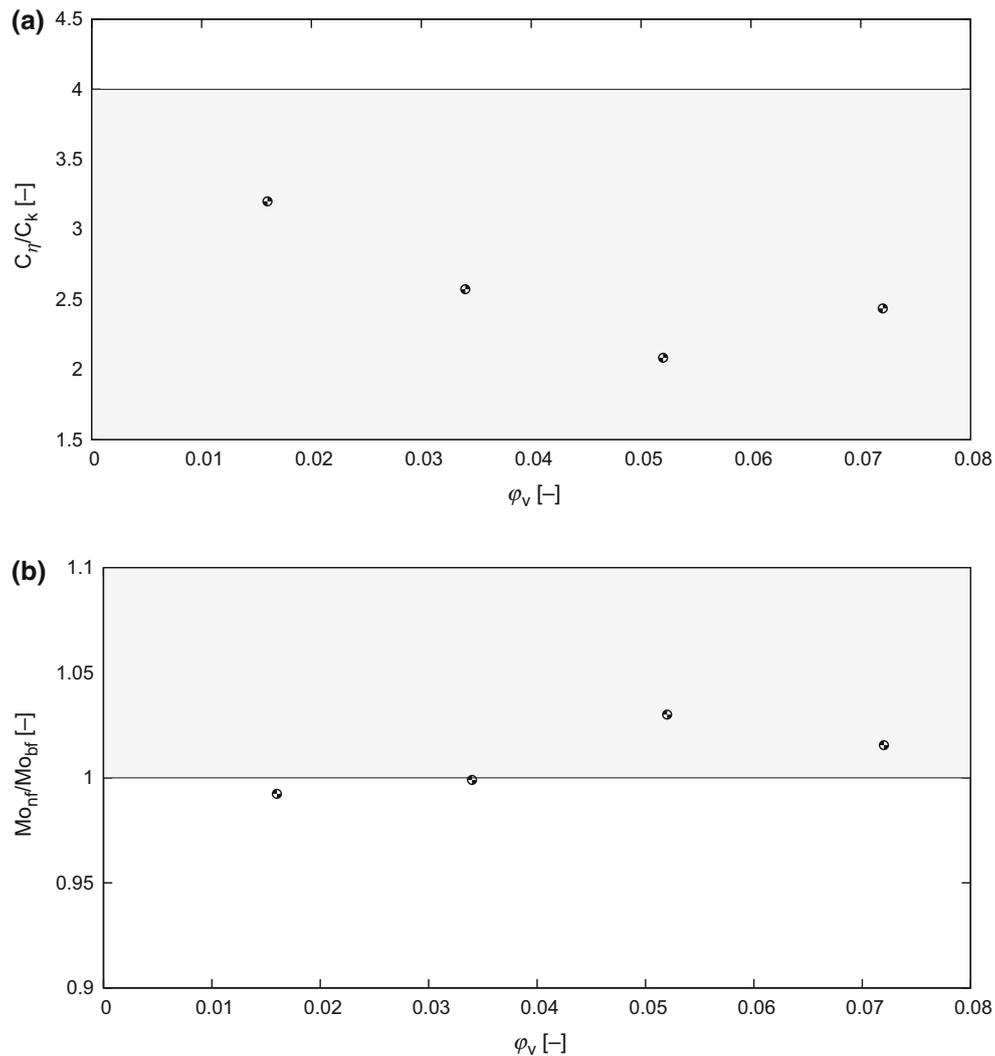

**Fig. 6** Dependence of **a**  $C_\eta/C_k$ , and **b**  $Mo_{nf}/Mo_{bf}$  ratios on volume fraction of particles in MgO–EG nanofluids at constant temperature 298.15 K. Grey areas are beneficial for **a** laminar, and **b** turbulent flows

where  $\rho$  is density and  $c_p$  is specific heat (at constant pressure). Nanofluids with higher Mo number present better heat transport capabilities. When the ratio of Mo number for nanofluid is higher than base liquid, then material might evaluate as beneficial for turbulent flow applications:

$$\frac{Mo_{nf}}{Mo_{bf}} > 1. \quad (23)$$

Viscosity and thermal conductivity necessary to calculate the Mo number was presented in this paper, and density and specific heat of nanofluids might be calculated as presented by Pak and Cho [69]:

$$\rho_{nf} = (1 - \phi_v)\rho_{bf} + \phi_v\rho_p, \quad (24)$$

$$c_{p,nf} = (1 - \phi_v)c_{p,bf} + \phi_vc_{p,p}. \quad (25)$$

The values of specific heat of MgO and ethylene glycol are well known and reported in the literature [51, 70], so it is possible to compare nanofluids with pure ethylene glycol based on their thermal properties. Figure 6 presents results of this evaluation. It is clearly visible that the greatest benefits for both applications for laminar and turbulent flows exhibit nanofluid with 0.052 volume fraction of particles.

## Conclusions

The paper presents results of research on basic thermo-physical properties of MgO–EG nanofluids. It was presented that with increasing volume fraction of nanoparticles in suspension viscosity of the material

increase. At the same time, it was confirmed that the material exhibit Newtonian nature. It was also confirmed that the empirical model proposed by Adio et al. (13) describes the enhancement of the viscosity in MgO–EG nanofluids correctly. It was presented that it is possible to model an increase of the viscosity by using modified K-D model (7) a second degree polynomial (12). It has been shown that the enhancement of thermal conductivity can be modeled also by using a second degree polynomial (20), and the classical models of thermal conductivity do not describe the MgO–EG nanofluids correctly. Comparison of MgO–EG nanofluids with pure ethylene glycol from the point of view of the benefits for applications in laminar and turbulent flows exhibits that nanofluid with 0.052 volume fraction of particles presents the best heat transfer capabilities.

**Acknowledgements** Author wish to thank Piotr Sagan (University of Rzeszow) for the SEM picture of nanoparticles.

**Open Access** This article is distributed under the terms of the Creative Commons Attribution 4.0 International License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made.

## References

- Taylor R, Coulombe S, Otanicar T, Phelan P, Gunawan A, Lv W, Rosengarten G, Prasher R, Tyagi H. Small particles, big impacts: a review of the diverse applications of nanofluids. *J Appl Phys*. 2013;113(1):011301.
- Saidur R, Leong K, Mohammad H. Application of nanofluids in heat exchangers: a review. *Renew Sustain Energy Rev*. 2011;15(3):1646.
- Joseph A, Mathew S. *ChemPlusChem*. 2014;79(10):1382.
- Mahian O, Kianifar A, Kalogirou SA, Pop I, Wongwises S. A review of the applications of nanofluids in solar energy. *Int J Heat Mass Transf*. 2013;57(2):582.
- Huminc G, Huminc A. Application of nanofluids in heat exchangers: a review. *Renew Sustain Energy Rev*. 2012;16(8):5625.
- Navas H, Estellé P, Begin D, Gleize J, Ghanbaja J, Desforges A, Vigolo B. Conference paper: Graphene-based nanofluids for heat transfer applications. *FEMS Junior Euromat July 2016*.
- Senthilraja S, Karthikeyan M, Gangadevi R. Nanofluid applications in future automobiles: comprehensive review of existing data. *Nano-Micro Lett*. 2011;2(4):306.
- Sidik NAC, Yazid MNAWM, Mamat R. A review on the application of nanofluids in vehicle engine cooling system. *Int Commun Heat Mass Transf*. 2015;68:85.
- Bashimezhad K, Rashidi MM, Yang Z, Bazri S, Yan WM. A comprehensive review of last experimental studies on thermal conductivity of nanofluids. *J Therm Anal Calorim*. 2015;122(2):863.
- Pastoriza-Gallego M, Lugo L, Legido J, Piñeiro M. Thermal conductivity and viscosity measurements of ethylene glycol-based Al<sub>2</sub>O<sub>3</sub> nanofluids. *Nanoscale Res Lett*. 2011;6(1):221.
- Wang B, Hao J, Li H. Remarkable improvements in the stability and thermal conductivity of graphite/ethylene glycol nanofluids caused by a graphene oxide percolation structure. *Dalton Trans*. 2013;42:5866.
- Ahamed N, Asirvatham LG, Wongwises S. Effect of volume concentration and temperature on viscosity and surface tension of graphene-water nanofluid for heat transfer applications. *J Therm Anal Calorim*. 2016;123(2):1399.
- Toghraie D, Chaharsoghi VA, Afrand M. Measurement of thermal conductivity of ZnO–TiO<sub>2</sub>/EG hybrid nanofluid. *J Therm Anal Calorim*. 2016;125(1):527–35.
- Mariano A, Pastoriza-Gallego MJ, Lugo L, Camacho A, Canzonieri S, Pineiro MM. Thermal conductivity, rheological behaviour and density of non-Newtonian ethylene glycol-based SnO<sub>2</sub> nanofluids. *Fluid Phase Equilib*. 2013;337:119.
- Li X, Zou C, Lei X, Li W. Stability and enhanced thermal conductivity of ethylene glycol-based SiC nanofluids. *Int J Heat Mass Transf*. 2015;89:613.
- Raei B, Shahraki F, Jamialahmadi M, Peyghambarzadeh SM. Experimental study on the heat transfer and flow properties of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>/water nanofluid in a double-tube heat exchanger. *J Therm Anal Calorim*. 2016. doi:10.1007/s10973-016-5868-x
- Kumar BR, Basheer NS, Jacob S, Kurian A, George SD. Thermal-lens probing of the enhanced thermal diffusivity of gold nanofluid–ethylene glycol mixture. *J Therm Anal Calorim*. 2015;119(1):453.
- Suganthi K, Vinodhan VL, Rajan K. Heat transfer performance and transport properties of ZnO–ethylene glycol and ZnO–ethylene glycol–water nanofluid coolants. *Appl Energy*. 2014;135:548.
- Pastoriza-Gallego M, Lugo L, Cabaleiro D, Legido J, Pineiro M. Thermophysical profile of ethylene glycol-based ZnO nanofluids. *J Chem Thermodyn*. 2014;73:23.
- Mariano A, Pastoriza-Gallego MJ, Lugo L, Mussari L, Pineiro MM. Co<sub>3</sub>O<sub>4</sub> ethylene glycol-based nanofluids: thermal conductivity, viscosity and high pressure density. *Int J Heat Mass Transf*. 2015;85:54.
- Yu W, Xie H, Li Y, Chen L, Wang Q. Experimental investigation on the thermal transport properties of ethylene glycol based nanofluids containing low volume concentration diamond nanoparticles. *Colloids Surf A Physicochem Eng Asp*. 2011;380(1–3):1.
- Żyła G, Fal J, Traciak J, Gizowska M, Perkowski K. Huge thermal conductivity enhancement in boron nitride–ethylene glycol nanofluids. *Mater Chem Phys*. 2016;180:250.
- Shamaeil M, Firouzi M, Fakhar A. The effects of temperature and volume fraction on the thermal conductivity of functionalized DWCNTs/ethylene glycol nanofluid. *J Therm Anal Calorim*. 2016;126(3):1455–62.
- Esfe MH, Ahangar MRH, Toghraie D, Hajmohammad MH, Rostamian H, Tourang H. Designing artificial neural network on thermal conductivity of Al<sub>2</sub>O<sub>3</sub>–water–EG (60–40%) nanofluid using experimental data. *J Therm Anal Calorim*. 2016;126(2):1.
- Beheshti A, Shanbedi M, Heris SZ. Heat transfer and rheological properties of transformer oil-oxidized MWCNT nanofluid. *J Therm Anal Calorim*. 2014;118(3):1451.
- Żyła G. Thermophysical properties of ethylene glycol based yttrium aluminum garnet (Y<sub>3</sub>Al<sub>5</sub>O<sub>12</sub>-EG) nanofluids. *Int J Heat Mass Transf*. 2016;92:751.
- Chadwick M, Goodwin J, Vincent B, Lawson E, Mills P. Rheological behaviour of titanium dioxide (uncoated anatase) in ethylene glycol. *Colloids Surf A Physicochem Eng Asp*. 2002;196(2–3):235.

28. Duan F, Wong T, Crivoi A. Dynamic viscosity measurement in non-Newtonian graphite nanofluids. *Nanoscale Res Lett*. 2012;7(1):360.
29. Li X, Zou C, Wang T, Lei X. Rheological behavior of ethylene glycol-based SiC nanofluids. *Int J Heat Mass Transf*. 2015;84:925.
30. Pastoriza-Gallego M, Lugo L, Legido J, Piñeiro M. Rheological non-Newtonian behaviour of ethylene glycol-based Fe<sub>2</sub>O<sub>3</sub> nanofluids. *Nanoscale Res Lett*. 2011;6(1):560.
31. Żyła G, Fal J, Gizowska M, Witek A, Cholewa M. Dynamic viscosity of aluminum oxide-ethylene glycol (Al<sub>2</sub>O<sub>3</sub>-EG) nanofluids. *Acta Phys Polon A*. 2015;128(2):240.
32. Żyła G, Witek A, Gizowska M. Rheological profile of boron nitride-ethylene glycol nanofluids. *J Appl Phys*. 2015;117(1):014302.
33. Żyła G, Fal J. Experimental studies on viscosity, thermal and electrical conductivity of aluminum nitride-ethylene glycol (AlN-EG) nanofluids. *Thermochim Acta*. 2016;637:11.
34. Fal J, Barylyak A, Besaha K, Bobitski YV, Cholewa M, Zawlik I, Szmuc J, Cebulski Kamiland, Żyła G. Experimental investigation of electrical conductivity and permittivity of SC-TiO<sub>2</sub>-EG Nanofluids. *Nanoscale Res Lett*. 2016;11(1):1.
35. Fal J, Cholewa M, Gizowska M, Witek A, Żyła G. Dielectric properties of boron nitride-ethylene glycol (BN-EG) nanofluids. *J Electron Mater*. 2016 (in press).
36. Hadadian M, Goharshadi EK, Youssefi A. Electrical conductivity, thermal conductivity, and rheological properties of graphene oxide-based nanofluids. *J Nanopart Res*. 2014;16(12):1.
37. Razali MZB, Khair MSA, Zakaria IA, Mohamed WANW. Effect of temperature towards electrical conductivities of low concentration of Al<sub>2</sub>O<sub>3</sub> nanofluid in electrically active cooling system. In: Control system, computing and engineering (ICCSC), IEEE international conference on IEEE; 2014. pp. 444-448.
38. Xie H, Yu W, Chen W. MgO nanofluids: higher thermal conductivity and lower viscosity among ethylene glycol-based nanofluids containing oxide nanoparticles. *J Exp Nanosci*. 2010;5(5):463.
39. Adio SA, Mehrabi M, Sharifpur M, Meyer JP. Experimental investigation and model development for effective viscosity of MgO-ethylene glycol nanofluids by using dimensional analysis, FCM-ANFIS and GA-PNN techniques. *Int Commun Heat Mass Transf*. 2016;72:71.
40. Adio SA, Sharifpur M, Meyer JP. Investigation into the pH and electrical conductivity enhancement of MgO-ethylene glycol nanofluids. In: Proceedings of the 15th international heat transfer conference, Kyoto, paper IHTC15-8604; 2014. pp. 11-15.
41. Adio SA, Sharifpur M, Meyer JP. Factors affecting the pH and electrical conductivity of MgO-ethylene glycol nanofluids. *Bull Mater Sci*. 2015;38(5):1345.
42. Yu W, Xie HQ, Li Y, Chen LF. The thermal transport properties of ethylene glycol based MGO nanofluids. In: ASME 2009 7th international conference on nanochannels, microchannels, and minichannels. American Society of Mechanical Engineers; 2009. pp. 901-905.
43. Esfe MH, Saedodin S, Bahiraei M, Toghraie D, Mahian O, Wongwises S. Thermal conductivity modeling of MgO/EG nanofluids using experimental data and artificial neural network. *J Therm Anal Calorim*. 2014;118(1):287.
44. Shoghl SN, Jamali J, Moraveji MK. Electrical conductivity, viscosity, and density of different nanofluids: an experimental study. *Exp Therm Fluid Sci*. 2016;74:339-46.
45. Menlik T, Sözen A, Gürü M, Öztaş S. Heat transfer enhancement using MgO/water nanofluid in heat pipe. *J Energy Inst*. 2015;88(3):247.
46. Esfe MH, Saedodin S, Mahmoodi M. Experimental studies on the convective heat transfer performance and thermophysical properties of MgO-water nanofluid under turbulent flow. *Exp Therm Fluid Sci*. 2014;52:68.
47. Davarnejad R, Jamshidzadeh M. CFD modeling of heat transfer performance of MgO-water nanofluid under turbulent flow. *Eng Sci Technol Int J*. 2015;18(4):536.
48. Manikandan S, Rajan K. MgO-Therminol 55 nanofluids for efficient energy management: analysis of transient heat transfer performance. *Energy*. 2015;88:408.
49. Manikandan S, Rajan KS. Rapid synthesis of MgO nanoparticles and their utilization for formulation of a propylene glycol based nanofluid with superior transport properties. *RSC Adv*. 2014;4(93):51830.
50. Hofmeister AM. Thermal diffusivity and thermal conductivity of single-crystal MgO and Al<sub>2</sub>O<sub>3</sub> and related compounds as a function of temperature. *Phys Chem Miner*. 2014;41(5):361.
51. Madelung USM, Rössler, O (ed.). Magnesium oxide (MgO) Debye temperature, heat capacity, density, melting and boiling points, hardness. II-VI and I-VII Compounds; Semimagnetic Compounds. Berlin: Springer; 1999.
52. Yang C, Ma P, Jing F, Tang D. *J Chem Eng Data*. 2003;48(4):836.
53. Bohne D, Fischer S, Obermeier E. Thermal, conductivity, density, viscosity, and prandtl-numbers of ethylene glycol-water mixtures. *Berichte der Bunsengesellschaft für physikalische Chemie*. 1984;88(8):739.
54. Einstein A. Eine neue Bestimmung der Molekul-dimension (a new determination of the molecular dimensions). *Annalen der Physik*. 1906;19(2):289.
55. Brinkman H. The viscosity of concentrated suspensions and solutions. *J Chem Phys*. 1952;20(4):571.
56. Batchelor G. The effect of Brownian motion on the bulk stress in a suspension of spherical particles. *J Fluid Mech*. 1977;83(pt 1):97.
57. Corcione M. Empirical correlating equations for predicting the effective thermal conductivity and dynamic viscosity of nanofluids. *Energy Convers Manag*. 2011;52(1):789.
58. Chen H, Ding Y, Tan C. Rheological behaviour of nanofluids. *N J Phys*. 2007;9(10):367.
59. Zeinali Heris S, Razbani M, Estellé P, Mahian O. Rheological behavior of zinc-oxide nanolubricants. *J Dispers Sci Technol*. 2015;36(8):1073.
60. Halefadi S, Estellé P, Aladag B, Doner N, Maré T. Viscosity of carbon nanotubes water-based nanofluids: influence of concentration and temperature. *Int J Therm Sci*. 2013;71:111.
61. Chow TS. Viscosities of concentrated dispersions. *Phys Rev E*. 1993;48:1977.
62. Maxwell JC. A treatise on electricity and magnetism. 3rd ed. London: Oxford University Press; 1892.
63. Jeffrey DJ. Conduction through a random suspension of spheres. *Proc R Soc Lond A Math Phys Sci*. 1973;335(1602):355.
64. Yamada APE, Ota APT. Effective thermal conductivity of dispersed materials. *Wärme-und Stoffübertragung*. 1980;13(1-2):27.
65. Xue Q. Model for thermal conductivity of carbon nanotube-based composites. *Phys B Condens Matter*. 2005;368(1-4):302.
66. Turian RM, Sung DJ, Hsu FL. Thermal conductivity of granular coals, coal-water mixtures and multi-solid/liquid suspensions. *Fuel*. 1991;70(10):1157.
67. Prasher R, Song D, Wang J, Phelan P. Measurements of nanofluid viscosity and its implications for thermal applications. *Appl Phys Lett*. 2006;89(13):133108.
68. Mourmteff I. Water and forced-air cooling of vacuum tubes nonelectronic problems in electronic tubes. *Proc IRE*. 1942;30(4):190.
69. Pak BC, Cho YI. Hydrodynamic and heat transfer study of dispersed fluids with submicron metallic oxide particles. *Exp Heat Transf Int J*. 1998;11(2):151.
70. Nan Z, Liu B, Tan Z. Calorimetric investigation of excess molar heat capacities for water+ ethylene glycol from  $T = 273.15$  to  $T = 373.15$  K. *J Chem Thermodyn*. 2002;34(6):915.