

# Synthesis, Crystal Structure and Luminescent Property of a New Two-Dimensional Zn(II) Coordination Polymer Based on Oxalic Acid and 1,4-Bis(imidazol-1-ylmethyl)-benzene

Qing-Wei Wang · Xiao-Fei Qi · Xiu-Mei Li ·  
Jian-Ye Ji · Yan-Ling Niu · Bo Liu

Received: 18 April 2013 / Accepted: 29 July 2013 / Published online: 13 August 2013  
© The Author(s) 2013. This article is published with open access at Springerlink.com

**Abstract** A new Zn(II) coordination polymer based on oxalic acid and 1,4-bis(imidazol-1-ylmethyl)benzene (bix), namely,  $[\text{Zn}(\text{C}_2\text{O}_4)(\text{bix})]_n$  (**1**), has been successfully synthesized under hydrothermal conditions. Its structure has been determined by single crystal X-ray diffraction analysis, elemental analyses and IR spectroscopy. Compound **1** shows a two-dimensional (2D) layer structure. The intermolecular C–H···O interactions extend the compound **1** into 3D supramolecular architectures and play an important role in stabilizing compound **1**. In addition, the luminescent property of the compound has also been investigated in solid state at room temperature.

**Keywords** Hydrothermal synthesis · Crystal structure · Coordination polymer

## 1 Introduction

Researches on the metal-directed extended networks have drawn great attention owing not only to their intriguing structural motifs but also to their potential applications in

catalysis, medicine, hostguest chemistry and molecular-based magnetic materials [1–5]. In this field, the metals often have different valences, making a number of building blocks to fulfill special needs. Many important properties of coordination polymers depend largely on their structures and topology. Therefore, the selection of special inorganic and organic building blocks is the key to the construction of a desired framework [6]. In this respect, the oxalate ligand is proved to be a good candidate due to its various bridging abilities and strong coordination tendency with transition metals to form 2- and 3-D moderately robust networks exhibiting tunable ferro- or antiferro-magnetic exchanges [7–9]. On the other hand, the introduction of bi- or multi-dentate ligands containing N- or O-donors to the metal-oxalate system may lead to new structural evolution since the binding of these ligands to metal centers may adjust the dimensionality of metalorganic coordination polymers [10, 11]. Among the organic N-donors, 1,4-bis(imidazol-1-ylmethyl)-benzene (bix) is an excellent ligand for the construction of novel metal–organic coordination frameworks because of its two donor sites [12]. In this paper, we report a new Zn(II) coordination polymer  $[\text{Zn}(\text{C}_2\text{O}_4)(\text{bix})]_n$ , in which the 1D chains are held together via bix ligands to form a two-dimensional layer structure. Such 2D structure geometry is reported scarcely.

**Electronic supplementary material** The online version of this article (doi:10.1007/s10904-013-9924-8) contains supplementary material, which is available to authorized users.

Q.-W. Wang (✉) · X.-F. Qi · B. Liu  
Key Laboratory of Preparation and Applications  
of Environmental Friendly Materials, Ministry of Education,  
College of Chemistry, Jilin Normal University, Siping 136000,  
People's Republic of China  
e-mail: wqw611223@163.com

X.-M. Li · J.-Y. Ji · Y.-L. Niu  
Faculty of Chemistry, Tonghua Normal University,  
Tonghua 134002, People's Republic of China

## 2 Experimental Section

### 2.1 General Procedures

All reagents were purchased commercially and used without further purification. Elemental analyses (C, H and N) were measured on a Perkin-Elmer 2400 CHN Elemental Analyzer. IR spectrum was recorded in the range of

4,000–400  $\text{cm}^{-1}$  on an Alpha Centaur FT/IR Spectrophotometer using a KBr pellet. The fluorescent studies were carried out on a computer-controlled JY Fluoro-Max-3 spectrometer at room temperature.

## 2.2 Synthesis of $[\text{Zn}(\text{C}_2\text{O}_4)(\text{bix})]_n$ (**1**)

The title compound was prepared from a mixture of  $\text{Zn}(\text{OAc})_2 \cdot 2\text{H}_2\text{O}$  (0.044 g, 0.2 mmol),  $\text{H}_2\text{C}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$  (0.050 g, 0.4 mmol), bix (0.048 g, 0.2 mmol) and  $\text{H}_2\text{O}$  (18 mL) in a 30 mL Teflon-lined stainless steel vessel, and then the vessel was sealed and heated at 150 °C for 7 days. After the reaction mixture was slowly cooled down to room temperature at the rate of 5 °C/h, pale yellow block crystals of compound **1** were obtained. Yield: 52 %. Anal. Calcd. For  $\text{C}_{16}\text{H}_{14}\text{N}_4\text{O}_4\text{Zn}$ : C, 49.06; H, 3.60; N, 14.30. Found C, 49.01; H, 3.58; N, 14.27. IR ( $\text{cm}^{-1}$ ): 3,103(w), 1,671(vs), 1,609(vs), 1,515(m), 1,313(m), 1,231(m), 1,112(m), 940(m), 796(m), 720(w), 659(w), 492(w).

## 2.3 X-ray Crystallographic Study of Compound (**1**)

Single-crystal X-ray diffraction data for **1** was recorded on a Bruker Smart Apex II CCD diffractometer with graphite-monochromated Mo  $\text{K}\alpha$  radiation ( $\lambda = 0.71073$  Å) at 293 K. The structure was solved with the direct method of SHELXS-97 and refined with full-matrix least-squares techniques using the SHELXL-97 program [13, 14]. The non-hydrogen atoms of the complexes were refined with anisotropic temperature parameters. The hydrogen atoms attached to carbons were generated geometrically. Crystallographic parameters and the data collection statistics for structure **1** are given in Table 1. Selected bond lengths and bond angles are listed in Table 2. Further crystallographic parameters have been deposited with the Cambridge Crystallographic Data Centre (no. 874947; deposit@ccdc.cam.ac.uk or [http://www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif)).

## 3 Results and Discussion

### 3.1 Syntheses and General Characterization

The new  $\text{d}^{10}$  metal complex reported here was simply synthesized under hydrothermal reaction condition. Complex **1** was controlled by the amount of triethylamine. In the reaction the molar ratio of  $\text{Zn}(\text{OAc})_2 \cdot 2\text{H}_2\text{O}$  with bix,  $\text{H}_2\text{C}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$  was kept at 1:1:2. However, the resulting products show small crystals when heating at 120 °C, yield: 35 %; when heating at 150 °C, block crystals suitable for the determination of X-ray were obtained, yield: 52 %.

**Table 1** Crystallographic parameters and summary of data collection for **1**

Parameter	Value
Empirical formula	$\text{C}_{16}\text{H}_{14}\text{N}_4\text{O}_4\text{Zn}$
Fw	391.68
Crystal system	Monoclinic
Space group	C2/c
$a$ [Å]	11.5588(18)
$b$ [Å]	15.664(2)
$c$ [Å]	9.2687(14)
$\alpha$ [°]	90
$\beta$ [°]	101.764(2)
$\gamma$ [°]	90
Volume [Å <sup>3</sup> ]	1642.9(4)
Z	4
$D_c$ (g/cm <sup>3</sup> )	1.584
GOF	1.094
Reflns collected/unique	4484/1636
$R_{\text{int}}$	0.0193
$R1$ [ $I > 2\sigma(I)$ ]	0.0567


**Table 2** Selected bond lengths (Å) and bond angles (deg) for **1**

Bond	$d$ , Å	Bond	$d$ , Å
Zn(1)–N(1)	2.115(3)	Zn(1)–N(1) <sup>#1</sup>	2.115(3)
Zn(1)–O(1)	2.089(3)	Zn(1)–O(1) <sup>#1</sup>	2.089(3)
Zn(1)–O(2) <sup>#2</sup>	2.148(3)	Zn(1)–O(2) <sup>#3</sup>	2.148(3)
Angle	$\omega$ , deg	Angle	$\omega$ , deg
N(1)–Zn(1)–N(1) <sup>#1</sup>	89.75(14)	O(1)–Zn(1)–O(2) <sup>#2</sup>	95.26(11)
O(1) <sup>#1</sup> –Zn(1)–O(1)	171.89(15)	N(1) <sup>#1</sup> –Zn(1)–O(2) <sup>#2</sup>	93.15(14)
O(1) <sup>#1</sup> –Zn(1)–N(1) <sup>#1</sup>	95.43(13)	N(1)–Zn(1)–O(2) <sup>#2</sup>	168.78(12)
O(1)–Zn(1)–N(1) <sup>#1</sup>	90.30(12)	O(1) <sup>#1</sup> –Zn(1)–O(2) <sup>#3</sup>	95.26(11)
O(1) <sup>#1</sup> –Zn(1)–N(1)	90.30(12)	O(1)–Zn(1)–O(2) <sup>#3</sup>	78.73(10)
O(1)–Zn(1)–N(1)	95.43(13)	N(1) <sup>#1</sup> –Zn(1)–O(2) <sup>#3</sup>	71.36(6)
N(1) <sup>#1</sup> –Zn(1)–N(1)	90.2(2)	N(1)–Zn(1)–O(2) <sup>#3</sup>	93.15(14)
O(1) <sup>#1</sup> –Zn(1)–O(2) <sup>#2</sup>	78.73(10)	O(2) <sup>#2</sup> –Zn(1)–O(2) <sup>#3</sup>	85.61(18)
N(1)–Zn(1)–O(2) <sup>#2</sup>	92.80(9)		

Symmetry codes: <sup>#1</sup> 1– $x$ ,  $y$ ,  $-z + 3/2$ ; <sup>#2</sup>  $x$ ,  $-y$ ,  $z + 1/2$ ; <sup>#3</sup> 1– $x$ ,  $-y$ ,  $1-z$

### 3.2 IR Spectrum

The  $\text{COO}^-$  is coordinated with its asymmetric and symmetric stretching appearing at 1,608  $\text{cm}^{-1}$  ( $\nu(\text{OCO})_{\text{asym}}$ ) and 1,428  $\text{cm}^{-1}$  ( $\nu(\text{OCO})_{\text{sym}}$ ) [15], respectively. The  $\Delta\nu$  ( $\nu(\text{OCO})_{\text{asym}} - \nu(\text{OCO})_{\text{sym}}$ ) is 180  $\text{cm}^{-1}$  ( $< 200$ ), showing the presence of bidentate linkage of carboxylates in the dianions. Thus the carboxylates coordinate to the metal as bidentate ligands via the carboxylate groups [16]. The absence of

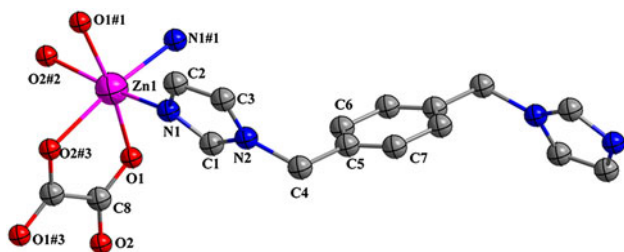


**Fig. 1** The coordination environment (at 30 % probability level) of the Zn(II) center of **1**. Symmetry codes: (#1)  $1-x, y, -z + 3/2$ ; (#2)  $x, -y, z + 1/2$ ; (-3)  $1-x, -y, 1-z$

characteristic bands around  $1,700\text{ cm}^{-1}$  in compound **1** attributed to the protonated carboxylic group indicates the complete deprotonation of  $\text{H}_2\text{C}_2\text{O}_4$  ligand upon reaction with Zn ions [17]. In addition, X-ray diffraction analysis further indicates the bidentate coordination manners of carboxylate groups and the deprotonation of  $\text{H}_2\text{C}_2\text{O}_4$  ligands.


### 3.3 Description of the Structure

A single-crystal X-ray diffraction study reveals that compound **1** crystallizes in the monoclinic space group  $C2/c$

**Fig. 2** Two-dimensional layer structure along the  $a$ -axis of **1**

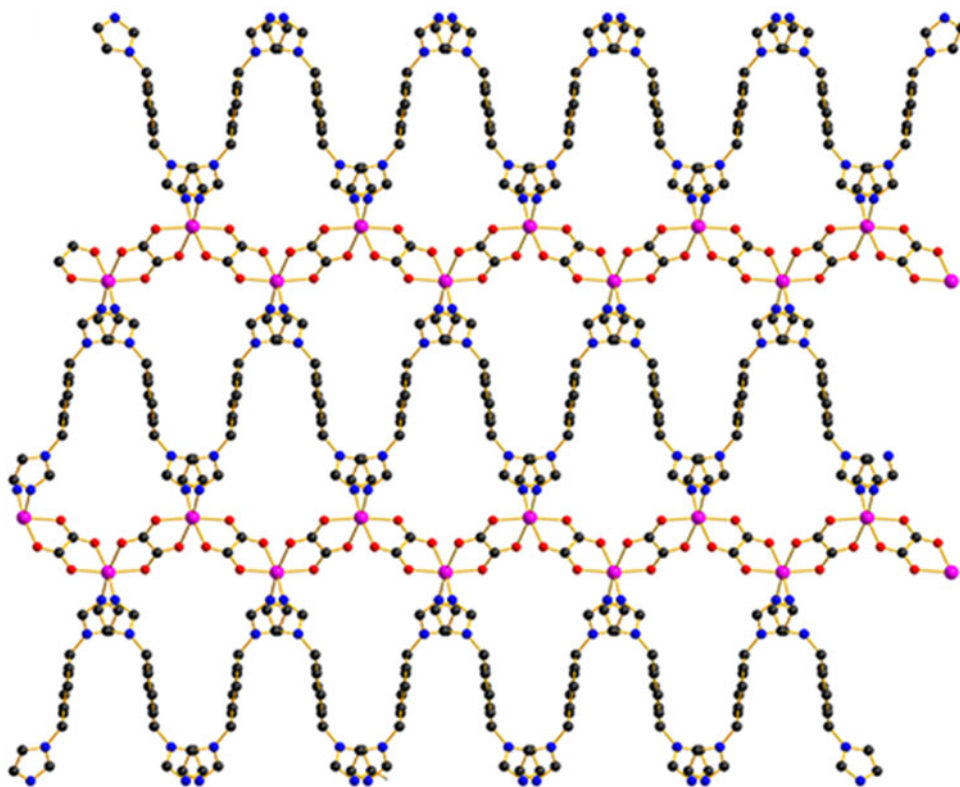

**Fig. 3** View of the 3D supramolecular architecture of **1** formed by hydrogen-bonding interactions

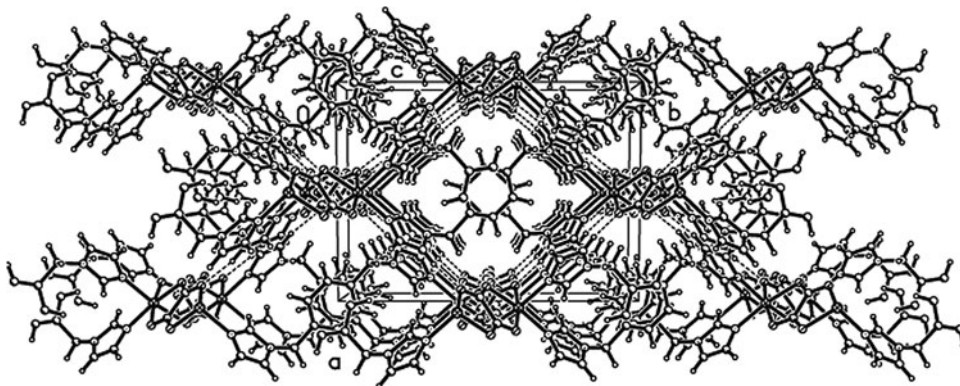


and features a two-dimensional (2D) layer-like structure. The asymmetric unit of **1** contains one six-coordinated Zn(II) atom, one  $C_2O_4^{2-}$  ligand and one bix ligand, as shown in Fig. 1. Each Zn(II) ion is six coordinated with distorted octahedral coordination geometry defined by two nitrogen donors (N(1) and N(1)<sup>#1</sup>) from two different bix molecules and four carboxylate oxygen atoms (O(1), O(1)<sup>#1</sup>, O(2)<sup>#2</sup>, O(2)<sup>#3</sup>) from two different  $C_2O_4^{2-}$  ligands. Three carboxylate oxygen (O(1), O(1)<sup>#1</sup>, O(2)<sup>#3</sup>) and one nitrogen (N(1)<sup>#1</sup>) atom define an equatorial plane, while the axial coordination sites are occupied by carboxylate oxygen (O(2)<sup>#2</sup>) and nitrogen (N(1)) atom. The bond distances of Zn–O in compound **1** fall in the 2.089(3)–2.148(3) Å range, and Zn–N bond length is 2.115(3)–2.115(4) Å, which are in the normal range and the coordination angles around Zn atom are in the range 78.73(10)–168.78(12)°. The completely deprotonated  $C_2O_4^{2-}$  ligands display one kind of coordination mode, namely bidentate bridging mode, and the bix ligand adopts *trans*-conformation bridging mode with a dihedral angle between the two imidazole rings of 0°.

The Zn(II) centers forms a type of 4O+2N mixed neutrality complex, and are interconnected by the bridging oxalate ligands to generate an infinite  $\{Zn_2(C_2O_4)_2\}_\infty$  chain along the *a* axis. The  $Zn \cdots Zn$  separation through the oxalate bridges is 5.667 Å, the neighboring 1D  $\{Zn_2(C_2O_4)_2\}_\infty$  infinite chains are linked via bix ligands to develop into 2D layer framework (Fig. 2), which is similar with our reported paper [18]. In [18], the structure of complex  $([Zn(C_2O_4)(1,3-bix)]_n)$  is 2D network with (4,4) topology. From the packing diagram, we can see that the  $C_2O_4^{2-}$  and bix ligands are also linked by means of C–H $\cdots$ O hydrogen-bonding interactions (C1 $\cdots$ O1 = 3.401(8) Å) which are known to be important in the synthesis of supramolecular architectures [19, 20] and undoubtedly play an important role in stabilizing compound **1** (Fig. 3).


To investigate whether the analyzed crystal structure is truly representative of the bulk materials, X-ray powder diffraction (PXRD) technology has been performed for the complex at room temperature (Fig. 4). The main peak positions observed are in good agreement with the simulated ones. Although minor differences can be found in the positions, widths, and intensities of some peaks, it still can be considered that the bulk synthesized materials and the analyzed crystal are homogeneous. The differences may be due to the preferred orientation of the powder samples [21, 22].

### 3.4 Luminescent Properties

Luminescence property is very important in photochemistry and photophysics [23, 24]. So in this study, the solid-state photoluminescence spectra of **1** (Fig. 5), free

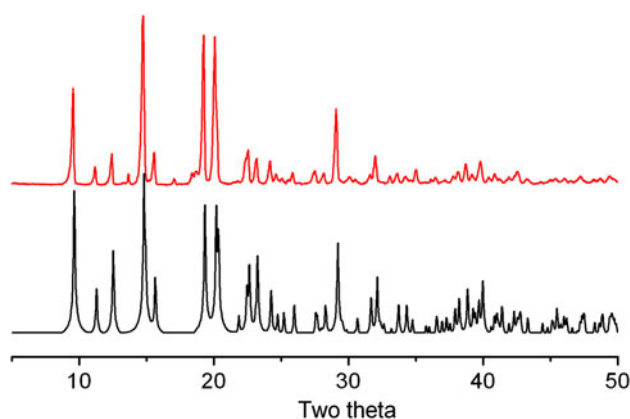

**Fig. 4** PXRD analysis of the title complex: bottom-simulated, top-experimental

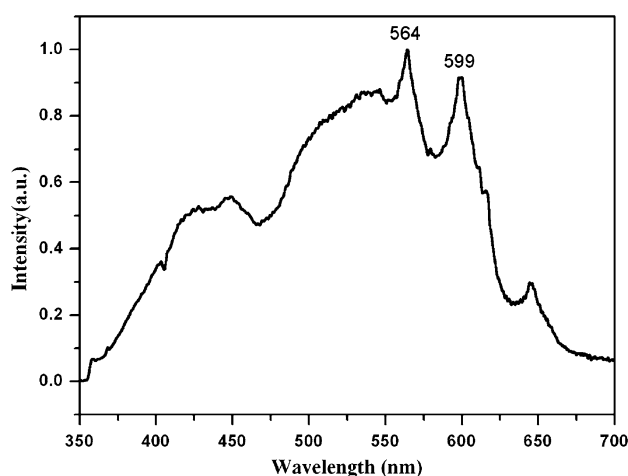


**Fig. 5** Solid-state emission spectrum of **1** at room temperature

**Table 3** Selected natural atomic charges (e) and natural electron configuration for **1**

Atom	Net charge	Electron configuration
Zn(1)	1.271	[core]4s(0.30)3d(9.98)4p(0.44)
O(1)	−0.726	[core]2s(1.70)2p(5.01)3p(0.01)
O(2) <sup>#3</sup>	−0.726	[core]2s(1.70)2p(5.01)3p(0.01)
O(1) <sup>#1</sup>	−0.576	[core]2s(1.72)2p(4.85)3p(0.01)
O(2) <sup>#2</sup>	−0.576	[core]2s(1.72)2p(4.85)3p(0.01)
N(1)	−0.607	[core]2s(1.38)2p(4.20)3p(0.02)
N(1) <sup>#1</sup>	−0.607	[core]2s(1.38)2p(4.20)3p(0.02)

Symmetry codes: <sup>#1</sup> 1−*x*, *y*, −*z* + 3/2; <sup>#2</sup> *x*, −*y*, *z* + 1/2; <sup>#3</sup> 1−*x*, −*y*, 1−*z*

$H_2C_2O_4 \cdot 2H_2O$  and bix ligands were investigated at room temperature. Excited by 355 nm, coordination polymer **1** gives wide yellow emission with the maximum peak at 599 nm plus shoulder peak at 564 nm. The main emission peak of ligand bix is at 508 nm. However, no obvious emission bands are observed for the free  $H_2C_2O_4$  ligand in

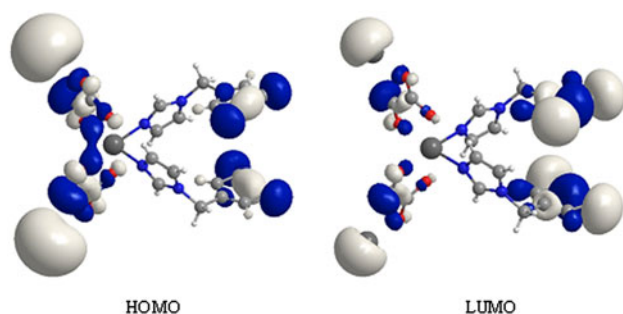

**Fig. 6** Frontier molecular orbitals of the complex

the range of 400–800 nm under the same experimental conditions. The significant phenomenon of the fluorescence emission of **1** here could be tentatively assigned to the ligand-to-metal charge transfer (LMCT) [25]. For possesses strong fluorescent intensity, it appears to be good candidates for novel hybrid inorganic–organic photoactive materials.

#### 4 Theoretical Calculations

All calculations in this work were carried out with the Gaussian 09 program [26]. The parameters of the molecular structure for calculation were all from the experimental data of the complex. Natural bond orbital (NBO) analysis was performed by density functional theory (DFT) [27] with the PBE0 [28, 29] hybrid functional and the LANL2DZ basis set [30].

The selected natural atomic charges and natural electron configuration for the complex is shown in Table 3. It is indicated that the electronic configurations of Zn(II) ion, N and O atoms are  $4s^{0.30}3d^{9.98}4p^{0.44}$ ,  $2s^{1.70-1.72}2p^{4.85-5.01}$   $3p^{0.01}$  and  $2s^{1.38}2p^{4.20}3p^{0.02}$ , respectively. Based on the above results, one can conclude that the Zn(II) ion coordination with N and O atoms is mainly on  $3d$ ,  $4s$ , and  $4p$  orbitals. N atoms form coordination bonds with Zn(II) ion using  $2s$  and  $2p$  orbitals. All O atoms supply electrons of  $2s$  and  $2p$  to Zn(II) ion and form the coordination bonds. Therefore, the Zn(II) ion obtained some electrons from two N atoms of bix ligand, four O atoms of  $C_2O_4^{2-}$  ligand. Thus, according to valence-bond theory the atomic net charge distribution in the complex shows the obvious covalent interaction between the coordinated atoms and Zn(II) ion. As can be seen from the Fig. 6, the HOMO mainly consists of Zn(II) ion and ligand and the LUMO is mainly composed of Zn(II) ion and ligand.

**Acknowledgments** This work was supported by the Science and Technology Development Project of Jilin Provincial Science & Technology Department (201205080) and the Science and Technology Research Projects of the Education Department of Jilin Province (2012.358). Program supports from State Key Laboratory of

Theoretical and Computational Chemistry of Jilin University are gratefully acknowledged.

**Open Access** This article is distributed under the terms of the Creative Commons Attribution License which permits any use, distribution, and reproduction in any medium, provided the original author(s) and the source are credited.

#### References

1. S. Leininger, B. Olenyuk, P.J. Stang, *Chem. Rev.* **100**, 853 (2000)
2. P.J. Hagrman, D. Hagrman, J. Zubieta, *Angew. Chem. Int. Ed.* **38**, 2638 (1999)
3. X.M. Zhang, M.L. Tong, X.M. Chen, *Angew. Chem. Int. Ed.* **41**, 1029 (2002)
4. S.H. Feng, R.R. Xu, *Acc. Chem. Res. J.* **34**, 239 (2001)
5. W.S. You, E.B. Wang, Y. Xu et al., *Inorg. Chem.* **40**, 5468 (2001)
6. X.M. Li, Q.W. Wang, D. Li et al., *Chin. J. Struct. Chem.* **11**, 1339 (2007)
7. M. Du, Y.M. Guo, X.H. Bu, *Inorg. Chim. Acta* **335**, 136 (2002)
8. S. Pérez-Yáñez, O. Castillo, J. Cepeda et al., *Inorg. Chim. Acta* **365**, 211 (2011)
9. L.M. Zheng, X. Fang, K.H. Li et al., *J. Chem. Soc. Dalton Trans.* 2311 (1999)
10. P.J. Hagrman, J. Zubieta, *Inorg. Chem.* **39**, 3252 (2000)
11. Y.G. Li, E.B. Wang, H. Zhang et al., *J. Solid State Chem.* **163**, 10 (2002)
12. Z.L. Wang, M.X. Li, J.W. Zhao et al., *Chin. J. Struct. Chem.* **5**, 654 (2011)
13. G.M. Sheldrick, *SHELXS-97, Programs for X-ray Crystal Structure Solution* (University of Göttingen, Göttingen, 1997)
14. G.M. Sheldrick, *SHELXL-97, Programs for X-ray Crystal Structure Refinement* (University of Göttingen, Göttingen, 1997)
15. M. Devereux, D.O. Shea, A. Kellett et al., *Inorg. Biochem.* **101**, 881 (2007)
16. L.J. Farrugia, X.A. Wing, *Windows Program for Crystal Structure Analysis* (University of Glasgow, Glasgow, 1988)
17. Z.Y. Fu, X.T. Wu, J.C. Dai et al., *Eur. J. Inorg. Chem.* **2002**, 2730 (2002)
18. P.Y. Zhan, J.Y. Ji, Y.L. Niu et al., *Chin. J. Inorg. Chem.* **2**, 424 (2013)
19. M. Yuan, Y.G. Li, E.B. Wang et al., *J. Chem. Soc. Dalton Trans.* 2916 (2002)
20. Z.B. Han, E.B. Wang, G.Y. Luan et al., *J. Mater. Chem.* **12**, 1169 (2002)
21. A. Gilbert, J. Baggott, *Essentials of Molecular Photochemistry* (CRC Press, Boca Raton, 1991)
22. Z. Han, Y. He, C. Ge, J. Ribas, L. Xu, *Dalton Trans.* 3020 (2007)
23. S. Mizukami, H. Houjou, K. Sugaya et al., *Chem. Mater.* **17**, 50 (2005)
24. C.W. Tang, S.A. Vanslyke, *Appl. Phys. Lett.* **51**, 913 (1987)
25. Y.X. Chi, S.Y. Niu, J. Jin et al., *Z. Anorg. Allg. Chem.* **633**, 1277 (2007)
26. M.J. Frisch, G.W. Trucks, H.B. Schlegel et al., *Gaussian 09* (Gaussian Inc., Wallingford, 2009)
27. R.G. Parr, W. Yang, *Density Functional Theory of Atoms and Molecules* (Oxford University Press, Oxford, 1989)
28. M. Ernzerhof, G.E. Scuseria, *J. Chem. Phys.* **110**, 5029 (1999)
29. C. Adamo, V.J. Barone, *Chem. Phys.* **110**, 6158 (1999)
30. T.H. Dunning, P.J. Hay Jr, in *Modern Theoretical Chemistry*, ed. by H.F. Schaefer III (Plenum, New York, 1976), p. 1