

# Theoretical and experimental study of the thermal strength of anticorrosive lined steel pipes

Zeng Dezhi<sup>1, 2</sup>, Deng Kuanhai<sup>2</sup>, Lin Yuanhua<sup>1\*</sup>, Shi Taihe<sup>1</sup>, Shi Daiyan<sup>3</sup> and Zhou Lizhi<sup>4</sup>

<sup>1</sup> State Key Laboratory of Oil and Gas Reservoir Geology and Exploitation (Southwest Petroleum University), Chengdu, Sichuan 610500, China

<sup>2</sup> CNPC Key Laboratory for Tubular Goods Engineering, Southwest Petroleum University, Chengdu, Sichuan 610500, China

<sup>3</sup> Southwest Branch of Engineering Design Co. Ltd., CNPC, Chengdu, Sichuan 610500, China

<sup>4</sup> Research Institute of Exploration and Development, Tarim Oilfield Company, PetroChina, Korla, Xinjiang 841000, China

© China University of Petroleum (Beijing) and Springer-Verlag Berlin Heidelberg 2014

**Abstract:** Bimetallic lined steel pipe (LSP) is a new anti-corrosion technology. It is widely used to transport oil, gas, water and corrosive liquid chemicals. At present, the hydroforming pressure for LSP has been investigated theoretically and experimentally by most researchers. However, there are a few reports on the thermal strength of bimetallic LSP. Actually, the bimetallic LSP will be subjected to remarkable thermal load in the process of three layer polyethylene (3PE) external coating. Reverse yielding failure may occur on the inner pipe of the bimetallic LSP when it suffers from remarkable thermal load and residual contact pressure simultaneously. The aim of this paper is to study the thermal load and strength of the bimetallic LSP. A mechanical model, which can estimate the thermal strength of the bimetallic LSP, was established based on the elastic theory and the manufacture of the bimetallic LSP. Based on the model, the correlation between the thermal strength of the bimetallic LSP and residual contact pressure and wall thickness of the inner pipe was obtained. Reverse yielding experiments were performed on the LSP (NT80SS-316L) under different thermal loads. Experiment results are consistent with calculated results from the theoretical model. The experimental and simulation results may provide powerful guidance for the bimetallic LSP production and use.

**Key words:** Thermal strength, reverse yielding, mechanical model, lined steel pipe, residual contact pressure

## 1 Introduction

In the process of oil and gas production and transportation, the corrosive environments to which oil country tubular goods (OCTG) are exposed become more and more complex due to the existence of high levels of carbon dioxide, hydrogen sulfide and sulfur (Chen and Rao, 2005; Eckert et al, 2012; Kermani and Morshed, 2003; Yin et al, 2008; Zhang and Lv, 2008). This makes OCTG more easily corroded and then leads to increasingly serious safety problems (Jiang, 2004; Liu et al, 2004; Zhang et al, 2005). In order to solve the corrosion problem, some methods such as corrosion inhibitor injection, a plastic internal coating, and a use of corrosion-resistant alloy, have been proposed to control corrosion (Aberle and Agarwal, 2008; Ahmad et al,

2011; Pavan et al, 2010; NACE International, 2012; Shouse et al, 2012). Analyses indicate that the bimetallic lined steel pipe (LSP) is more economic and reliable than other anti-corrosion technologies so it has been widely used in the oil and gas industry (Chen and Petersen; 1991; Nikitina, 1998; Reformatskaya et al, 2000; Place et al, 1991; Zhu et al, 2011). A bimetallic LSP consists of an inner pipe and an outer pipe. The outer pipe is an ordinary carbon steel pipe that withstands mechanical loads, and the inner one is a corrosion resistant alloy (CRA) pipe that should prevent the corrosion of steel in the oil and gas environments (Rommerskirchen, 2005; Wang et al, 2004).

It is well known that the bimetallic LSP, which is widely used to transport oil and gas, must be covered with a 3 layer anticorrosive coating of polyethylene (PE) before it is used. The bimetallic LSP will suffer from remarkable thermal load in the process of preheating for the external anticorrosive processing. The yield strength of the inner pipe of the LSP decreases under thermal load (Miura and Sakuraba, 1995). In

\*Corresponding author. email: yhlin28@163.com

Received September 17, 2013

addition, performance indicators and specification calculation method of thermal strength of the bimetallic LSP are not given by the current international standards (American Petroleum Institute, 1998). However, some users and manufacturers only pursue blindly high residual contact pressure between the inner and outer pipes of the bimetallic LSP to prevent the inner pipe from being separated from the outer pipe without considering the thermal strength of the bimetallic LSP. In a sense, the higher the residual contact pressure is, the better the bimetallic LSP is. However, previous research showed that reverse yielding failure occurred easily on the inner pipe when the LSP suffered from additional thermal load and residual contact pressure simultaneously (Zhang et al, 2012; Zheng and Lu, 2010). Namely, the higher the residual contact pressure between the inner and outer pipes of the bimetallic LSP, the easier the inner pipe yields. So it is unreasonable to blindly pursue high residual contact pressure.

The key to solve the problem of blindly pursuing high residual contact pressure is to determine the critical temperature load which makes the inner pipe of the bimetallic LSP yield. As a result, the theoretical and experimental research on the thermal strength of the bimetallic LSP has been done based on elastic theory and the forming principle of the bimetallic LSP (Akisanya et al, 2011; Wang et al, 2002; 2005) and reported in this paper.

## 2 Analysis of thermal strength of the bimetallic LSP

The bimetallic LSPs are generally manufactured at room temperature but are on service as petroleum pipelines at changing temperature environments, even more than 150 °C. The inner and outer pipes are bonded together tightly by relatively large residual contact pressure. The inner pipe is a thin-walled corrosion resistant steel pipe and it has a higher coefficient of thermal expansion than the outer one. Therefore, a radial thermal load is applied on the bonding surface due to differences in coefficients of thermal expansion between the inner and outer pipes when the environment temperature changes (Zhang and Jiang, 1997).

In order to facilitate to solve and analyze this mechanical model, some assumptions are made as follows:

1) The LSP is a long thin-walled cylinder, and the axial force caused by temperature is so small that it can be neglected.

2) The inner and outer pipes are ideal cylinders with uniform wall thickness.

3) The mechanical analysis of the LSP under thermal load belongs to a plane strain problem.

### 2.1 Radial thermal load produced by temperature change

A radial thermal load will be generated on the bonding surface of the bimetallic LSP due to difference in thermal expansion coefficients between the inner and outer pipes, when the surrounding temperature of the LSP changes. Therefore, there are two types of circumferential strain due to the temperature change. One is free expansion strain caused by temperature variation and the other is constrained strain caused by radial thermal load.


If the radial thermal load caused by temperature change is equal to  $p_r^t$ , the inner wall of the outer pipe suffers from an additional internal pressure  $p_r^t$  and the outer wall of the inner pipe suffers from the additional external pressure  $p_r^t$ , as shown in Fig. 1.

Assume that the inner pipe expands freely in the outer pipe. When the temperature increases from  $T_1$  to  $T_2$ , a circumferential strain between the inner wall of the outer pipe and the outer wall of the inner pipe may be generated due to differences in thermal expansion coefficients between the inner and outer pipes:

$$\begin{cases} \varepsilon_{\theta_{io}}^t = \alpha_i (T_2 - T_1) \\ \varepsilon_{\theta_{oi}}^t = \alpha_o (T_2 - T_1) \end{cases} \quad (1)$$

where  $\alpha_i$  and  $\alpha_o$  are the thermal expansion coefficients of the inner and outer pipes, respectively, °C<sup>-1</sup>;  $T_1$  and  $T_2$  are the forming temperature and working temperature of the LSP, respectively, °C.

According to the Lamé formula (Xu, 2006), the thermal stress component at the inner pipe caused by radial thermal load  $p_r^t$  can be obtained:

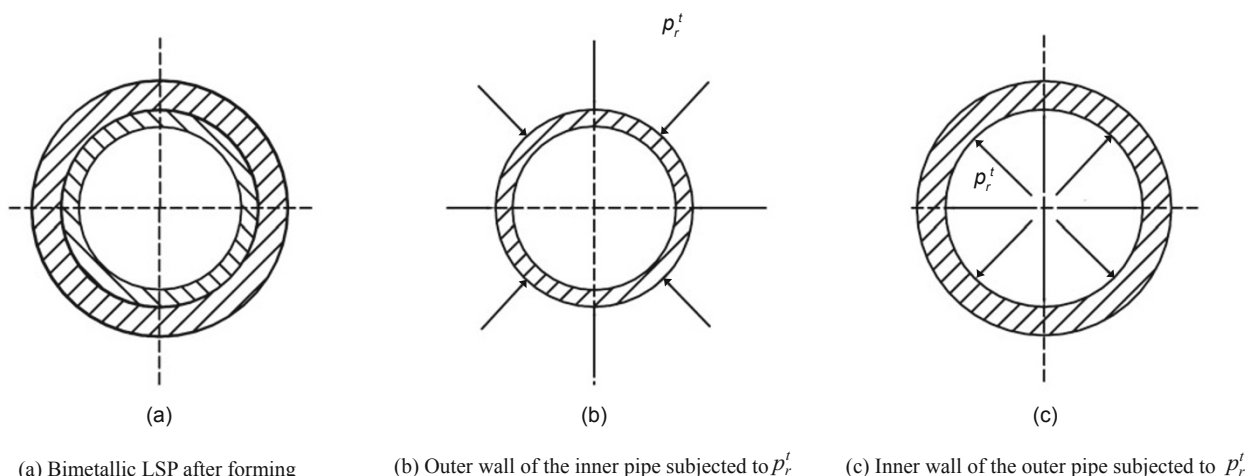

**Fig. 1** Schematic diagrams of the bimetallic LSP suffering from radial thermal load

$$\begin{cases} \sigma'_{r_{io}} = -\frac{p'_r k^2}{k^2 - 1} \left[ 1 - \frac{r_i^2}{r^2} \right] \\ \sigma'_{\theta_{io}} = -\frac{p'_r k^2}{k^2 - 1} \left[ 1 + \frac{r_i^2}{r^2} \right] \end{cases} \quad (2)$$

where  $r$  is the radius of the inner pipe;  $r_i$  is the inside radius of the inner pipe;  $k$  is the ratio of the outer radius  $r_o$  to the inside radius  $r_i$  of the inner pipe.

From Eq. (2), the thermal stress component at the outer wall of the inner pipe ( $r=r_o$ ) can be obtained:

$$\begin{cases} \sigma'_{r_{io}} = -p'_r \\ \sigma'_{\theta_{io}} = -\frac{k^2 + 1}{k^2 - 1} p'_r \end{cases} \quad (3)$$

where  $\sigma'_{r_{io}}$  is the radial stress component at the outer wall of the inner pipe, MPa;  $\sigma'_{\theta_{io}}$  is the circumferential stress component at the outer wall of the inner pipe, MPa.

According to the constitutive equations of plane problems, the circumferential strain at the outer surface of the inner pipe caused by the radial thermal load  $p'_r$  can be obtained:

$$\varepsilon'_{\theta_{io}} = \frac{1}{E_i} (\sigma'_{\theta_{io}} - \mu_i \sigma'_{r_{io}}) \quad (4)$$

Substituting Eq. (3) into Eq. (4) gives:

$$\varepsilon'_{\theta_{io}} = -\frac{1}{E_i} \left[ \frac{k^2 + 1}{k^2 - 1} - \mu_i \right] p'_r \quad (5)$$

Similarly, according to the Lamé formula (Xu, 2006), the thermal stress component at the inner wall of the outer pipe caused by radial thermal load  $p'_r$  can be expressed as follows:

$$\begin{cases} \sigma_r = \frac{p'_r}{K^2 - 1} \left[ 1 - \frac{R_o^2}{R^2} \right] \\ \sigma_\theta = \frac{p'_r}{K^2 - 1} \left[ 1 + \frac{R_o^2}{R^2} \right] \end{cases} \quad (6)$$

where  $R$  is the radius of the outer pipe;  $R_o$  is the outer radius of the outer pipe;  $K$  is the ratio of the outer radius  $R_o$  to the inside radius  $R_i$  of the outer pipe.

From Eq. (6), the thermal stress component at the inner wall of the outer pipe ( $R=R_i$ ) can be obtained:

$$\begin{cases} \sigma'_{r_{oi}} = -p'_r \\ \sigma'_{\theta_{oi}} = \frac{K^2 + 1}{K^2 - 1} p'_r \end{cases} \quad (7)$$

where  $\sigma'_{r_{oi}}$  is the radial stress component at the inner wall of the outer pipe, MPa;  $\sigma'_{\theta_{oi}}$  is the circumferential stress component at the inner wall of the outer pipe, MPa.

According to the constitutive equations of plane problems, the circumferential strain at the inner wall of the outer pipe

caused by radial thermal load  $p'_r$  can be obtained:

$$\varepsilon'_{\theta_{oi}} = \frac{1}{E_o} (\sigma'_{\theta_{oi}} - \mu_o \sigma'_{r_{oi}}) \quad (8)$$

Substituting Eq. (7) into Eq. (8) gives:

$$\sigma'_{\theta_{oi}} = \frac{1}{E_o} \left[ \frac{K^2 + 1}{K^2 - 1} + \mu_o \right] p'_r \quad (9)$$

A combination of Eq. (1) and Eq. (5) gives the total circumferential strain  $\varepsilon''_{\theta_{io}}$  at the outer wall of the inner pipe caused by radial thermal load  $p'_r$  and temperature change:

$$\varepsilon''_{\theta_{io}} = \varepsilon'_{\theta_{io}} + \alpha_i \Delta T = -\frac{1}{E_i} \left[ \frac{k^2 + 1}{k^2 - 1} - \mu_i \right] p'_r + \alpha_i \Delta T \quad (10)$$

Combining Eq. (1) with Eq. (9) gives the total circumferential strain  $\varepsilon''_{\theta_{oi}}$  at the inner wall of the outer pipe caused by radial thermal load  $p'_r$  and temperature change:

$$\varepsilon''_{\theta_{oi}} = \varepsilon'_{\theta_{oi}} + \alpha_o \Delta T = \frac{1}{E_o} \left[ \frac{K^2 + 1}{K^2 - 1} + \mu_o \right] p'_r + \alpha_o \Delta T \quad (11)$$

The outer pipe of the bimetallic LSP can always keep compatibility of deformation with the inner pipe. So the total circumferential strain at the inner pipe of the bimetallic LSP is equal to that at the outer pipe. The compatibility equation of deformation can be expressed as follow:

$$\varepsilon'_{\theta_{io}} = \varepsilon'_{\theta_{oi}} \quad (12)$$

Substituting Eqs. (10) and (11) into Eq. (12) gives:

$$\begin{aligned} & -\frac{1}{E_i} \left[ \frac{k^2 + 1}{k^2 - 1} - \mu_i \right] p'_r + \alpha_i \Delta T \\ & = \frac{1}{E_o} \left[ \frac{K^2 + 1}{K^2 - 1} + \mu_o \right] p'_r + \alpha_o \Delta T \end{aligned} \quad (13)$$

From Eq. (13), the radial thermal load  $p'_r$  can be obtained:

$$p'_r = \frac{(\alpha_i - \alpha_o) \Delta T}{\frac{1}{E_o} \left[ \frac{K^2 + 1}{K^2 - 1} + \mu_o \right] + \frac{1}{E_i} \left[ \frac{k^2 + 1}{k^2 - 1} - \mu_i \right]} \quad (14)$$

The radial thermal load  $p'_r$  that the inner pipe of the bimetallic LSP suffers from under any temperature environment can be calculated from Eq. (14).

## 2.2 Reverse yielding of the inner pipe of the bimetallic LSP

Based the hydroforming principle of the bimetallic LSP, it can be known that the inner wall of the inner pipe is subjected to the forming pressure, which make the inner pipe yield and produce plastic deformation in the loading forming process.

The outer pipe is in the elastic deformation under the forming pressure. Residual contact pressure between the inner and outer pipes of the bimetallic LSP is produced because the elastic deformation of the outer pipe is recovered completely while the plastic deformation of the inner pipe cannot be recovered in the unloading process. It is the residual contact pressure that makes the inner pipe bind tightly to the outer pipe of the LSP. Thus the outer wall of the inner pipe is subjected to the residual contact pressure  $p_c$  after forming. Therefore, the reverse yielding of the inner pipe is more likely to occur when the radial thermal load  $p_r^t$  caused by temperature is applied to the outer wall of the inner pipe.

The stress component at the inner wall of the inner pipe, which is under the residual contact pressure  $p_c$ , can be derived from the Lamé equation (Xu, 2006):

$$\begin{cases} \sigma_r = 0 \\ \sigma_\theta = -\frac{2p_c k^2}{k^2 - 1} \end{cases} \quad (15)$$

Reverse yielding of the inner pipe occurs under high residual contact pressure  $p_c$  because the outer pipe of the bimetallic LSP can always keep compatibility of deformation with the inner pipe. The collapse strength ( $p_{c\max}$ ) of the inner pipe of the lined steel pipe can be obtained from Eq. (15) and the Tresca yield criterion:

$$p_{c\max} = \frac{\sigma_{-si}(k^2 - 1)}{2k^2} \quad (16)$$

where  $\sigma_{-si}$  is the yield strength of the inner pipe considering the Bauschinger effect, MPa; but  $\sigma_{-si}$  is difficult obtained, so the Bauschinger effect of the inner pipe is not considered in general. It is considered that  $\sigma_{-si}$  is equal to the yield strength  $\sigma_{si}$ .

So the reverse yielding of the inner wall of the inner pipe occurs firstly under radial thermal load  $p_r^t$  and residual contact pressure  $p_c$  between the inner and outer pipes simultaneously. The thermal strength  $p_{rc}^t$  (the maximum radial thermal load  $p_r^t$ ) of the inner pipe can be obtained from Eq. (16):

$$p_{rc}^t = p_{c\max} - p_c = \frac{\sigma_{-si}(k^2 - 1)}{2k^2} - p_c \quad (17)$$

The thermal strength of the inner pipe of the bimetallic LSP can be obtained when the inner pipe is subjected to different residual contact pressures from Eq. (17). The critical temperature of the inner pipe of the lined steel pipe can be obtained by substituting the value of thermal strength into Eq. (14). To analyze the correlation between the thermal strength of the bimetallic LSP and residual contact pressure and wall thickness of the inner pipe, the thermal strengths of the lined steel pipes (NT80SS-316L) were calculated using Eqs. (16) and (17) and the calculation results are plotted in Fig. 2.

Fig. 2 shows that the thermal strength of the inner pipe decreases with an increase in the residual contact pressure. This indicates that the bimetallic LSP with higher residual contact pressure may not be better than the LSP with lower

residual contact pressure. It further proves that blindly pursuing high residual contact pressure to prevent the inner pipe from being separated from the outer pipe is not reasonable. In addition, it can be seen from Fig. 2 that the thermal strength of the inner pipe decreases with a decrease in its wall thickness. This indicates that the wall thickness of the inner pipe should not be too small for safety. So, the reasonable residual contact pressure and the wall thickness of the inner pipe can be determined under the actual working environments by Eqs. (16) and (17), which not only ensures the safety of the bimetallic LSP in service, but also prevents the waste of materials.

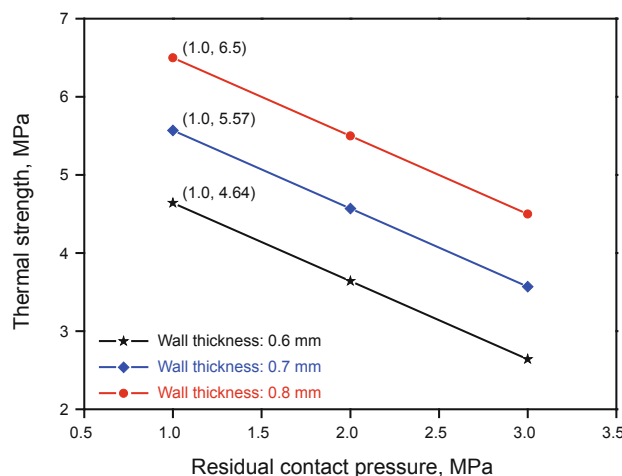


Fig. 2 Correlations between the thermal strength and  $p_c$  and wall thickness of the inner pipe

### 3 Reverse yielding test of the inner pipe

#### 3.1 Experimental

It is known that the inner pipe and outer pipe are bonded together tightly during manufacture by high residual contact pressure. The residual contact pressure is proportional to the shear strength between the inner and outer pipes (Zhang et al, 2012). The higher the residual contact pressure is, the larger the shear strength between the inner and outer pipes. The residual contact pressure and shear strength do not change under relatively low temperatures; and then the reverse yielding of the inner pipe occurs with an increase in temperature, which makes the shear strength decrease with a decrease in the residual contact pressure. So, based on that phenomenon, the critical temperature which makes the inner pipe reverse yielding can be determined.

#### 3.2 Specimen preparation

To validate the accuracy of the theoretical model, one bimetallic LSP with some residual contact pressure was made. The hydroforming test was conducted using a corrosion resistant alloy tube ( $\phi 63 \times 0.76$  mm) and a oil tube ( $\phi 70 \times 3.5$  mm), as shown in Fig. 3. The forming pressure and temperature were 48 MPa and 21 °C. The geometric and mechanical parameters of the lined pipe are listed in Table



1. The metallographic micrograph of the inner pipe (316L) is shown in Fig. 4. It can be observed from Fig. 4 that the bar ferrite is dispersed in the austenitic matrix. The chemical composition of the inner pipe (316L) is shown in Table 2.

The collapse strength  $p_{cimax}$  of the inner pipe can be calculated with Eq. (16), as listed in Table 1. The difference of thermal expansion coefficients between the inner and outer pipes is  $6 \times 10^{-6} \text{ } ^\circ\text{C}^{-1}$  and the thermal expansion of the inner pipe is larger than that of the outer pipe. The test result is shown in Fig. 5.

Based on the calculation method reported by Zeng (2007), the residual contact pressure (3.36 MPa) of the bimetallic LSP was obtained according to the residual circumferential strain in Fig. 5(b). The thermal strength ( $p'_{rc}=0.66 \text{ MPa}$ ) and the critical temperature ( $T_2=48.6 \text{ } ^\circ\text{C}$ ) were also obtained from Eqs. (17) and (14).

### 3.3 Test procedure


1) The bimetallic LSP was divided into 9 segments by linear cutting, as shown in Fig. 6.

**Table 1** The geometric and mechanical parameters of the bimetallic LSP


Bimetallic LSP	Yield strength, MPa	Outer diameter, mm	Wall thickness, mm	Elastic modulus, MPa	Poisson's ratio $\mu$	Collapse strength $p_{cimax}$ , MPa
Inner pipe (316L)	180	63	0.76	$1.95 \times 10^5$	0.3	4.29
Outer pipe (NT80SS)	551	70	3.5	$2.06 \times 10^5$	0.3	–

**Table 2** Chemical composition of the inner pipe (316L)

Component	Cr	Ni	Mo	Mn	Si	S	C	P
Content, wt%	17.04	11.14	2.16	1.44	0.54	0.012	0.020	0.020

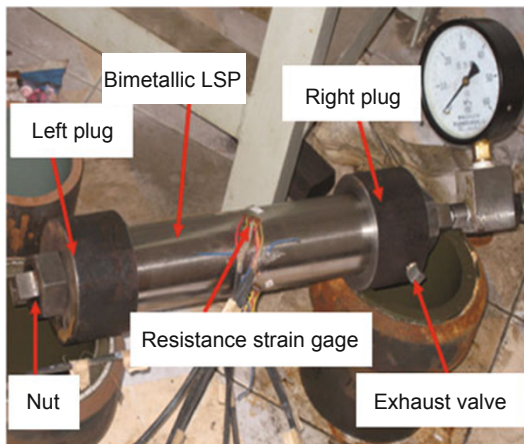


**Fig. 3** Equipment for the hydroforming test of the bimetallic LSP

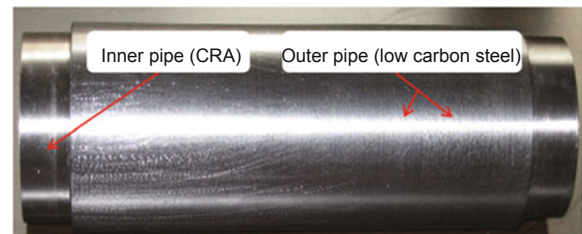

**Fig. 5(a)** The morphology of the bimetallic LSP after hydroforming



**Fig. 4** Microphotograph of the inner pipe (316L)

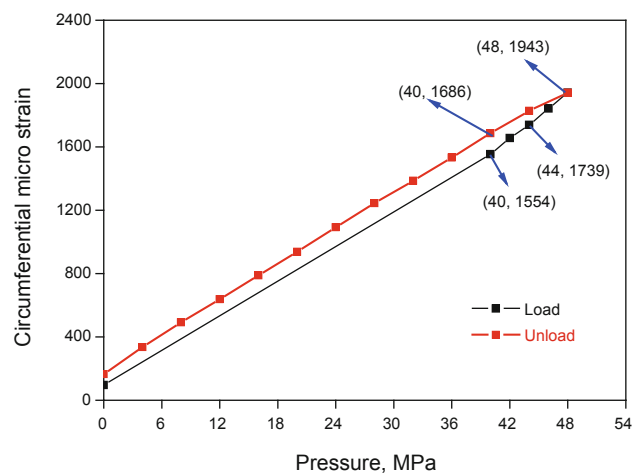


**Fig. 5(b)** Circumferential strain at the outer pipe in the forming process (0-48 MPa)

2) The 9 samples were put in an oven, and then the oven was heated to the set temperature respectively and maintained for 15 minutes, as shown in Table 3.

3) The samples were taken out and cooled to room temperature in air.

**Table 3** Experimental scheme for estimating the reverse yielding of the inner pipe

No.	Sample length $l$ , mm	Heating temperature $T_2$ , °C	Heating equipment	Radial thermal load caused by temperature $p_r^t$ , MPa
1	15	21 (Forming temperature)	—	0
2	15	40	101-2 oven	0.45
3	15	50	101-2 oven	0.68
4	15	60	101-2 oven	0.92
5	15	70	101-2 oven	1.15
6	20	80	101-2 oven	1.38
7	20	100	101-2 oven	1.84
8	20	120	101-2 oven	2.30
9	20	200	Resistance furnace	4.14

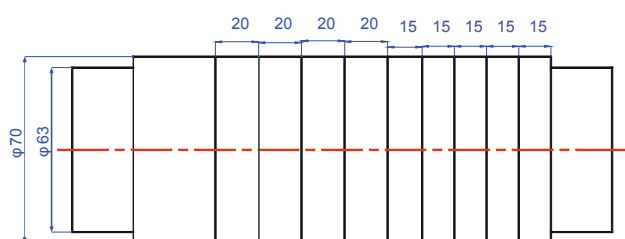**Fig. 6** The sampling method of the bimetallic LSP

4) Shear tests were conducted on the cooled samples with a MTS testing machine to measure the shear force.

5) The shear strength of each sample was calculated by using the measured shear force and the size of the bimetallic LSP based on the standard method (CJ/T192, 2004).


6) The change of residual contact pressure was analyzed according to the shear strength.

### 3.4 Test results and discussion

The appearance of some samples after shearing test was shown in Fig. 7. The shear strength of all samples under different temperatures can be calculated by the standard method (CJ/T192, 2004). The shear strengths at different temperatures are plotted in Fig. 8.

Fig. 8 shows that the shear strength (0.39 MPa) of samples after air-cooling basically remained unchanged when the heating temperature was less than 50 °C. This indicates that the shear strength of the bimetallic LSP is 0.39 MPa. The shear strength of samples dropped sharply when the heating temperature was higher than 50 °C. According to the forming principle, it can be known that reverse yielding occurs on the inner pipe when the temperature is 50 °C, the critical temperature (50 °C) and the corresponding thermal strength (0.68 MPa) can be obtained. The test results are very close to the calculation results (the critical temperature and corresponding thermal strength are 48.6 °C and 0.66 MPa respectively) of this mechanical model.

The shear strength of samples decreased linearly with an increase in temperature when the temperature was higher than 50 °C. However, there was still some residual contact

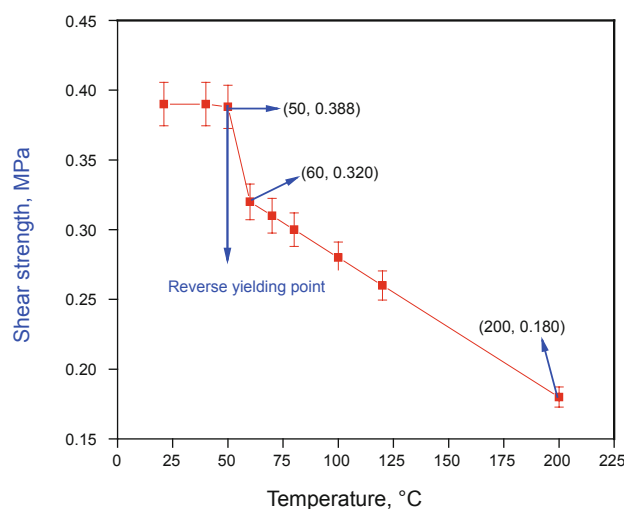**Fig. 7** The appearance of some samples after shearing test**Fig. 8** The correlation between shear strength of the bimetallic LSP and heating temperature

pressure between the inner and outer pipes. This indicates that the deformation of the bimetallic LSP under thermal load accords with the assumption of deformation compatibility.

## 4 Conclusions

1) A mechanical model was developed to calculate the thermal strength of the bimetallic LSP. Its accuracy and reliability was validated by test data. Based on the model, the correlations between the thermal strength of the bimetallic LSP and residual contact pressure and wall thickness of the inner pipe were obtained.

2) Reverse yielding tests were performed on the inner pipe of the bimetallic LSP ( $\phi 70 \times (3.5+0.76)$  mm). The shear strength of the bimetallic LSP was measured at different temperatures. The critical temperature and its corresponding thermal strength, which made the inner pipe yield, were obtained.

3) Reverse yielding failure of the inner pipe of the bimetallic LSP occurred easily when it was subjected to thermal load and residual contact pressure simultaneously. So, blindly pursuing high residual contact pressure is not reasonable. The manufacturers and users should reasonably determine the value of residual contact pressure of the bimetallic LSP to avoid reverse yielding failure according to the service conditions of the bimetallic LSP.

## Acknowledgements

The authors are grateful for financial support from the National Natural Science Foundation of China (Nos. 51004084, 51274170) and the Doctoral Fund of Ministry of Education of China (No. 20105121120002).

## References

- Aberle D and Agarwal D C. High performance corrosion resistant stainless steels and nickel alloys for oil & gas applications. Paper SPE 08085 presented at Corrosion 2008, 16-20 March 2008, New Orleans LA
- Ahmad I, Gazwi R H and Elosheby I I M. Pipeline integrity management through corrosion mitigation and inspection strategy in corrosive environment: an experience of Arabian Gulf Oil Company in Libya. Paper SPE 11311 presented at Corrosion 2011, 13-17 March 2011, Houston, Texas
- Akisanya A R, Khan F U and Deansa W F. Cold hydraulic expansion of oil well tubulars. *International Journal of Pressure Vessels and Piping*. 2011. 88(1-12): 465-472
- Chen F and Rao W Y. Mechanism of CO<sub>2</sub> corrosion in high pressure and condensate gas wells and techniques for preventing it. *Journal of Jiangnan Petroleum Institute*. 2005. 27(1): 297-299 (in Chinese)
- Chen W C and Petersen C W. Corrosion performance of welded CRA lined pipes for flowlines. Paper SPE 6693 presented at Offshore Technology Conference, 6-9 May 1991, Houston, Texas
- CJ Industry Standard. CJ/T192-2004. Composite Steel Pipe Stainless Steel Lined. Beijing: Beijing Standards Press of China. 2004 (in Chinese)
- Eckert R B, Bensman L A, Wechel S J, et al. Employing forensic corrosion engineering in a corrosion management system. Paper SPE 2012-1636 presented at Corrosion 2012, 11-15 March 2012, Salt Lake City, Utah
- Jiang F. Evaluation methods of metal materials for high sour gas fields. *Natural Gas Industry*. 2004. 24(10): 105-107 (in Chinese)
- Kermani M B and Morshed A. Carbon dioxide corrosion in oil and gas production: a compendium. *Corrosion*. 2003. 59(8): 595-603
- Liu Z D, Huang L M and Yang Z X. Material corrosion factors of ground gathering line in a highly sulfurous environment. *Natural Gas Industry*. 2004. 24(12): 122-123 (in Chinese)
- Miura R and Sakuraba M. Clad steel pipe for corrosive gas transportation. Paper SPE 7790-MS presented at Offshore Technology Conference, 1-4 May 1995, Houston, Texas
- National Association of Corrosion Engineers. NACE TM0479-2012. Measurement techniques related to criteria for cathodic protection on underground or submerged metallic piping systems. NACE International, 2012 Houston TX
- Nikitina L A. Status and prospects for the manufacture of multilayered and bimetallic metal products. *Metallurgist*. 1998. 42(8): 297-301
- Pavan K S, Roberto P, Lietai Y, et al. On development of accelerated of testing methods for organic coating performance above 100 °C. Paper SPE 10006 presented at Corrosion 2010, 14-18 March 2010, San Antonio, TX
- Place M C, Mack R D and Rhodes P R. Qualification of corrosion-resistant alloys for sour service. Paper SPE 6603-MS presented at Offshore Technology Conference, 6-9 May 1991, Houston, Texas
- Reformatskaya I I, Zav'yalov V V, Rodionova I G, et al. Prospects for use of bimetal pipes in field oil and gas pipelines of West Siberia. *Protection of Metals*. 2000. 36(1): 46-51
- Rommerskirchen I. New progress caps 10 years of work with BuBi pipes. *World Oil*. 2005. 226(7): 69-70
- Shouse L, Logan M, Brock G, et al. Corrosion prevention technology break-through. Paper SPE 2012-1611 presented at Corrosion 2012, 11-15 March 2012, Salt Lake City, Utah
- Specification API. 5LD-1998. Specification for CRA clad or lined steel pipe. American Petroleum Institute, 1998
- Wang X S, Li P N, Wang R Z, et al. Calculation of hydro-forming pressure for bi-metal clad pipe. *Journal of Mechanical Strength*. 2002. 24(3): 439-442
- Wang X S, Wang R Z and Li P N. Estimation of residual contact pressures in CRA-lined pipe manufactured by a hydroforming process. *Chinese Journal of Mechanical Engineering*. 2004. 15(8): 662-665 (in Chinese)
- Wang X S, Li P N and Wang R Z. Study of hydro-forming technology of manufacturing bimetallic CRA-lined pipe. *International Journal of Machine Tools and Manufacture*. 2005. 45(4-5): 373-378
- Xu Z L. *Elasticity Mechanics (4th Edition)*. Beijing: Higher Education Press. 2006 (in Chinese)
- Yin Z F, Zhao W Z, Bai Z Q, et al. Corrosion behavior of SM80SS tube steel in stimulant solution containing H<sub>2</sub>S and CO<sub>2</sub>. *Electrochimica Acta*. 2008. 53(10): 3690-3700
- Zeng D Z. Theoretical and Experimental Study of Hydraulic Forming Process for Bimetal-pipe. Ph.D. Thesis. Southwest Petroleum University, Sichuan. 2007 (in Chinese)
- Zhang G X and Lv X H. Effect of temperature on the corrosion rate of oil tubing and casing. *Journal of Xi'an Shiyou University (Natural Science Edition)*. 2008. 23(4): 74-78 (in Chinese)
- Zhang L, Lu X F and Zheng X. Numerical simulation and experimental study on thermal load effect on bonding strength of cold drawing 20 /316L bimetal composite pipes. *Chemical Machinery*. 2012. 39(6): 718-723 (in Chinese)
- Zhang X S and Jiang W J. Thermal instability analysis of metal lined pipe lined layer. *Pipeline Technology Equipment*. 1997. 25(1): 25-27 (in Chinese)
- Zhang Z, Shi D Y and Shi T H. Simulation research on the corrosion of downhole tubes in high production gas well. *Natural Gas Industry*. 2005. 25(1): 103-105
- Zheng X and Lu X F. Numerical simulation studies of the effect of heat load on the residual contact pressure of cold drawing 20/316L bimetal composite pipe. *Coal Mine Machinery*. 2010. 31(11): 76-78 (in Chinese)
- Zhu S D, Wang D, Li G S, et al. The research status of bimetal composite pipe used in oil and gas field. *Corrosion Science and Protection Technology*. 2011. 23(6): 529-534 (in Chinese)

(Edited by Sun Yanhua)