

Synthesis and Characterization of WS₂ Inorganic Nanotubes with Encapsulated/Intercalated CsI

Sung You Hong¹, Ronit Popovitz-Biro², Gerard Tobias³, Belén Ballesteros³, Benjamin G. Davis¹, Malcolm L. H. Green³, and Reshef Tenne⁴ (✉)

¹ Department of Chemistry, Chemistry Research Laboratory, University of Oxford, Mansfield Road, Oxford, OX1 3TA, UK

² Electron Microscopy Unit, Weizmann Institute of Science, Rehovot 76100, Israel

³ Inorganic Chemistry Laboratory, University of Oxford, South Parks Road, Oxford, OX1 3QR, UK

⁴ Department of Materials and Interfaces, Weizmann Institute of Science, Rehovot 76100, Israel

Received: 11 December 2009 / Revised: 1 January 2010 / Accepted: 4 January 2010

© The Author(s) 2010. This article is published with open access at Springerlink.com

ABSTRACT

WS₂ nanotubes have been filled and intercalated by molten phase caesium iodide. The presence of caesium iodide inside the WS₂ nanotubes has been determined using high-resolution transmission electron microscopy (HRTEM) coupled with electron energy-loss spectroscopy (EELS) and energy-dispersive X-ray spectroscopy (EDS). Noticeably, a Moiré pattern was observed due to the interference between encapsulated CsI and WS₂ layers. The intercalation of CsI into the host concentric WS₂ lattices resulted in an increase in the interplanar spacing.

KEYWORDS

Inorganic nanotubes, transmission electron microscopy, intercalation, encapsulation

1. Introduction

The discovery of carbon nanotubes (CNTs) initiated the exploration and discovery of inorganic layered compounds with related tubular structures [1]. A wide variety of metal oxides, metal halides, and other materials have been introduced into CNTs by capillary wetting [2–5]. For example, Green and coworkers reported one-dimensional crystals of various metal halides in both multi-walled and single-walled carbon nanotube capillaries [3, 6, 7]. By analogy, filling by use of nanocapillaries was also explored for the inorganic WS₂ nanotubes. In 1992, Tenne and coworkers first showed that WS₂ material of nanometer scale in a platelet form could spontaneously form closed cage structures known as inorganic fullerene-like (IF)

nanoparticles and inorganic nanotubes [8], which are akin to carbon fullerenes and carbon nanotubes. The structures of graphite and WS₂ belong to the space group, *P6₃/mmc*. However, the structure of WS₂ is more complex than that of graphite. The WS₂ layer contains a layer of metal atoms, sandwiched between two sulphur layers, with the metal atom bonded to six sulphur atoms in a trigonal prismatic coordination [9]. Folding and bonding of edge atoms on the periphery of the quasi two-dimensional planar nanostructure leads to the formation of closed cages with polyhedral or nanotubular shapes [1]. The inner diameters of WS₂ inorganic nanotubes range between 15–30 nm and the tips are inherently open-ended [10], so this nanotubular structure is suitable for capillary filling using molten metal halides.

Address correspondence to reshef.tenne@weizmann.ac.il

2. Experimental

2.1 Synthesis of CsI@WS₂ NTs

WS₂ nanotubes and fullerene-like nanoparticles were prepared in a fluidized-bed reactor [10]. A mixture of the multi-walled WS₂ nanotubes (5%) in IF-WS₂ nanoparticle powder (30 mg) and CsI (120 mg, Acros, 99.9%, m.p. 621 °C) were ground using a mortar and pestle and transferred to a silica quartz ampoule 10 mm in diameter. The mixture was dried under high vacuum (approx. 10⁻⁴–10⁻⁵ torr) for 2 h, and the ampoule was then sealed. The ampoule was heated to 640 °C for 4 h. The furnace was cooled to room temperature overnight.


2.2 TEM analysis of CsI@WS₂ NTs

The product was sonicated in ethanol, placed on a carbon/collodion-coated Cu grid, and analyzed by transmission electron microscopy (TEM) (Philips CM-120, 120 kV) and high-resolution TEM (HRTEM) (FEI Tecnai F-30 with electron energy-loss spectroscopy (EELS) or JEOL JEM-3000F field emission gun, 300 kV). Images were acquired digitally on a Gatan model 794 (1000 × 1000) charge coupled device (CCD) camera, the magnification of which was calibrated with the Si [110] lattice spacing. Energy-dispersive X-ray spectroscopy (EDS) was performed with an electron probe 0.5 nm in diameter.


3. Results and discussion

Compared to the carbon nanotubes, the inorganic WS₂ nanotubes have heavier elements (W, Z = 74; S, Z = 16). Therefore, there is a severe limitation to the visualization of light elements, which may be filled within WS₂ nanotubes. For this reason caesium iodide was the metal halide of choice, because of the strong electron-scattering power of Cs (Z = 55) and I (Z = 53) which it was anticipated would allow observation of CsI crystal structures within the WS₂ nanotubes using HRTEM analysis. We note that CsI is one of a group of alkali halides that adopt the *Pm3m* CsCl structural archetype ($a = 0.4520$ nm) [11]. An HRTEM micrograph of the resulting composite is presented in Fig. 1, where the (110) lattice plane of CsI with lattice interplanar spacing of 0.32 nm is observed within the core of the

WS₂ nanotubes, as confirmed by the fast Fourier transform (FFT) pattern. Remarkably, a Moiré pattern was found along the WS₂ nanotube surface. The Moiré d spacing was calculated based on the two lattice spacings with a mismatch of 0.049 or 0.056 nm from the (100) or (101) spacings of the WS₂ crystal, respectively. The calculated Moiré spacing was 1.5–1.8 nm, which was in good agreement with the corresponding Moiré spacing measured from the line profile recorded on the HRTEM image (ca. 1.6 nm). Stacking of the caesium iodide crystals inside the nanocapillary exhibited various orientations, such as (110) and (100) lattice planes (see Figs. S-1 and S-2 in the Electronic Supplementary Material (ESM)). Further, EELS analysis performed (Fig. S-3 in the ESM) on such nanotubes gave a Cs:I ratio fairly close to 1:1, consistent with the existence of CsI layers. EDS analysis also confirmed

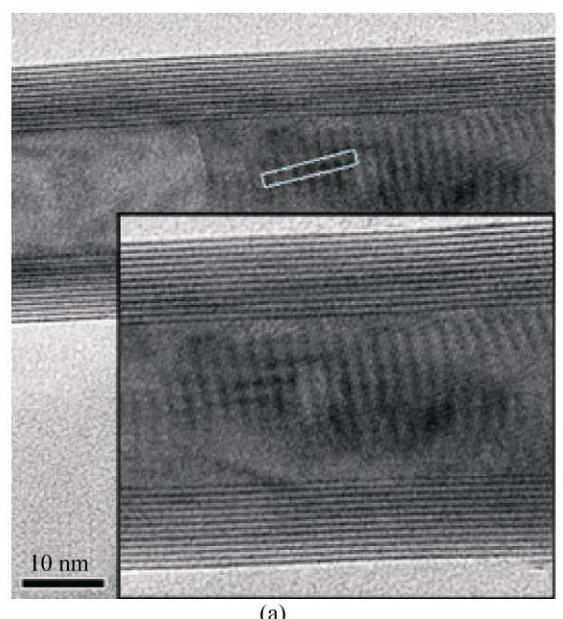

(a)

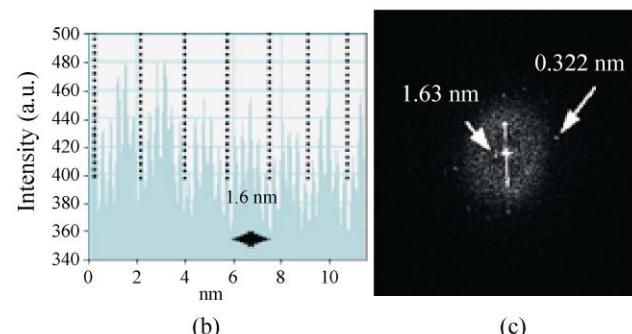

(b)

(c)

Figure 1 (a) Moiré pattern of HRTEM image of CsI filled WS₂ nanotube; (b) line profile integrated along the region enclosed in the rectangle; (c) FFT pattern



the presence of W, S, Cs, and I (Fig. S-3 in the ESM). In addition to the nanotubes filled with CsI rod-like crystals, occasionally, some of WS_2 nanotubes (< 10%) showed lattice expansion of the concentric WS_2 layers and revealed a substantial increase (ca. 0.7 nm) in the interlayer spacing (Fig. 2). While the encapsulation is induced by nanocapillarity, the intercalation mechanism is not clearly understood. Presumably, it involves diffusion from both inner and outer walls of WS_2 nanotubes: such a significant increase in layer spacing can be attributed to the uptake of water into these intercalated layers during exposure to the atmosphere. A similar behavior of hydration of intercalated layers has been described earlier for WS_2 materials intercalated by alkali metals [12, 13]. Also, alkali metal atom intercalated CNTs show a similar hydration expansion [14]. The occurrence of intercalation of CsI into the layers may be associated with the weak interlayer van der Waals interaction between the tungsten metal dichalcogenide layers [15]. However, more extensive studies are required to explain the interlayer expansion.

4. Conclusions

We have shown that filling of nanotubes by nanocapillarity is not limited to carbon nanotubes but can be applied to the inorganic nanotubes of WS_2 . Molten phase wetting with CsI resulted in the formation of one-dimensional crystal structures inside WS_2 nanocapillaries. A Moiré pattern was observed in the $\text{CsI}@\text{WS}_2$ nanotubes due to the interference between CsI and WS_2 crystal layers. Moreover, the observation of an increase (ca. 0.7 nm) of the interlayer spacing between concentric WS_2 layers of inorganic nanotubes indicates that intercalation has occurred and the expansion with the CsI is larger than that (0.3–0.5 nm) found for alkali metal intercalated IF- WS_2 [15]. Unlike the previously described $\text{PbI}_2@\text{WS}_2$ nanotubes (PbI_2 , two-dimensional layered) having a core–shell nanotubular structure [16], the $\text{CsI}@\text{WS}_2$ nanotube (CsI, 3-D CsCl archetype) has a one-dimensional stacking inside the WS_2 nanotube and also intercalation between concentric WS_2 . This suggests that metal halides do not interact strongly with the WS_2 layers but instead

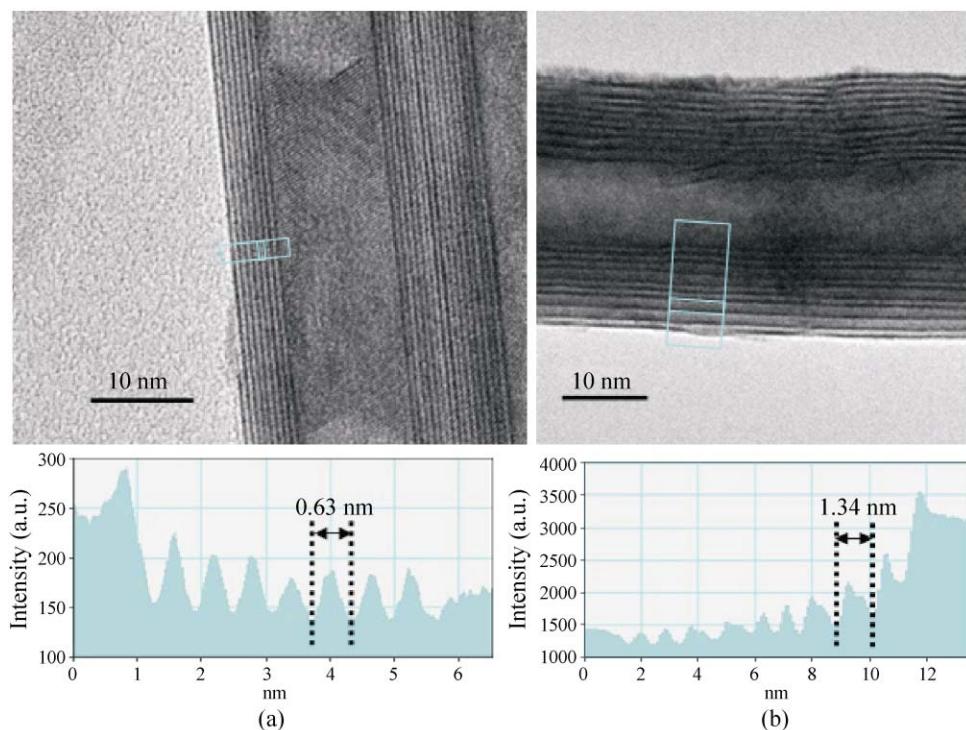


Figure 2 HRTEM images with line profiles: (a) non-intercalated WS_2 nanotube with encapsulated CsI; (b) WS_2 nanotube with intercalated CsI

adopt their preferred ionic structures.

Acknowledgements

This work was supported by the Israel Science Foundation, European Research Council (ERC) grant (No. INTIF 226639); H. Perlman Foundation and the Cherna Moskowitz Center for Nano and Bio-Nano imaging. We thank Dr. Rita Rosentsveig for the supply of WS₂ inorganic nanotubes. G. T. acknowledges support through FP7 European Community Marie Curie European Reintegration Grant (ERG) (No. PERG04-GA-2008-239303) and B. B. a contract from Ministry of Science and Innovation (Ministerio de Ciencia e Innovación, MICINN) Spain. S. Y. H was supported by a Samsung Corporation fellowship (2005–2009). B. G. D. is a Royal Society-Wolfson Research Merit Award recipient and is also supported by an Engineering and Physical Sciences Research Council of the UK (EPSRC) Platform Grant (No. EPSRC EP/E000614/1).

Electronic Supplementary Material: Additional HRTEM images and details of elemental analysis by EDS and EELS are available in the online version of this article at <http://dx.doi.org/10.1007/s12274-010-1018-0> and are accessible free of charge.

Open Access: This article is distributed under the terms of the Creative Commons Attribution Noncommercial License which permits any noncommercial use, distribution, and reproduction in any medium, provided the original author(s) and source are credited.

References

- [1] Tenne, R. Inorganic nanotubes and fullerene-like nanoparticles. *Nat. Nanotechnol.* **2006**, *1*, 103–111.
- [2] Ajayan, P. M.; Iijima, S. Capillarity-induced filling of carbon nanotubes. *Nature* **1993**, *361*, 333–361.
- [3] Tsang, S. C.; Chen, Y. K.; Harris, P. J. F.; Green, M. L. H. A simple chemical method of opening and filling carbon nanotubes. *Nature* **1994**, *372*, 159–162.
- [4] Ugarte, D.; Chatelain, A.; de Heer, W. A. Nanocapillarity and chemistry in carbon nanotubes. *Science* **1996**, *274*, 1897–1899.
- [5] Takenobu, T.; Takano, T.; Shiraishi, M.; Murakami, Y.; Ata, M.; Kataura, H.; Achiba, Y.; Iwasa, Y. Stable and controlled amphoteric doping by encapsulation of organic molecules inside carbon nanotubes. *Nat. Mater.* **2003**, *2*, 683–688.
- [6] Sloan, J.; Kirkland, A. I.; Hutchison, J. L.; Green, M. L. H. Integral atomic layer architectures of 1D crystals inserted into single walled carbon nanotubes. *Chem. Commun.* **2002**, 1319–1332.
- [7] Meyer, R. R.; Sloan, J.; Dunin-Borkowski, R. E.; Kirkland, A. I.; Novotny, M. C.; Bailey, S. R.; Hutchison, J. L.; Green, M. L. H. Discrete atom imaging of one-dimensional crystals formed within single-walled carbon nanotubes. *Science* **2000**, *289*, 1324–1326.
- [8] Tenne, R.; Margulis, L.; Genut, M.; Hodes, G. Polyhedral and cylindrical structures of tungsten disulphide. *Nature* **1992**, *360*, 444–446.
- [9] Kertes, M.; Hoffman, R. Octahedral vs. trigonal-prismatic coordination and clustering in transition-metal dichalcogenides. *J. Am. Chem. Soc.* **1984**, *106*, 3453–3460.
- [10] Rosentsveig, R.; Margolin, A.; Feldman, Y.; Popovitz-Biro, R.; Tenne, R. WS₂ nanotube bundles and foils. *Chem. Mater.* **2002**, *14*, 471–473.
- [11] Kelly, A.; Groves, G. W.; Kidd, P. *Crystallography and Crystal Defects*; Wiley: Chichester, 2nd ed., 2000.
- [12] Wypych, F.; Schollhorn, R. 1T MoS₂, a new metallic modification of molybdenum disulfide. *J. Chem. Soc., Chem. Commun.* **1992**, 1386–1388.
- [13] Schellenberger, A.; Schlaf, R.; Pettenkofer, C.; Jaegerman, W. Synchrotron-induced surface-photovoltage saturation at intercalated Na/WSe₂ interfaces. *Phys. Rev. B* **1992**, *45*, 3538–3545.
- [14] Zhou, O.; Fleming, R. M.; Murphy, D. W.; Chen, C. H.; Haddon, R. C.; Ramirez, A. P.; Glarum, S. H. Defects in carbon nanostructures. *Science* **1994**, *263*, 1744–1747.
- [15] Zak, A.; Feldman, Y.; Lyakhoviskaya, V.; Leitus, G.; Popovitz-Biro, R.; Wachtel, E.; Cohen, H.; Reich, S.; Tenne, R. Alkali metal intercalated fullerene-like MS₂ (M = W, Mo) nanoparticles and their properties. *J. Am. Chem. Soc.* **2002**, *124*, 4747–4758.
- [16] Kreizman, R.; Hong, S. Y.; Sloan, J.; Popovitz-Biro, R.; Albu-Yaron, A.; Tobias, G.; Ballesteros, B.; Davis, B. G.; Green, M. L. H.; Tenne, R. Core–shell PbI₂@WS₂ inorganic nanotubes from capillary wetting. *Angew. Chem. Int. Ed.* **2009**, *48*, 1230–1233.

