

# Structure and electrical properties of ternary BiFeO<sub>3</sub>-BaTiO<sub>3</sub>-PbTiO<sub>3</sub> high-temperature piezoceramics

Zhonghua YAO\*, Ying LIU, Zhe SONG, Zhijian WANG,  
Hua HAO, Minghe CAO, Zhiyong YU, Hanxing LIU\*

State Key Laboratory of Advanced Technology for Materials Synthesis and Processing and Key Laboratory of Advanced Technology for Specially Functional Materials, Ministry of Education, Wuhan University of Technology, Wuhan 430070, China

Received September 7, 2012; Accepted October 4, 2012

© The Author(s) 2012. This article is published with open access at Springerlink.com

**Abstract:** In the current work, the bulk ternary (0.85- $x$ ) BiFeO<sub>3</sub>- $x$ BaTiO<sub>3</sub>-0.15PbTiO<sub>3</sub> (BF-BT $_x$ -PT,  $x=0.08$ -0.35) system has been studied as a potential high-temperature piezoceramics. Samples with various content of BT were prepared via solid-state route, and pure perovskite phase was confirmed by X-ray diffraction. The temperature dependence of dielectric constants confirmed the decrease of Curie temperature with increasing BT content. It was found that the morphotropic phase boundary (MPB) composition of BF-BT $_x$ -PT ceramics was in the vicinity of  $x=0.15$ , which exhibits optimal properties with piezoelectric constant  $d_{33}$  of 60 pC/N, high Curie temperature of 550 °C, and low sintering temperature of 920 °C. Measurements also showed that the depoling temperature was 300 °C, about 150 °C higher than that of commercialized PZT ceramics, which indicated good temperature stability. BF-BT $_x$ -PT ceramics are promising candidates for high temperature applications.

**Key words:** ceramics; piezoelectric materials; barium titanate; perovskite; ferroelectrics

## 1 Introduction

Many piezoelectric devices require piezoelectric ceramics with Curie temperatures higher than that of the most widely used lead zirconate titanate (PZT) in high temperature environment [1]. The recently-covered BiMeO<sub>3</sub>-PT family of MPB containing materials has allowed the development of such solid solutions [2-12]. Among these systems, the BiFeO<sub>3</sub>-PbTiO<sub>3</sub> (BF-PT) solid solution system is

peculiar for its high Curie temperature (~700 °C) and large tetragonality ( $c/a=1.16$ -1.18) at the morphotropic phase boundary (MPB) composition and thus promising for high temperature piezoelectric applications [12]. However, the applied field required to reorient domains is very high which results in the high dielectric loss (3.5% for 0.7BF-0.3PT at 1 MHz measured at room temperature) and high leakage current, and this makes it difficult to achieve good piezoelectric properties and well-saturated ferroelectric hysteresis loops [13-15]. The same difficulty also occurs in BiFeO<sub>3</sub>-BaTiO<sub>3</sub> (BF-BT) solid solution system. Recently, Mn-doped BiFeO<sub>3</sub>-BaTiO<sub>3</sub> (BF-BT) solid solution system was studied, and a small amount

\* Corresponding author.

E-mail: yaozhhua@whut.edu.cn; lhxhp@whut.edu.cn

of Mn doping can greatly improve the resistivity of resultant ceramics [16-18]. Eitel et al reported that the optimal Mn-doped BF-BT solid solution system sintered in oxygen atmosphere exhibited excellent piezoelectric properties ( $d_{33}=116$  pC/N) with high Curie temperature ( $T_c > 450$  °C) for 25 mol% BaTiO<sub>3</sub> content [16,17].

Here, the ternary  $(0.85-x)\text{BiFeO}_3-x\text{BaTiO}_3-0.15\text{PbTiO}_3$  (BF-BT<sub>x</sub>-PT,  $x=0.08-0.35$ ) solid-solution piezoceramics were chosen and prepared by conventional solid-state synthesis. It is possible for BF-BT<sub>x</sub>-PT system to obtain a MPB region and to own high Curie temperature ( $T_c$ ) with excellent electrical properties suitable for high temperature application.

## 2 Experimental

Specimens with the compositions of  $(0.85-x)\text{BiFeO}_3-x\text{BaTiO}_3-0.15\text{PbTiO}_3$  (BF-BT<sub>x</sub>-PT,  $x=0.08-0.35$ ) were prepared by conventional solid-state synthesis. The reagent-grade materials of Bi<sub>2</sub>O<sub>3</sub> ( $\geq 99.5$ , Sinopharm Chemical Reagent Co., Ltd. or SCRC), Fe<sub>2</sub>O<sub>3</sub> ( $>99.5\%$ , SCRC), PbO (yellow,  $>99.0\%$ , SCRC), TiO<sub>2</sub> ( $>99.0\%$ , SCRC), and BaCO<sub>3</sub> ( $>99.0\%$ , SCRC) powders were weighed as starting powders according to the nominal compositions. The powders were re-mixed, calcined, ground, dried and then mixed with polyvinyl alcohol (PVA) binder. The powders were pressed into disks 12 mm in diameter and 1.2 mm in thickness at 200 MPa. Following binder burnout at 650 °C, samples were sintered at 800-1100 °C (800-960 °C for  $x \leq 0.15$  and 960-1100 °C for  $x > 0.15$ ) for 2 h.

Density measurement was performed using the Archimedes method. Phase structures were measured by a Philips vertical X-ray diffractometer (PW3050/60, MPSS) using Cu K $\alpha$ 1 radiation. Sintered pellets were ground to the thickness of 0.5 mm, electroded with Ag-conductive paste, and fired at 800 °C for 40 min for electrical property characterization. The samples were poled under a field of 3-6 kV/mm for 15 min at 100 °C. Temperature frequency dependence of dielectric properties of the ceramic samples was measured using an Agilent E4980A Precision LCR Meter from room temperature to 650 °C. The piezoelectric constant  $d_{33}$  of the poled specimens were measured one day after poling using a quasi-static piezoelectric  $d_{33}$  meter (Model ZJ-3D, China). The thermal depoling experiments were performed by holding the poled

specimens with Ag electrode for 30 min at various temperatures, then cooling to room temperature, measuring their piezoelectric constant  $d_{33}$ , and repeating the procedure up to the temperature above their Curie point.

## 3 Results and discussion

It is well known that BF-PT and BF-BT can form solid solution in the MPB region, respectively [12,19-22]. The MPB compositions were identified as the enhancement of piezoelectric properties due to the high polarizabilities resulting from the coexistence of tetragonal and rhombohedral phases. BiFeO<sub>3</sub>-PbTiO<sub>3</sub> (BF-PT) has been reported to be a continuous solid solution across its entire composition range, with a rhombohedral-tetragonal morphotropic phase boundary (MPB) at 0.7-0.8 mol BiFeO<sub>3</sub> [19,20]. Similarly, it was reported that the BiFeO<sub>3</sub>-BaTiO<sub>3</sub> system has three structural phase transitions at room temperature over the entire compositional range. Above 70 mol% of BF, the structure is in the rhombohedral and below 4 mol%, it is tetragonal [21]. The crystal structure changes from tetragonal to cubic phase at room temperature when 8 mol% of BiFeO<sub>3</sub> was added into BaTiO<sub>3</sub> for  $x\text{BiFeO}_3-(1-x)\text{BaTiO}_3$  [22]. It can be predicted that there is a MPB region in the BF-BT-PT ternary system. The boundary of the tetragonal and cubic phase was not presented clearly enough yet. Figure 1 shows the compositional ternary diagram of BF-BT-PT in and around estimated MPB regions and the hatched part was the predicted MPB compositions in the BF-BT-PT ternary compounds.

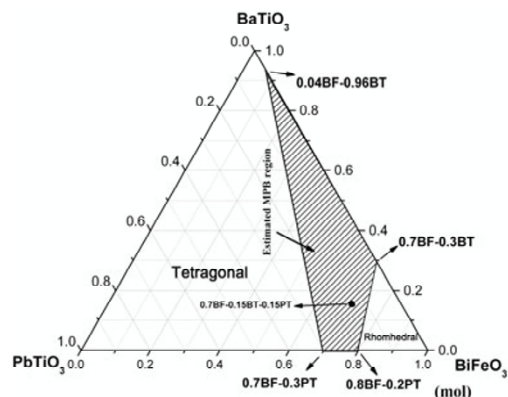


Fig.1 Compositional ternary diagram of BF-BT-PT indicating compositions synthesized in this study. The estimated MPB region was marked by the shaded areas.

XRD of BF-BT $x$ -PT-sintered pellets indicated high-purity perovskite structure without traces of secondary phases (Fig. 2) in the studied compositions. The lower symmetry phases, being either rhombohedral or tetragonal, are identified by splitting of perovskite peaks  $\{hkl\}$ , either  $\{111\}$  splitting for rhombohedral, or  $\{110\}$  and  $\{100\}$  splitting for tetragonal symmetry [23]. It is found from Fig. 2 that the crystalline symmetry of BF-BT $x$ -PT shifts from rhombohedral to tetragonal with increasing  $x$  by the splitting of (002)/(200) peaks near  $45^\circ$ , indicating the existence of a MPB range near  $x=0.15$ . This result is in agreement with the result reported in BiScO $_3$ -PbTiO $_3$  system [23,24].

Figure 3 shows the relative density of the ceramics of the BF-BT $x$ -PT compositions near MPB with sintering temperatures. It can be seen that the addition of BF can effectively decrease the densified temperature of BF-BT $x$ -PT compositions. Furthermore, high sintering temperature can deteriorate the density

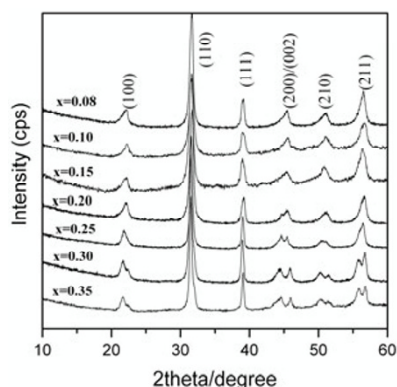


Fig. 2 XRD patterns of BF-BT $x$ -PT ceramics for  $x=0.08-0.35$ .

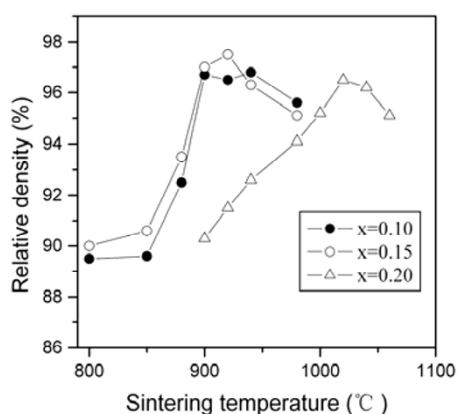


Fig. 3 Relative density of the ceramics with sintering temperatures of the BF-BT $x$ -PT compositions near MPB.

for high BF compositions. The optimal sintering temperature for  $x=0.15$  near MPB is  $920^\circ\text{C}$ .

Figure 4 shows the typical piezoelectric constant  $d_{33}$  of BF-BT $x$ -PT ceramics poled under 3 kV/mm and saturated poling fields for the composition  $x > 0.15$ , respectively. The composition  $x=0.15$  exhibited the highest  $d_{33}$  value (60 pC/N) under the same poling field (3 kV/mm). However, the compositions ( $x > 0.15$ ) show higher piezoelectric properties when poled till to saturation (4-6 kV/mm) than that poled under 3 kV/mm. It is possible that more dipole orientations occurred under high poling fields (4-6 kV/mm) than that under low fields (3 kV/mm). Theoretically, the composition ( $x=0.15$ ) near MPB owns more dipole orientations than that of far from MPB due to the mixed crystallite phases when poled till to saturation. However, the increase of BF content can result in the difficulty of poling due to the enhancement of leakage current and large tetragonality. The applied field required to reorient domains is very high. Therefore, the compositions of  $x \leq 0.15$  with high BF content cannot be poled completely. To achieve high electrical fields across samples, materials have had to be doped reducing the possibility of electrical breakdown for BiFeO $_3$ -based system [16-18,25].

The Curie temperature is an important factor for piezoelectric ceramics used in high working temperature. Figure 5 shows the variation of Curie temperatures with compositions in the BF-BT $x$ -PT system. From Fig. 5, it is evident that the Curie temperature increases obviously with increasing BF content. All the studied compositions exhibit high

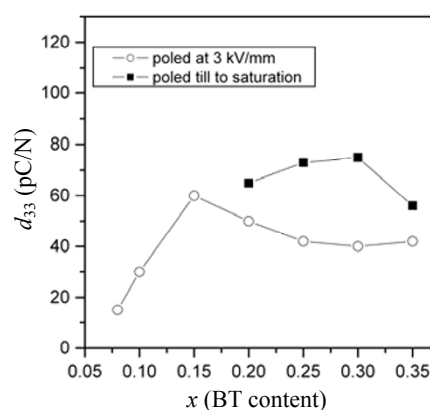


Fig. 4 Typical piezoelectric constant  $d_{33}$  of BF-BT $x$ -PT ceramics poled under 3 kV/mm and saturated poling fields.

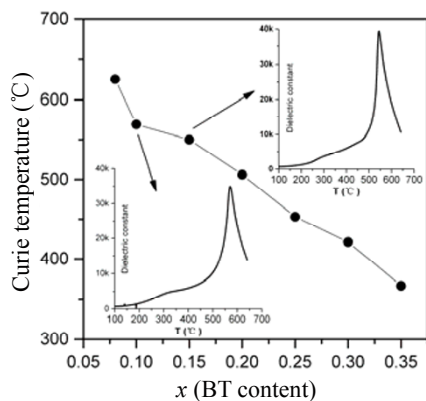


Fig. 5 The variation of Curie temperatures with compositions in the BF-BTx-PT system. The inset graphs are the dielectric temperature spectra of compositions  $x=0.10$  and  $0.15$  measured at 1 kHz.

Curie temperatures compared to PZT system. The composition near MPB exhibited high Curie temperature of  $550\text{ }^{\circ}\text{C}$  for  $x=0.15$  and  $569\text{ }^{\circ}\text{C}$  for  $x=0.10$ , respectively.

Thermal depoling temperature of ferroelectrics determines the usage range of their application in piezoelectric devices. It is well-known that there is a polymorphic phase transition for KNN-based lead-free piezoelectric ceramics which limits the applications at elevated temperature due to thermal instability at high temperatures [26]. The effect of thermal depoling on  $d_{33}$  values of poled BF-BTx-PT ( $x=0.15, 0.20,$  and  $0.30$ ) ceramics for different thermal treatments measured *ex situ* is shown in Fig. 6. As the temperature increases,  $d_{33}$  for the studied compositions remains almost constant and then drops dramatically above a critical temperature due to thermal depoling. This critical temperature can be defined as depolarization

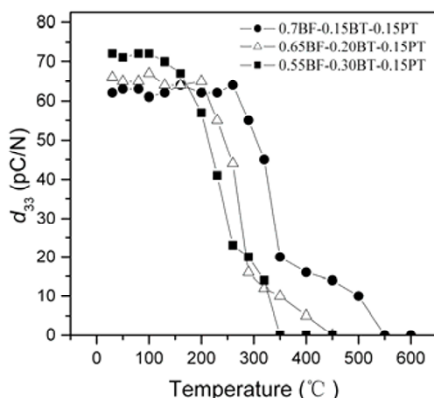


Fig. 6 Effect of thermal depoling on  $d_{33}$  values of poled BF-BTx-PT ( $x=0.15, 0.20,$  and  $0.30$ ) ceramics for different thermal treatments measured *ex situ*.

temperature ( $T_d$ ). As shown in Fig. 6,  $d_{33}$  decreases at the temperature above the depolarization temperature  $T_d$  but not zero till to the Curie temperature. This remnant piezoelectric constant  $d_{33}$  can be ascribed to the asymmetry of crystal structure for the composition till to the symmetric cubic structure above Curie temperature. Also,  $T_d$  depends on BT content by the variation of the thermal depoling temperature. Based upon these results, the BF-BTx-PT ( $x=0.15$ ) system shows potentialities as a new type of piezoelectric material used near  $300\text{ }^{\circ}\text{C}$ , about  $150\text{ }^{\circ}\text{C}$  higher than that of commercialized PZT ceramics.

## 4 Conclusions

In conclusion, the structure and electrical properties of ternary  $\text{BiFeO}_3\text{-BaTiO}_3\text{-PbTiO}_3$  high-temperature piezoceramics were investigated, focusing on the electrical properties of the compositions near MPB.

(1) The MPB region showing the coexistence of rhombohedral and tetragonal phases is confirmed near  $x=0.15$ .

(2) The composition  $0.7\text{BiFeO}_3\text{-}0.15\text{BaTiO}_3\text{-}0.15\text{PbTiO}_3$  exhibits a  $T_c=550\text{ }^{\circ}\text{C}$ , enhanced piezoelectric constant  $d_{33}=60\text{ pC/N}$ , and low sintering temperature ( $920\text{ }^{\circ}\text{C}$ ), respectively.

(3) Thermal depoling measurement indicates that the BF-BTx-PT ( $x=0.15$ ) composition can be used at the temperature near  $300\text{ }^{\circ}\text{C}$  as a new high temperature piezoelectric system.

## Acknowledgement

The authors would like to thank the support of the Key Programmer of Natural Science Foundation of China (No. 50932004), the International Technology Cooperation Project from the Ministry of Science and Technology of China (No. 2011DFA52680), the National Natural Science Foundation of China (No. 51102189), the Key Grant Project of Chinese Ministry of Education (No. 309022), the program for New Century Excellent Talents in University (No. NCET-11-0685), and the Fundamental Research Funds for the Central Universities (No. 2012-IV-006).

## References

- [1] Damjanovic D. Materials for high temperature piezoelectric transducers. *Curr Opin Solid State*

- Mater Sci* 1998, **3**: 469-473.
- [2] Eitel RE, Randall CA, Shrout TR, *et al.* New high temperature morphotropic phase boundary piezoelectrics based on Bi(Me)O<sub>3</sub>-PbTiO<sub>3</sub> ceramics. *Jpn J Appl Phys* 2001, **40**: 5999-6002.
- [3] Hu W, Tan XL, Rajan K. Piezoelectric ceramics with compositions at the morphotropic phase boundary in the BiFeO<sub>3</sub>-PbZrO<sub>3</sub>-PbTiO<sub>3</sub> ternary system. *J Am Ceram Soc* 2011, **94**: 4358-4363.
- [4] Yao ZH, Liu HX, Hao H, *et al.* Structure, electrical properties, and depoling mechanism of BiScO<sub>3</sub>-PbTiO<sub>3</sub>-Pb(Zn<sub>1/3</sub>Nb<sub>2/3</sub>)O<sub>3</sub> high-temperature piezoelectric ceramics. *J Appl Phys* 2011, **109**: 014105.
- [5] Chen JG, Shi HD, Liu GX, *et al.* Temperature dependence of dielectric, piezoelectric and elastic properties of BiScO<sub>3</sub>-PbTiO<sub>3</sub> high temperature ceramics with morphotropic phase boundary (MPB) composition. *J Alloys Compds* 2012, **537**: 280-285.
- [6] Zhang SJ, Randall CA, Shrout TR. High Curie temperature piezocrystals in the BiScO<sub>3</sub>-PbTiO<sub>3</sub> perovskite system. *Appl Phys Lett* 2003, **83**: 3150.
- [7] Zou TT, Wang XH, Wang H, *et al.* Bulk dense fine-grain (1-x)BiScO<sub>3</sub>-xPbTiO<sub>3</sub> ceramics with high piezoelectric coefficient. *Appl Phys Lett* 2008, **93**: 192913.
- [8] Sehirlioglu A, Sayir A, Dynys F. Microstructure-property relationships in liquid phase-sintered high-temperature bismuth scandium oxide-lead titanate piezoceramics. *J Am Ceram Soc* 2008, **91**(9): 2910-2916.
- [9] Sehirlioglu A, Sayir A, Dynys F. Doping of BiScO<sub>3</sub>-PbTiO<sub>3</sub> ceramics for enhanced properties. *J Am Ceram Soc* 2010, **93**(6): 1718-1724.
- [10] Zou T, Wang X, Zhao W, *et al.* Preparation and properties of fine-grain (1-x)BiScO<sub>3</sub>-xPbTiO<sub>3</sub> ceramics by two-step sintering. 2008, **91**: 121-126.
- [11] Stringer CJ, Randall CA. In situ TEM investigations of the high-temperature relaxor ferroelectric BiScO<sub>3</sub>-Pb(Mg<sub>1/3</sub>Nb<sub>2/3</sub>)O<sub>3</sub>-PbTiO<sub>3</sub> ternary solid solution. *J Am Ceram Soc* 2007, **90**(6): 1802.
- [12] Stringer CJ, Shrout TR, Randall CA. Classification of transition temperature behavior in ferroelectric PbTiO<sub>3</sub>-Bi(Me'Me'')O<sub>3</sub> solid solutions. *J Appl Phys* 2006, **99**: 024106.
- [13] Comyn TP, McBride SP, Bell AJ. Processing and electrical properties of BiFeO<sub>3</sub>-PbTiO<sub>3</sub> ceramics. *Mater Lett* 2004, **58**: 3844-3846.
- [14] Cheng J, Li N, Cross LE. Structural and dielectric properties of Ga-modified BiFeO<sub>3</sub>-PbTiO<sub>3</sub> crystalline solutions. *J Appl Phys* 2003, **94**: 5153-5157.
- [15] Woodward DI, Reaney IM. Crystal and domain structure of the BiFeO<sub>3</sub>-PbTiO<sub>3</sub> solid solution. *Appl Phys Lett* 2003, **94**: 3313-3318.
- [16] Leontsevw SO, Eitel RE. Dielectric and piezoelectric properties in Mn-modified (1-x)BiFeO<sub>3</sub>-xBaTiO<sub>3</sub> ceramics. *J Am Ceram Soc* 2009, **92**: 2957-2961.
- [17] Leontsevw SO, Eitel RE. Origin and magnitude of the large piezoelectric response in the lead-free (1-x)BiFeO<sub>3</sub>-xBaTiO<sub>3</sub> solid solution. *J Mater Res* 2011, **26**(1): 9-17.
- [18] Itoh N, Shimura T, Sakamoto W, *et al.* Fabrication and characterization of BiFeO<sub>3</sub>-BaTiO<sub>3</sub> ceramics by solid state reaction. *Ferroelectrics* 2007, **356**: 19-23.
- [19] Sunder VVSS, Halliyal A, Umarji AM. Investigation of tetragonal distortion in the BiFeO<sub>3</sub>-PbTiO<sub>3</sub> system by high-temperature X-ray diffraction. *J Mater Res* 1995, **10**: 1301-1306.
- [20] Fedulov SA, Ladyzhinskii PB, Pyatigorskaya IL, *et al.* Complete phase diagram of the PbTiO<sub>3</sub>-BiFeO<sub>3</sub> system. *Sov Phys Solid State* 1964, **6**: 375-377.
- [21] Kumar MM, Srinivas A, Suryanarayana SV. Structure property relations in BiFeO<sub>3</sub>/BaTiO<sub>3</sub> solid solutions. *J Appl Phys* 2000, **87**: 855-862.
- [22] Guo X, Wu Y, Zou Y, *et al.*, Effects of addition of BiFeO<sub>3</sub> on phase transition and dielectric properties of BaTiO<sub>3</sub> ceramics. *J Mater Sci: Mater Electron* 2012, **23**: 1072-1076.
- [23] Chen S, Dong X, Mao C, *et al.* Thermal Stability of (1-x)BiScO<sub>3</sub>-xPbTiO<sub>3</sub> Piezoelectric Ceramics for High-Temperature Sensor Applications. *J Am Ceram Soc* 2006, **89**: 3270-3272.
- [24] Eitel RE, Randall CA, Shrout TR, *et al.* Preparation and characterization of high temperature perovskite ferroelectrics in the solid-solution (1-x)BiScO<sub>3</sub>-xPbTiO<sub>3</sub>. *Jpn J Appl Phys* 2002, **41**: 2099-2104.
- [25] Wataru S, Asaki I, Toshinobu Y. Ferroelectric properties of chemically synthesized perovskite BiFeO<sub>3</sub>-PbTiO<sub>3</sub> thin films. *J Appl Phys* 2008, **104**: 104106.
- [26] Thomas AS, Tim PC, Steven JM. Temperature stability of ([Na<sub>0.5</sub>K<sub>0.5</sub>NbO<sub>3</sub>]<sub>0.93</sub>-[LiTaO<sub>3</sub>]<sub>0.07</sub>) lead-free piezoelectric ceramics. *Appl Phys Lett* 2009, **94**: 222902.