

Preparation of Nb₃Al superconductor by powder metallurgy and effect of mechanical alloying on the phase formation

Zhao Liu · Yongliang Chen · Lupeng Du ·
Pingyuan Li · Yajing Cui · Xifeng Pan ·
Guo Yan

Received: 28 October 2013 / Revised: 16 January 2014 / Accepted: 18 January 2014 / Published online: 23 February 2014
© The Author(s) 2014. This article is published with open access at Springerlink.com

Abstract Adoption of powder-in-tube method to fabricate superconducting wire can realize a large application of Nb₃Al prepared by powder metallurgy. Powder metallurgy was used to synthesize Nb₃Al under various heat-treatment conditions, annealing temperature was varied from 700 to 1,000 °C and heating time was varied from 10 to 50 h. X-ray diffraction patterns reveal that a reaction between Nb and Al took place and formed NbAl₃ phase. Under current heat-treatment conditions (annealing temperature was varied from 700 to 1,000 °C and heating time was varied from 10 to 50 h), NbAl₃ was so stable that it did not further react with the unreacted Nb and was not sensitive to the heat-treatment condition. By mechanical alloying, adoption of high-energy ball milling significantly decreases particle size and enhances surface free energy, which promotes the formation of Nb₃Al phase. X-ray diffraction patterns indicate that relatively pure Nb₃Al phase was obtained under the same heat-treatment condition. Energy-dispersive X-ray analysis measurement demonstrates that the obtained samples were close to the right stoichiometry of A15 structure Nb₃Al.

Keywords Nb₃Al · Superconductivity · Powder metallurgy · Mechanical alloying

1 Introduction

With development of modern transportation and pursuit of high speed in various vehicles, superconducting maglev is promising in taking an important role in the future transportation system. Selection of a proper superconducting wire is vital in fabrication of superconducting magnet. Nb₃Al, due to its excellent superconducting properties, has drawn comprehensive attention since 1980s [1, 2]. A15 structure materials are famous for their superconductivities and Nb₃Al has the higher critical temperature among all the A15 structure materials [3, 4]. Furthermore, high value of critical current density (J_c) under high applied field makes it a promising substitution material for the fabrication of high-field magnet. The current existing fabrication method, powder-in-tube (PIT), makes it possible for a large-scale application of Nb₃Al prepared by powder metallurgy.

In International Thermonuclear Experimental Reactor (ITER) [5], compared with the well-developed Nb₃Sn, Nb₃Al possesses better stress/strain tolerance. This makes it an ideal choice for the fabrication of the toroidal field (TF) coil in terms of the large size of the D-shape TF [6, 7]. At the moment, the relatively successful methods to prepare Nb₃Al wire are restricted to high-temperature methods, because of the difficulty of the phase formation. Therefore, in order to acquire Nb₃Al in the right stoichiometry, high-temperature generation specialized instruments are needed, such as RHQT [8]. In this work, powder metallurgy was used to synthesize Nb₃Al and the effect of mechanical alloying on the phase formation was investigated.

Z. Liu · Y. Chen (✉) · L. Du · P. Li · Y. Cui
Key Laboratory of Magnetic Levitation Technologies and
Maglev Trains, Ministry of Education of China, and
Superconductivity and New Energy R&D Center, Southwest
Jiaotong University, Chengdu 610031, People's Republic of
China
e-mail: llchen@home.swjtu.edu.cn

X. Pan · G. Yan
Western Superconducting Technologies Co., Ltd., Xi'an 710018,
People's Republic of China

2 Methods

The experimental process includes into two parts. In the first part, normal hand grinding method was used to mill the Nb, Al powder. The mole ratio of Nb/Al = 3/1 was weighed, placed in an agate mortar and pestle, and mixed by gentle hand grinding for 0.5 h. The mixtures were pressed into round pellet with a diameter of 11.5 mm and a thickness of 1.5 mm using hardened steel die with uniaxial 12 MPa pressure. Then, the pellet was sealed into a vacuum-fused quartz tube with a vacuum degree of 5.5×10^{-3} Pa. Finally, the samples were heat treated in a tube furnace and argon was vented to avoid permeability or leakage.

In the second part, mechanical alloying was adopted and a SPEX [9] mixer 8000 high-energy mill was used. All other experimental procedures were the same.

The crystal structure was studied by powder X-ray diffraction (XRD) using an X'Pert MRD diffractometer with Cu $K\alpha$ radiation. All observed reflections were indexed. Lattice constants were determined from LeBail refinements. Microstructure and composition of the sample were analyzed using a field emission scanning electron microscope (FESEM) equipped with an energy-dispersive X-ray analysis (EDX). DC magnetization was measured with a SQUID magnetometer (MPMS, Quantum Design) and resistivity measurements were performed with a physical property measurement system (PPMS, Quantum Design).

3 Results and discussion

Figure 1 shows the XRD patterns of Nb/Al reaction samples sintered at 800 °C for different times. It can be observed that the main phases can be indexed as NbAl₃ and Nb. According to the phase diagram, Nb is inferred as the α -Nb which is the Nb-rich solid solution of aluminum in niobium. Figure 2 shows the XRD patterns of the samples sintered for 10 h at different sintering temperatures. Compared with the data of Fig. 1, it is obvious that both the changes of temperature and extension of heating duration make no difference to the resultant phase formation. Figure 2 shows the XRD patterns of the samples sintered for 10 h at different sintering temperatures. By comparison, it is apparent that either the change of temperature or extension of heating duration makes no difference to the resultant phase formation.

Thus, it is concluded that the reaction between Nb and Al results in the formation of NbAl₃ under the selected heat-treatment conditions. Furthermore, NbAl₃ is the most thermodynamically stable of the Nb–Al intermediate phases and so the kinetics of conversion to Nb₃Al by reaction with Nb can be expected to be slow. Consequently, it is

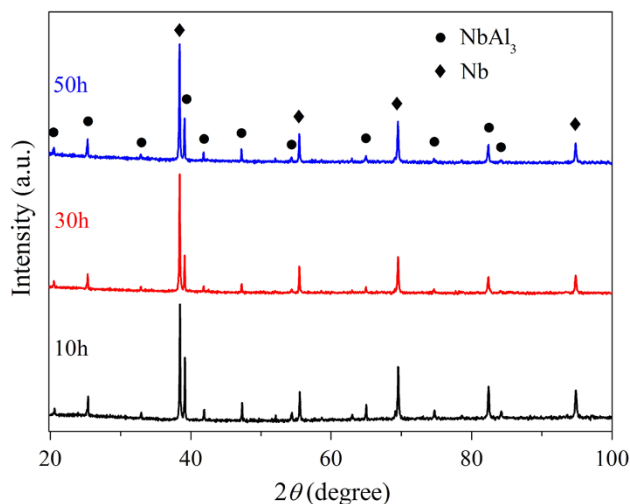


Fig. 1 XRD patterns of samples sintered at 800 °C

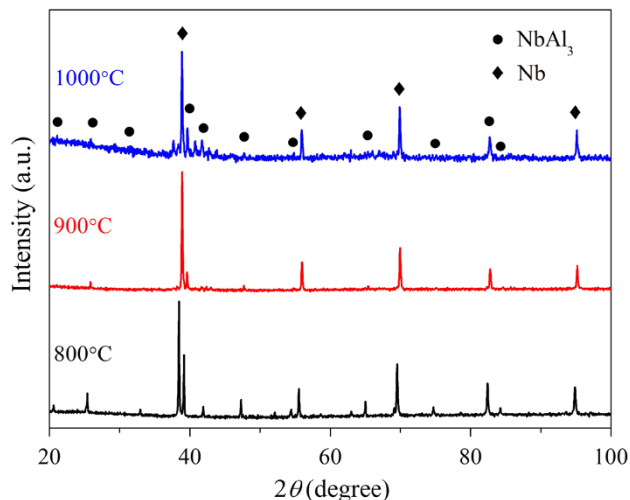


Fig. 2 XRD pattern of samples sintered at 10 h for different temperatures

concluded that, in the range of 800–1,000 °C, the temperature and duration of heat treatment are not the controlling factors of the formation of Nb₃Al.

The SEM image of sample sintered at 800 °C for 50 h is displayed in Fig. 3. It can be seen from the picture that the sample is very porous and the size of the biggest grain in this field of view is more than 10 μ m. The very coarse morphology of the sample would give the diffusion reaction a very long diffusion distance. Considering the very high formation enthalpy [9] of Nb₃Al, the long diffusion distance between the two grains makes it impossible for the formation of Nb₃Al using hand milling. The EDX data on grains (see Table 1) support the conclusion that the big grains are NbAl₃.

Figure 4 shows the XRD patterns of Nb₃Al samples prepared for different spex milling and sintering times at

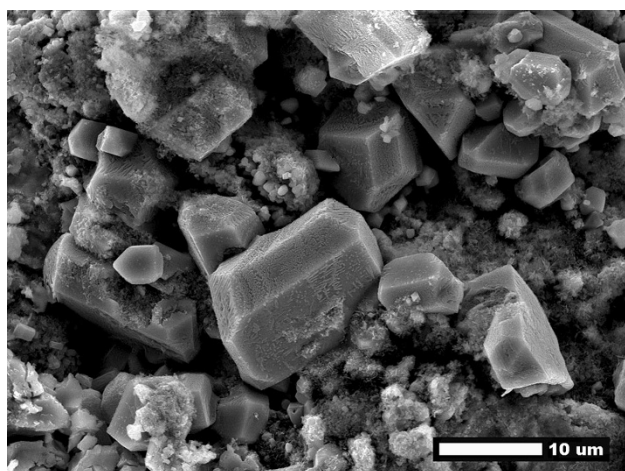


Fig. 3 SEM image for the sample sintered at 800 °C for 50 h

Table 1 EDX results of a random point on the grain

Element	Weight (%)	Atom (%)
Al	44.0	73.0
Nb	56.0	27.0

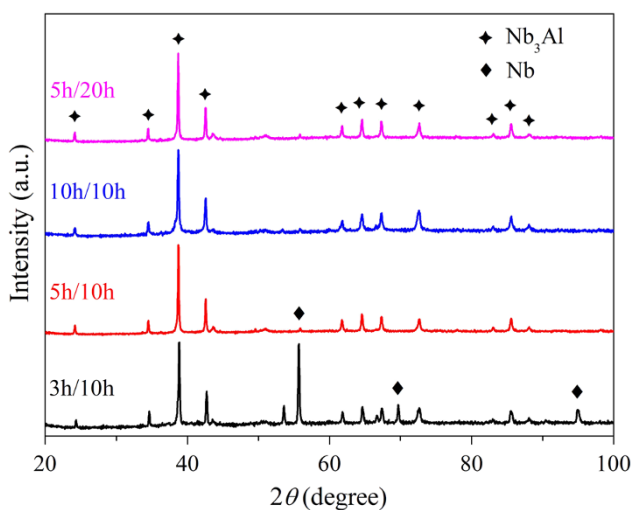


Fig. 4 XRD patterns of the samples prepared for different milling and sintering times at 900 °C

900 °C. The main phase can be indexed as the A15 structure Nb₃Al. The high-purity Nb₃Al sample was obtained when the spex milling time reached to 5 h, and spex milling for 10 h and sintering for 10 h gave the optimal sample. The sample that was spex milled for only 3 h contained a great quantity of Nb. This can be explained by short spex milling time; the Nb/Al powders lacked enough extra driving forces for diffusion reaction. Furthermore, it can be seen from all the four patterns that no NbAl₃ phase was found, thus indicating that spex milling is

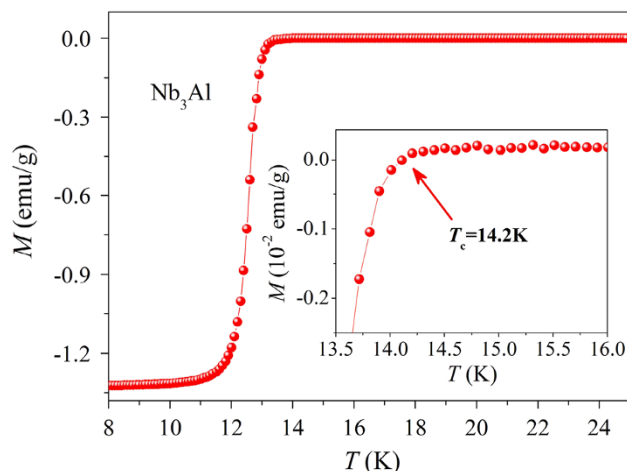


Fig. 5 The temperature dependence of magnetization for the Nb₃Al sample, and *inset* shows the enlarged view of the superconducting transition

effective in increasing the activity of the two powders by improving the mixing and reducing the diffusion distance.

Figure 5 shows the temperature dependence of magnetization for the sample spex milled for 5 h and sintered for 20 h, and the critical temperature (T_{conset}) is 14.2 K which is 4 K lower than the optimal value. The impurity phases and the porous microstructure may give rise to the poor superconducting property, although little impurity phase was indexed from the XRD patterns. It should be noted that no superconducting transition of Nb was detected, which further confirms that the Nb has sufficiently reacted. However, it is important to realize that the Nb₃Al single phase range is relatively wide according to the phase diagram. In addition, the heat-treatment temperature selected in this work can only give an Nb₃Al sample with the stoichiometry of only 20 at.% Al. Therefore, the deviation from the right stoichiometric concentration of Aluminum may be another reason that accounts for the low T_c of the sample, though the sample is an almost-pure single phase as the XRD reflects.

4 Conclusions

1. The composition of Nb/Al powder used in the experiment is not in the Nb₃Al solid solution homogeneity region in phase diagram of Nb–Al binary alloy, but the as-grown sample appears to be single phase.
2. 800 °C is not adequate in terms of kinetics for the equilibration of Nb₃Al phase formation.
3. Spex milling is effective in increasing activity of the powders by improving the mixing of the powders, simultaneously reducing the diffusion distance. By adoption of spex milling and the conventional PIT

method, fabrication of Nb₃Al magnet under low temperature can be realized.

4. The impurities and the deviation of the right stoichiometric concentration of aluminum in Nb₃Al are probably responsible for the poor quality of superconducting transition.
5. Combination of spex milling and the PIT method may be one of the solutions to prepare Nb₃Al wire under low temperature in the future.

Acknowledgments This work was supported by the National Magnetic Confinement Fusion Science Program (Grant No. 2011GB112001), the Program of International S&T Cooperation (Grant No. 2013DFA51050), the National Natural Science Foundation of China (Grant Nos. 11104224, 11004162, 51377138, and 51302224), the Research Fund for the Doctoral Program of Higher Education of China (Grant No. 20110184120029), the Fundamental Research Funds for the Central Universities (Grant Nos. 2682013ZT16, SWJTU11ZT31, 2682013CX004, and SWJTU11BR063), and the Science Foundation of Sichuan Province (Grant Nos. 2011JY0031 and 2011JY0130).

Open Access This article is distributed under the terms of the Creative Commons Attribution License which permits any use, distribution, and reproduction in any medium, provided the original author(s) and the source are credited.

References

1. Yamada Y, Ayai N (1999) Development of Nb₃Al superconductors for International Thermonuclear Experimental Reactor (ITER). *Cryogenics* 39:115–122
2. Koizumi N, Takeuchi T, Okuno K (2005) Development of advanced Nb₃Al superconductors for a fusion demo plant. *Nucl Fusion* 45:431–438
3. Takeuchi T (2000) Nb₃Al conductors for high-field applications. *Supercond Sci Technol* 13:R101–R119
4. Okuno K, Shikov A, Koizumi N (2004) Superconducting magnet system in a fusion reactor. *J Nucl Mater* 329–333:141–147
5. Seeber B (2007) Critical current of a Nb₃Sn bronze route conductor under uniaxial tensile and transverse compressive stress. *Supercond Sci Technol* 20:S184–S188
6. Ando T (1996) Design consideration of the ITER-TF coil with a react-and-wind technique using Nb₃Al conductor. *IEEE Trans Magn* 32:2324–2327
7. Fukuzaki T, Takeuchi T, Banno N (2002) Effect of rapid heating, quenching and transformation conditions on the superconducting properties and microstructure of Jelly-Roll processed Nb₃Al superconductors. *Supercond Sci Technol* 15:1404–1409
8. Koizumi N, Ando T, Sugimoto M et al (1998) Development of a 13-T and 40-kA Nb₃Al conductor for toroidal coils of fusion reactors. *Fusion Eng Des* 41:277–281
9. Calka A, Wexler D, Zhou J et al (1998) Mechano-synthesis of niobium–aluminum superconductors for the high field applications. *Mater Sci Forum* 269–272:1043–1048