

NANO EXPRESS

Open Access

Exciton quantum confinement in nanocones formed on a surface of CdZnTe solid solution by laser radiation

Artur Medvid'^{1*}, Natalia Litovchenko^{2^}, Aleksandr Mychko¹ and Yuriy Naseka²

Abstract

The investigation of surface morphology using atomic force microscope has shown self-organizing of the nanocones on the surface of CdZnTe crystal after irradiation by strongly absorbed Nd:YAG laser irradiation at an intensity of 12.0 MW/cm². The formation of nanocones is explained by the presence of a thermogradient effect in the semiconductor. The appearance of a new exciton band has been observed after irradiation by the laser which is explained by the exciton quantum confinement effect in nanocones.

Keywords: Nanocones, Exciton quantum confinement effect, Thermogradient effect, CdZnTe, Nd:YAG laser

Background

Nowadays, nanostructures are one of the most investigated objects in semiconductor physics, especially the quantum confinement effect (QCE) in such quantum systems as quantum dots or 0D [1-5], quantum wires or 1D [6-8] and quantum wells or 2D [9-14]. In the case of nanostructures, the energy band diagram of the semiconductor is strongly changed. This leads to a crucial change of semiconductor properties, such as electrical properties (the change of free charge carriers concentration and their mobility), optical properties (absorption coefficient, reflectivity coefficient, and radiative recombination efficiency), and mechanical and thermal properties [15]. Another possibility to change a property of a semiconductor is by using solid solution, such as Cd_{1-x}Zn_xTe [16] and Si_{1-x}Ge_x [17], which change the component content. It was shown [18] that the shapes and sizes of the mentioned quantum systems have more influence on the properties of a semiconductor than its component content. For example, the 'blue shift' of Si_{0.7}Ge_{0.3} photoluminescence (PL) spectrum of nanocones is up to 1.2 eV, but the possible maximal shift of PL spectra due to change of x is only up to 0.33 eV. Moreover, the band of PL spectrum is broader and more

intense due to QCE and graded band gap. Moreover, nanocones enhance radiation hardness of CdZnTe detector, as shown in [19].

In this paper, we report about the appearance of a new band in PL spectra of Cd_{1-x}Zn_xTe solid solution irradiated by Nd:YAG laser, which is explained by exciton QCE in nanocones formed on the irradiated surface of the sample.

Methods

The laser processing was performed on the samples of Cd_{1-x}Zn_xTe solid solution with $x=0.1$ in ambient atmosphere at room temperature, pressure 1 atm, and 80% humidity. The surface of Cd_{1-x}Zn_xTe sample was irradiated by pulses of Nd:YAG laser with the wavelength of $\lambda=532$ nm, pulse duration of $\tau=15$ ns and power $p=1$ MW. The spot of laser beam with 3 mm diameter was moved by 20 μm steps over the surface of the sample. Atomic force microscope (AFM) was used for the study of the irradiated surface morphology. The low-temperature PL at 5 K was carried out to investigate the optical properties of the nanostructures formed by laser radiation (LR) on the samples. He-Ne laser with $\lambda=632.8$ nm was used as an excitation source.

Results and discussion


The formation of nanocones on a surface of Cd_{1-x}Zn_xTe solid solution with $x=0.1$ after irradiation by the

* Correspondence: medvids@latnet.lv

[^] Deceased


¹Riga Technical University, Azenes Street 14, Riga 1048, Latvia

Full list of author information is available at the end of the article

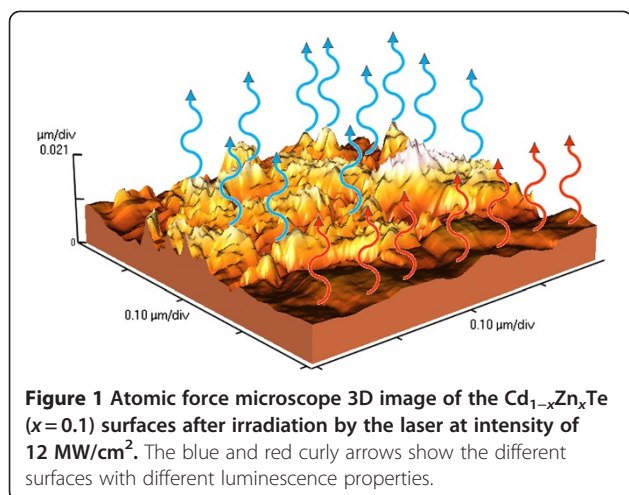

strongly absorbed Nd:YAG laser radiation with intensity of $I = 12.0 \text{ MW/cm}^2$ was observed using AFM, as shown in Figure 1.

While studying the optical properties of nanocones, a new exciton band at energy up to 1.87 eV in PL spectrum for the first time was found, as shown in Figure 2. The PL spectrum is rather complex, consisting of an intense line (A^0, X) at 1.6362 eV , which is ascribed to bound excitons to shallow acceptors (Cd vacancies, V_{Cd}) and its longitudinal optical (LO)-phonon replica at 1.6181 eV , an intense line (D^0, X) at 1.6475 eV ascribed to bound excitons to shallow donors (Cd interstitial atoms, I_{Cd}). At the same time, the shift of A^0X and D^0X exciton lines of 3.2 and 2.7 meV , correspondingly, toward the higher energy of quantum, that is, the so-called 'blue shift' was observed, as shown in Figure 2. The appearance of a new PL band is explained by exciton quantum confinement (EQC) effect in nanocones, and

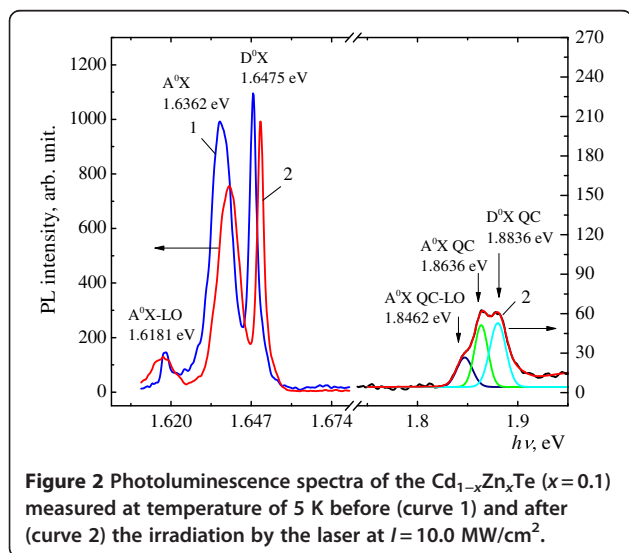

the blue shift of A^0X and D^0X exciton bands - due to photo-induced mechanical compressive stress of the top layer.

This process takes place in the following way: the irradiation of the $\text{Cd}_{1-x}\text{Zn}_x\text{Te}$ solid solution by the laser leads to the drift of Cd atoms toward the irradiated surface and of Zn atoms - in the opposite direction due to high gradient of temperature. This is so-called thermo-gradient effect (TGE) [20]. As a result, the formation of $\text{CdTe}/\text{Cd}_{1-x_1}\text{Zn}_{x_1}\text{Te}$ heterostructure, where $x_1 > x$, takes place due to the replacement of Zn atoms by Cd atoms at the irradiated surface. At the same time, the opposite process takes place under the top layer. In the buried layer of the semiconductor, Zn atoms replace Cd atoms. At least three factors determine A^0X and D^0X exciton lines position in PL spectrum. They are as follows: the concentration of Zn atoms in the CdTe top layer and in CdZnTe buried layer, 2D EQC effect in the CdTe layer when its thickness is comparable with Bohr radius of the exciton, and the mechanical compressive stress of the CdTe top layer due to mismatch of CdTe and CdZnTe crystalline lattice constant.

The decrease of Zn atoms concentration in the top layer with increased intensity of LR, according to the proposed model, leads to the 'red shift' of the exciton bands in PL spectra, as was shown in [21], but increase of the Zn atoms concentration in the buried CdZnTe layer manifests itself in the blue shift of PL spectrum, as shown in Figure 3. These effects do not compensate each other because they take place in different layers. This unusual situation can be explained by different input of these layers in the position and intensity of PL spectrum. If the top layer is excited by short wavelength light, then mostly the red shift of PL spectrum will be observed; but if mainly the buried layer is excited, for example, due to small thickness or transparency of top layer, then the blue shift will be observed. Of course, it is possible to observe both PL spectra simultaneously at intermediate situation. Such situation is exactly observed in the PL spectrum in Figure 2, after the destruction of the CdTe top layer and formation of nanocones on the irradiated surface of the sample. The relaxation of the mechanical compressive stress in CdTe layer corresponds to the decreasing part of the curves in Figure 3. It is manifested as the self-assembly of nanocones on the irradiated surface of the structure as explained by Stransky-Krastanov' growth mode. A simultaneous appearance of a new exciton band at 1.872 eV in PL spectrum at high intensity of LR takes place. The reconstruction of this band according to Gaussian fitting shows that it consists of three lines which look like A^0X , D^0X , and $A^0X\text{-LO}$ lines (the distance between the lines and their full width at half maximum are the same) in the nonirradiated PL spectrum of the semiconductor.

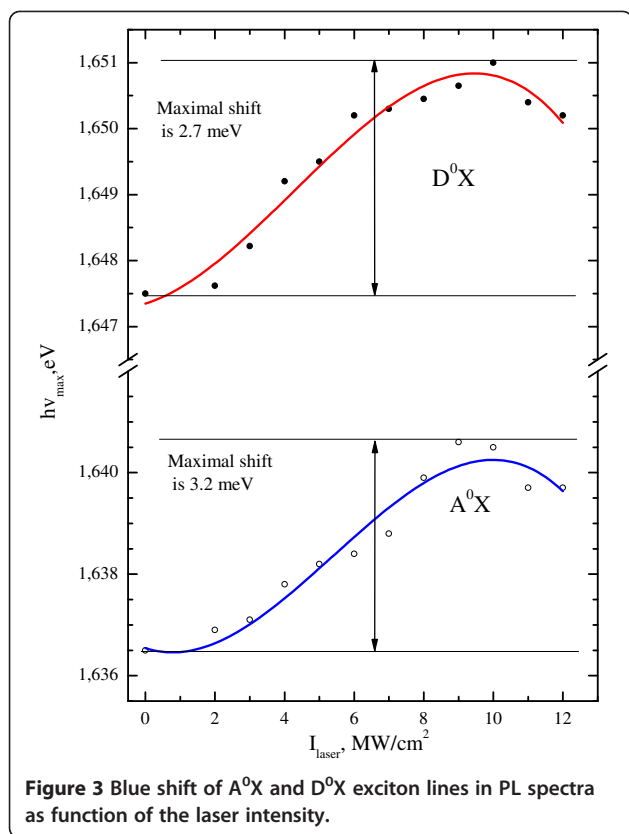


Figure 3 Blue shift of A^0X and D^0X exciton lines in PL spectra as function of the laser intensity.

Therefore, we connect the appearance of the new lines in PL spectrum with the nanocones' formation on the irradiated surface of the semiconductor and with EQC in the nanocones. We denote them as A^0XQC and D^0XQC lines. An evidence of the mechanical stress relaxation process in CdTe layer is a non-monotonic dependence of the blue shift as a function of LR intensity, as shown in Figure 3. Such non-monotonic dependence have been observed in p- and n-type Si after studying of mechanical micro hardness of Si after irradiation by Nd: YAG laser [22]. The calculation of the mechanical compressive stress in CdTe top layer using the maximum of the blue shift of A^0X exciton line from Figure 3 and $dE_g/dP = 10$ eV/GPa [23], where E_g and P are band gap of CdTe crystal and mechanical stress, correspondingly, gives $P = 4.62 \times 10^5$ Pa. This value corresponds to the ultimate strength limit of CdTe [24]. The calculation of the quantum dot diameter using formula from [25] and the blue shift of A^0XQC in the PL spectrum of 0.27 eV gives about 10.0 nm diameter of the quantum dots. These data correspond to the size of nanocones [26] (height and diameter of the bottom of the cones are 10.0 nm) measured using 3D image of AFM as can be seen in Figure 1. An evidence of the presence of EQC in nanocones is the decrease of LO phonon energy by 0.7 meV in the PL spectrum. This is the so-called 'phonon quantum confinement effect' [27]. Moreover, the

increase of Huang-Rhys factor for A^0X -LO line up to three times is a good evidence of EQC effect in the nanocones. Our calculation of Zn atoms distribution depending on the intensity of LR using the thermo-diffusion equation has shown that the process of CdTe/ $Cd_{1-x_1}Zn_{x_1}Te$ heterostructure formation is characterized by the gradual increase of Zn atoms concentration in the buried layer with intensity of LR up to 8% ($x_1 = 0.18$). The thickness of the CdTe layer after irradiation by the laser with intensity of $I = 12.0$ MW/cm² becomes 10 nm. The process of nanocones formation is characterized by the LR threshold intensity of approximately $I = 10.0$ MW/cm², as can be seen in Figure 3: nanocones formation starts at the maximums of the blue shift position. Therefore, the process of the nanocones formation is characterized by two stages: the first stage is the formation of CdTe/ $CdZnTe$ heterostructure, and the second stage is the nanocones' self-assembly due to laser annealing of the mechanical compressive stress in CdTe layer. An evidence of the presence of the first stage of nanocones formation process is the redistribution of the intensity of LO-ZnTe, TO-CdTe, and LO-CdTe phonon bands in Raman back scattering spectra, as shown in Figure 4.

It means that before the irradiation of the sample by the laser, the intensity of LO-ZnTe phonon band was three to four times higher than the intensity of TO and LO-CdTe phonon bands, but after irradiation the opposite situation in Raman spectra is observed.

Conclusions

The studies of the effect of highly absorbed laser radiation on the optical properties of the $Cd_{1-x}Zn_xTe$ ($x = 0.1$) compound have revealed the formation of nanocones on the surface of the semiconductor under

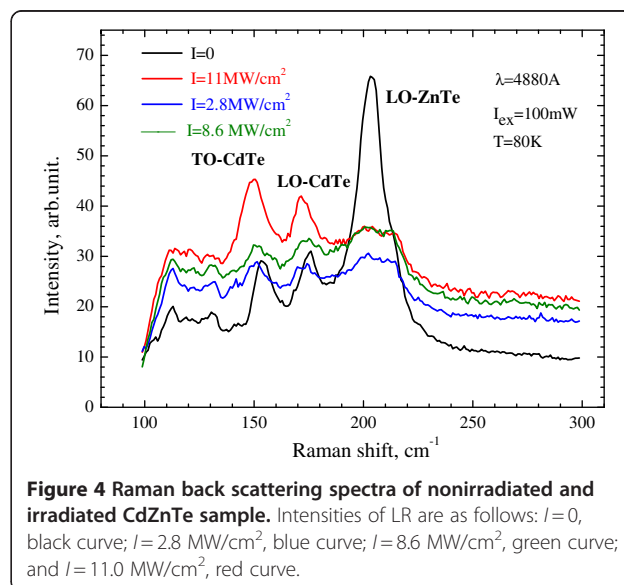


Figure 4 Raman back scattering spectra of nonirradiated and irradiated CdZnTe sample. Intensities of LR are as follows: $I = 0$, black curve; $I = 2.8$ MW/cm², blue curve; $I = 8.6$ MW/cm², green curve; and $I = 11.0$ MW/cm², red curve.

irradiation by the Nd:YAG laser within the intensity range of 9.0-12.0 MW/cm² and the simultaneous appearance of a new PL band at 1.87 eV, which is explained by the exciton quantum confinement effect in nanocones.

The TGE has the main role in redistribution of Zn atoms at the surface of Cd_{1-x}Zn_xTe irradiated by the second harmonic of Nd:YAG laser. The graded band gap structure with open optical window is formed on the top of nanocones after the irradiation by Nd:YAG laser at the intensity 4.0-12.0 MW/cm². Formation of a graded band gap with a close of optical window in Cd_{1-x}Zn_xTe crystal is possible under irradiation by the second harmonic of Nd:YAG laser at the intensity 0.2-2.0 MW/cm². A two-stage model of the nanocones formation on the surface of the Cd_{1-x}Zn_xTe ($x = 0.1$) under the irradiation by Nd:YAG laser at the intensity 4.0-12.0 MW/cm² was proposed.

Abbreviations

AFM: Atomic force microscope; 0D: Quantum dots; 1D: Quantum wires; 2D: Quantum wells; EQC: Exciton quantum confinement; I_{Cd} : Cd interstitial atoms; LR: Laser radiation; PL: Photoluminescence; QCE: Quantum confinement effect; TGE: Thermogradient effect; V_{Cd} : Cd vacancies.

Competing interests

The authors declare that they have no competing interests.

Authors' contributions

AM and LN conceived the studies and coordinated the experiment. All of the authors participated to the analysis of the data and wrote the article. AMy and YN carried out the sample preparation, the measurements for solid solutions of CdZnTe. All the authors read and approved the manuscript.

Acknowledgment

The authors gratefully acknowledge the financial support in part by the European Regional Development Fund within the projects 'Sol-gel and laser technologies for the development of nanostructures and barrier structures' and 2010/0221/2DP/2.1.1.0/10/APIA/VIAA/145, RTU PVS ID 1535.

Author details

¹Riga Technical University, Azenes Street 14, Riga 1048, Latvia. ²Institute of Semiconductor Physics, NAS of Ukraine, Pr. Nauki 28, Kyiv 03028, Ukraine.

Received: 15 August 2012 Accepted: 6 September 2012

Published: 20 September 2012

References

1. Alivisatos A: Semiconductor clusters, nanocrystals, and quantum dots. *Science* 1996, **271**:933-937.
2. Norris D, Bawendi M: Measurement and assignment of the size-dependent optical spectrum in CdSe quantum dots. *Phys Rev B* 1996, **53**:16338-16346.
3. Kunz A, Weidman R, Collins T: Pressure-induced modifications of the energy band structure of crystalline CdS. *J Phys C: Solid State Phys* 1981, **14**:L581-L584.
4. Lee C, Mizel A, Banin U, Cohen M, Alivisatos A: Observation of pressure-induced direct-to-indirect band gap transition in InP nanocrystals. *J Chem Phys* 2000, **113**:2016-2020.
5. Yoffe A: Low-dimensional systems - quantum-size effects and electronic properties of semiconductor micro crystallites (zero-dimensional systems) and some quasi-2-dimensional systems. *Adv Phys* 1993, **42**:173-266.
6. Xia Y, Yang P, Sun Y, Wu Y, Mayers B, Gates B, Yin Y, Kim F, Yan H: One-dimensional nanostructures: synthesis, characterization, and applications. *Adv Mater* 2003, **15**:353-389.

7. Krutarth T, Hyungsang Y, Herman C, Moon J, Walter H: Quantum confinement induced performance enhancement in sub-5-nm lithographic Si nanowire transistors. *Nano Lett* 2011, **11**:1412-1417.
8. Reed M, Randall J, Aggarwal R, Matyi R, Moore T, Wetsel A: Observation of discrete electronic states in a zero-dimensional semiconductor nanostructure. *Phys Rev Lett* 1988, **60**:535-537.
9. Fowler A, Fang F, Howard W, Stiles P: Magneto-oscillatory conductance in silicon surfaces. *Phys Rev Lett* 1966, **16**:901-903.
10. Tulkki J, Heinamaki A: Confinement effect in quantum well dot induced by InP stressor. *Phys Rev B* 1995, **52**:8239.
11. Xiao X, Liu C, Sturm J, Lenchyshyn L, Thewalt M, Gregory R, Fejes P: Quantum confinement effects in strained silicon-germanium alloy quantum wells. *Appl Phys Lett* 1992, **60**:2135-2137.
12. Kuo Y, Lee Y, Ge Y, Ren S, Roth J, Kamins T, Miller D, Harris J: Strong quantum-confined Stark effect in germanium quantum-well structures on silicon. *Nature* 2005, **437**:1334-1336.
13. Dingle R, Wiegmann W, Henry C: Quantum states of confined carriers in very thin Al_xGa_{1-x}As-GaAs-Al_xGa_{1-x} as heterostructures. *Phys Rev Lett* 1974, **33**:827-830.
14. Parsons C, Thacker B, Szymid D, Peterson M, McMahon W, Nozik A: Characterization and photocurrent spectroscopy of single quantum wells. *J Chem Phys* 1990, **93**:7706-7715.
15. Li J, Hong X, Liu Y, Li D, Wang Y, Li J, Bai Y, Li T: Highly photoluminescent CdTe/poly(N-isopropylacrylamide) temperature-sensitive gels. *Adv Mater* 2005, **17**:163-166.
16. Reno J, Jones E: Determination of the dependence of the band-gap energy on composition for Cd_{1-x}Zn_xTe. *Phys Rev B* 1992, **45**:1440-1442.
17. Sun K, Sue S, Liu C: Low-dimensional systems and nanostructures. *Physica E* 2005, **28**:525-530.
18. Medvid' A: Nano-cones formed on a surface of semiconductors by laser radiation: technology, model and properties. In *Nanowires Science and Technology*. Edited by Viena LN. Rijeka: INTECH; 2010:61-82.
19. Medvid' A, Mychko A, Dauksta E, Naseka Y, Crocco J, Dieguez E: The effect of laser radiation on CdZnTe radiation hardness. *JINST* 2011, **6**:C11010.
20. Medvid' A: Redistribution of point defects in the crystalline lattice of a semiconductor in an inhomogeneous temperature field. *Defect Diffus Forum* 2002, **89-102**:210-212.
21. Medvid' A, Fedorenko L, Korbutjak B, Kryluk S, Yusupov M, Mychko A: Formation of graded band-gap in CdZnTe by YAG:Nd laser radiation. *Radiat Meas* 2007, **42**:701-703.
22. Medvid' A, Onufrijevs P, Chiradz G, Muktapavela F: Impact of laser radiation on microhardness of a semiconductor. *AIP Conf Proc* 2011, **1399**:181-182.
23. Thomas D, Hopfield J: Excitons and band splitting produced by uniaxial stress in CdTe. *J Appl Phys* 1961, **32**:2298-2304.
24. Yonenaga I: Hardness, yield strength, and dislocation velocity in elemental and compound semiconductors. *Mater Trans* 2005, **46**:1979-1985.
25. Kayanuma Y: Quantum-size effects of interacting electrons and holes in semiconductor microcrystals with spherical shape. *Phys Rev B* 1988, **38**:9797-9805.
26. Lee H, Park H, Lee I, Kim T: Formation and optical properties of CdTe/ZnTe nanostructures with different CdTe thicknesses grown on Si (100) substrates. *Appl Phys Lett* 2007, **102**(103507):1-5.
27. Campbell H, Fauchet P: The effect of microcrystal size and shape on the one phonon Raman-spectra of crystalline semiconductors. *Solid State Commun* 1986, **58**:739-741.

doi:10.1186/1556-276X-7-514

Cite this article as: Medvid' et al.: Exciton quantum confinement in nanocones formed on a surface of CdZnTe solid solution by laser radiation. *Nanoscale Research Letters* 2012 **7**:514.