

NANO COMMENTARY

Open Access

Photo-induced electric polarizability of Fe₃O₄ nanoparticles in weak optical fields

Valentin A Milichko^{1,2*}, Anton I Nechaev³, Viktor A Valtsifer³, Vladimir N Strelnikov³, Yurii N Kulchin¹ and Vladimir P Dzyuba¹

Abstract

Using a developed co-precipitation method, we synthesized spherical Fe₃O₄ nanoparticles with a wide nonlinear absorption band of visible radiation. Optical properties of the synthesized nanoparticles dispersed in an optically transparent copolymer of methyl methacrylate with styrene were studied by optical spectroscopy and z-scan techniques. We found that the electric polarizability of Fe₃O₄ nanoparticles is altered by low-intensity visible radiation ($I \leq 0.2 \text{ kW/cm}^2$; $\lambda = 442$ and 561 nm) and reaches a value of 10^7 \AA^3 . The change in polarizability is induced by the intraband phototransition of charge carriers. This optical effect may be employed to improve the drug uptake properties of Fe₃O₄ nanoparticles.

Keywords: Magnetite nanoparticles; Electric polarizability; Low-intensity visible radiation

PACS: 33.15.Kr; 78.67.Bf; 42.70.Nq

Background

Magnetite (FeO*Fe₂O₃, or Fe₃O₄) nanoparticles, and materials based on them, have been successfully used to solve applied problems in biology and magneto-optics. Pronounced superparamagnetic [1-4] and ferromagnetic [5] properties at room temperature enable the use of these nanoparticles in magnetic resonance imaging [6-9] and biosensing [9] as well as in drug delivery and drug uptake applications [8-13]. Because they possess magneto-optical properties [14,15], Fe₃O₄ nanoparticles have also been used to develop tunable filters [16,17] and optical switches [18,19] that operate under magnetic fields.

In fact, Fe₃O₄ nanoparticles have been examined for the presence of unique magnetic properties because magnetite is a narrow-gap semiconductor [20-22] and the optical properties of other semiconductor nanoparticles have been thoroughly studied. Currently, there are several experimental and theoretical works dedicated to studying the optical properties of both bulk magnetite [23-26] and its nanoparticles [27-29]. However, some

specific optical properties of Fe₃O₄ nanoparticles (in particular, the effects of electric polarizability on their biological activity, conductivity, ferroelectricity, and electro-optical properties) as well as the nature of these properties remain virtually unexplored.

In this paper, we demonstrate that Fe₃O₄ nanoparticles exhibiting a wide nonlinear absorption band of visible radiation (1.7:3.7 eV) are able to significantly change their electric polarizability when exposed to low-intensity visible radiation ($I \leq 0.2 \text{ kW/cm}^2$). The observed change in polarizability was induced by the intraband phototransition of nanoparticle charge carriers, and polarizability changes were orders of magnitude greater than those of semiconductor nanoparticles and molecules [30,31].

Experiments

Synthesis of nanoparticles

There are several techniques for the synthesis of Fe₃O₄ nanoparticles with an arbitrary shape and size and for their dispersal in different matrices [4,5,11,12,27,29,32-36]. In this study, we synthesized nanoparticles using co-precipitation method [1,2,13-15,37,38], dispersed them in monomeric methyl methacrylate with styrene (MMAS), and polymerized this composition using pre-polymerization method.

* Correspondence: ariesval@mail.ru

¹Institute of Automation and Control Processes, FEB RAS, Radio 5, Vladivostok 690041, Russia

²Far Eastern Federal University, Sukhanova 8, Vladivostok 690950, Russia

Full list of author information is available at the end of the article

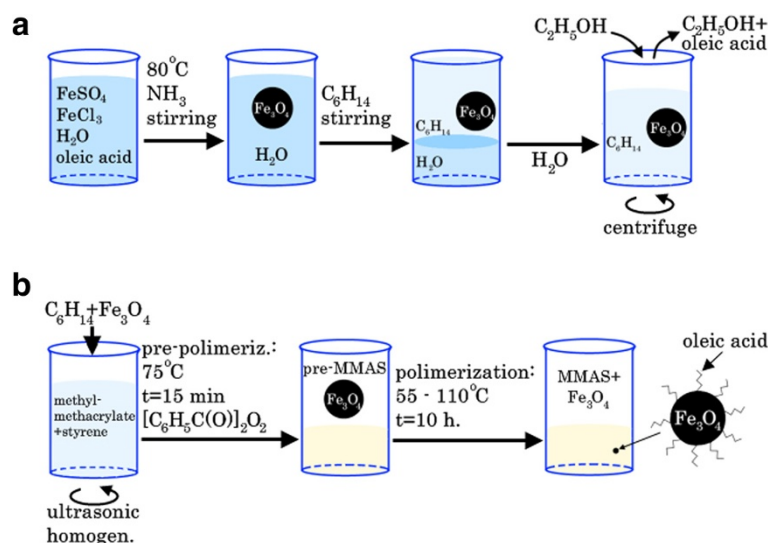


Figure 1 The developed co-precipitation method. (a) The synthesis of Fe₃O₄ nanoparticles with a monolayer of oleic acid by the developed co-precipitation method and (b) the composite MMAS + Fe₃O₄ preparation.

In the first step (Figure 1a), Fe₃O₄ nanoparticles were synthesized by co-precipitation of soluble salts of ferrous and ferric ions with an aqueous ammonia solution: FeSO₄*7H₂O + 2FeCl₃*6H₂O + 8NH₃*H₂O ↔ Fe₃O₄ + 6NH₄Cl + (NH₄)₂SO₄ + 20H₂O.

Oleic acid (in a mass ratio of 0.7:1 with the formed Fe₃O₄) was added to a 0.5% solution of iron salts (FeSO₄/FeCl₃ = 1:2.2 molar ratio) in 0.1 M HCl. The aqueous solution of iron salts was heated to 80°C, followed by the addition of concentrated aqueous ammonia (20% excess). The solution was heated and stirred for an hour.

Stabilized nanoparticles were then extracted from the aqueous phase into a nonpolar organic solvent hexane at a ratio of 1:1. The organic layer containing the iron oxide Fe₃O₄ was separated from the aqueous medium. The sample was centrifuged for 15 min (6,000 rpm) to remove larger particles. Excess acid was removed with ethanol.

The size of the nanoparticles was determined by dynamic light scattering method (Zetasizer Nano ZS, Malvern, UK). Measurements were conducted in hexane with a laser wavelength of 532 nm. The average hydrodynamic diameter of the synthesized nanoparticles was 15 nm, as illustrated in Figure 2.

Composite preparation

The second step (Figure 1b) focused on obtaining a solid composite based on Fe₃O₄ nanoparticles and MMAS. The organic solvent containing nanoparticles and monomers (methyl methacrylate with styrene) was subjected to stirring and ultrasonic homogenization. To prevent nanoparticle aggregation during the polymerization

process, we used the pre-polymerization method at 75°C because the nanoparticles had different affinities to the monomer and polymer.

Finally, the composite was synthesized *in situ* by radical polymerization. The polymerization of methyl methacrylate with styrene (in the mass ratio of 20:1) proceeded for over 10 h (in a temperature gradient mode that progressed from 55°C to 110°C) in the presence of benzoyl peroxide (10⁻³ mol/L).

The obtained solid composites had 0.001%, 0.003%, 0.005%, and 0.01% volume concentrations of Fe₃O₄ nanoparticles in MMAS. Importantly, the synthesized Fe₃O₄ nanoparticles generally had a thick layer of acids [36,39] surrounding them to prevent aggregation of the nanoparticle. In our case, the synthesized Fe₃O₄

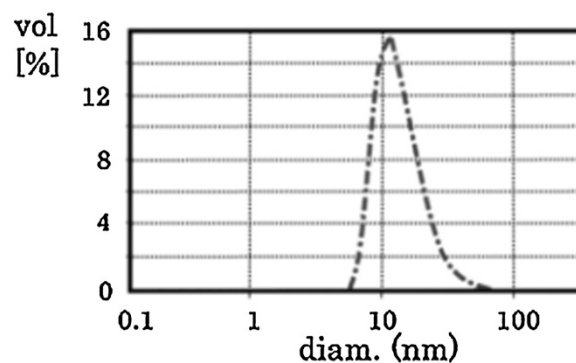


Figure 2 Nanoparticle size. The average hydrodynamic diameter of the synthesized nanoparticles (15 nm) dispersed in hexane was determined by dynamic light scattering method (Zetasizer Nano ZS, Malvern, UK) at a laser wavelength of 532 nm.

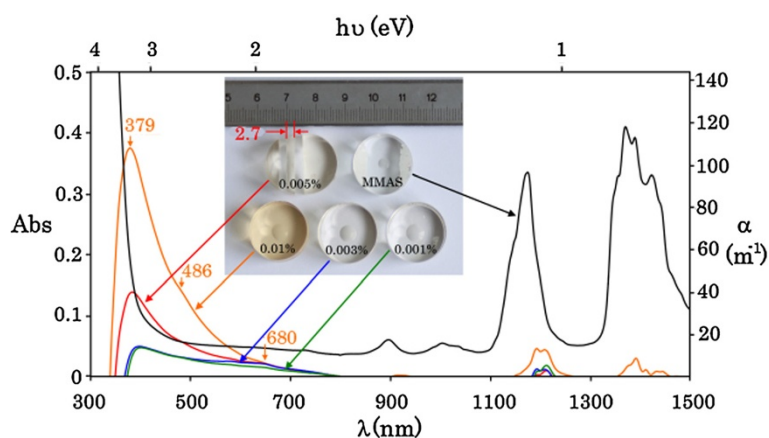


Figure 3 Absorbance spectra for the MMAS and Fe_3O_4 nanoparticle array. The optical absorbance spectra for pure MMAS and Fe_3O_4 nanoparticle arrays with 0.001%, 0.003%, 0.005%, and 0.01% volume concentrations.

nanoparticles had a monolayer of oleic acid that allowed the nanoparticles to exhibit their specific optical properties.

UV-vis spectroscopy

Room-temperature optical absorbance spectra of pure MMAS (Figure 3, black curve) and of the composites were obtained using a Varian Cary 5000I spectrophotometer (Agilent Technologies, Santa Clara, CA, USA) over the wavelength range of 300 to 1,500 nm. These spectra allowed the derivation of the absorbance spectra for Fe_3O_4 nanoparticle arrays (Figure 3, color curves). Figure 3 shows the absorbance values (Abs) and the absorption coefficients ($\alpha = (\text{Abs} \times \ln 10)/l$, where $l = 7.95$ mm is the length of the composite) measured at a maximum radiation intensity of $1 \mu\text{W}/\text{cm}^2$.

z-Scan experiments

Because they have absorption bands of 380 to 650 nm, Fe_3O_4 nanoparticles should exhibit an optical response upon external radiation with wavelengths in this band [40]. To detect the optical response of the nanoparticles contained in the composite (0.005% nanoparticle volume concentration), we used the standard z-scan technique [41]. This technique enabled the analysis of changes in the absorption coefficient $\Delta\alpha(I)$ and refractive index $\Delta n(I)$ of the composite and pure MMAS, which were induced by weak optical radiation with different intensities 0 to $0.14 \text{ kW}/\text{cm}^2$.

For radiation sources, we used semiconductor lasers of continuous wave (cw) radiation with wavelengths of 442 nm (blue) and 561 nm (yellow) providing maximal intensities of 0.07 and $0.14 \text{ kW}/\text{cm}^2$. Lenses with focal lengths of 75 mm provided the beam waists $\omega_0 = 102$ and $110 \mu\text{m}$ for blue and yellow radiation (Figure 4b). The length (L) of experimental samples of the MMAS and the composite was 2.7 mm (inset in Figure 3).

Because the Rayleigh range $z_0 = \pi n \omega^2 / \lambda$ exceeded 10 cm, the calculation of $\Delta\alpha$ and Δn was performed using the formulae [40,41]:

$$\begin{cases} \Delta\alpha(I) = \frac{2\sqrt{2}\Delta T(I)}{L}, \\ \Delta n(I) = \gamma I = \frac{\lambda \Delta T_{pv}(I) \times (\alpha + \Delta\alpha(I))}{0.812\pi(1-S)^{0.27}(1-e^{-(\alpha+\Delta\alpha(I))L})}, \end{cases} \quad (1)$$

where $\Delta T(I)$ (Figure 4a) and $\Delta T_{pv}(I)$ (Figure 5b) were the integral transmitted intensity and the normalized


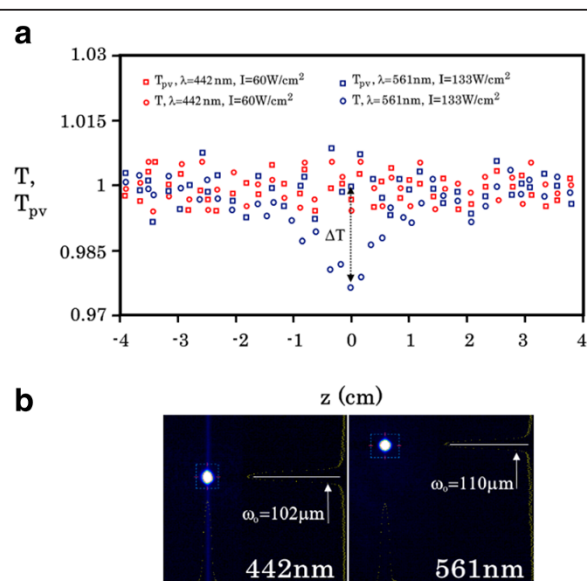


Figure 4 z-Scan results for the MMAS. (a) Curves for z-scans with open (circle) $T(I)$ and closed (square) $T_{pv}(I)$ apertures at radiation wavelengths of 442 nm (red points, $60 \text{ W}/\text{cm}^2$) and 561 nm (blue points, $133 \text{ W}/\text{cm}^2$) for the MMAS sample ($L = 2.7$ mm). (b) Profilometer images for the beam waists ω_0 .

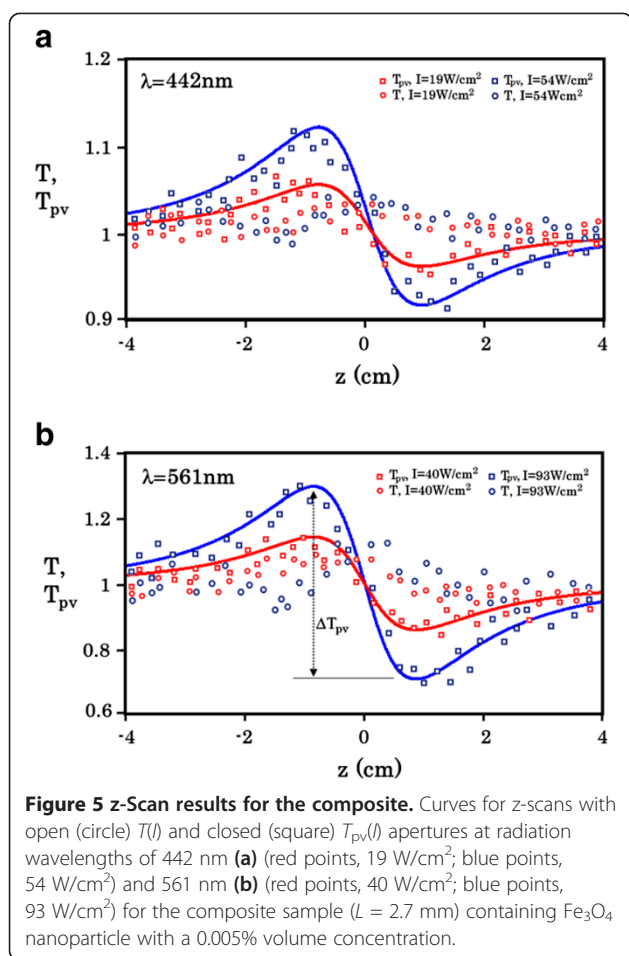

transmittance between the peak and valley at different radiation intensities, respectively; λ and α were the radiation wavelength and absorption coefficient (Figure 3), respectively, and S was the fraction of radiation transmitted by the aperture without the sample, which was 0.184.

The experimental curves $T(I)$ and $T_{pv}(I)$, which contain information about ΔT and ΔT_{pv} , showed that only the reverse saturable absorption of yellow radiation occurred in pure MMAS (Figure 4a). In contrast, the composite manifested the expected optical response: the shape of the experimental curves $T(I)$ and $T_{pv}(I)$ indicated the saturable absorption of visible radiation in the composite and a negative change in its refractive index (Figure 5), and the values of $\Delta T(I)$ and $\Delta T_{pv}(I)$ increased linearly with increasing intensities of blue (Figure 5a) and yellow (Figure 5b) radiation.

The approximation of T_{pv} based on the theoretical curves (solid lines in Figure 5) was performed using the equation [42]:


$$T = 1 + \frac{2(-\rho x^2 + 2x - 3\rho)}{(x^2 + 9)(x^2 + 1)} \Delta\Phi \quad (2)$$

where the coupling factor $\rho = \Delta\alpha \times \lambda / 4\pi \times \Delta n$ and the phase shift due to nonlinear refraction $\Delta\Phi = 2\pi \times \Delta n \times L_{\text{eff}} / \lambda$ had the following values: $\rho = 0.09$ and $\Delta\Phi = -0.23$ and -0.5 for blue radiation with intensities of 0.019 and 0.054 kW/cm² and $\rho = 0.05$ and $\Delta\Phi = -0.7$ and -1.45 for yellow radiation with intensities of 0.04 and 0.093 kW/cm².

Discussion

The saturable absorption of visible radiation with intensities less than 0.14 kW/cm² in the composite and the negative change in the refractive index were due to the presence of Fe₃O₄ nanoparticles since pure MMAS showed only the relatively weak reverse saturable absorption of yellow radiation. Therefore, the experimental data $\Delta T(I)$ and $\Delta T_{pv}(I)$ obtained for the composite could be used to calculate the values of $\Delta\alpha(I)$ and $\Delta n(I)$ for Fe₃O₄ nanoparticle arrays (Equation 1), and these values are listed in Figure 6.

Because the observed dependence of Δn on the radiation intensity I (Figure 6b) for Fe₃O₄ nanoparticle arrays could be considered a linear function, it can be

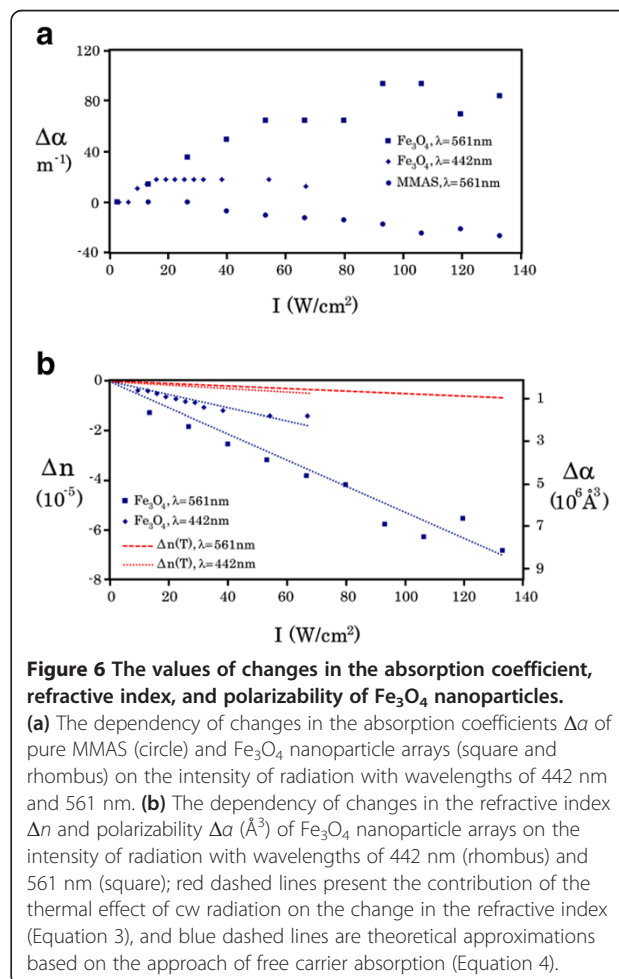

assumed that Δn was caused by the thermal effect of the radiation. We estimated the contribution of this effect to the changes of the composite refractive index using the equation [43]:

$$\Delta n_{\text{therm}} = \frac{\Delta E \times \frac{dn}{dT}}{c_{\text{hc}} \rho_d}, \quad (3)$$

where c_{hc} was the MMAS heat capacity (0.7 J/g·K), ρ_d was the MMAS density (1.3 g/cm³), dn/dT was the MMAS thermo-optic coefficient (-10^{-5} K⁻¹), and ΔE was the energy absorbed by the composite per unit volume per second. The thermal effect of cw low-intensity radiation on the change in the refractive index (red dashed lines in Figure 6b) was relatively small (not more than 20% for blue radiation and 8% for yellow radiation).

Generally, the possibility of a nonthermal optical response of the composite due to external optical radiation is associated with the polarization of Fe₃O₄ nanoparticles in the external field E . Nanoparticle polarization occurs at the spatial separation of positive and negative charges, i.e., at the electron transition to higher allowed energy states (quantum number $l \neq 0$). These transitions should be accompanied by the absorption of external radiation. In our case, we observed the absorption of radiation with wavelengths of 380 to 650 nm (Figure 3). This absorption band consisted of three maxima (380, 480, and 650 nm), indicating the broadened quantum-size states for the electrons in Fe₃O₄ nanoparticles. Because the bandgap of magnetite is rather small (approximately 0.2 eV) [20-22], the conduction and valence bands of the nanoparticles should be coupled due to quantum-size effect [44]. Therefore, the transitions of Fe₃O₄ nanoparticle electrons to higher energy states by the action of photons with energies of 2.3 eV ($\lambda = 561$ nm) and 2.6 eV ($\lambda = 442$ nm) can be considered intraband transitions. In turn, these transitions result in changes in the refractive index of the media as follows [45-47]:

$$\Delta n(I) = -\frac{e^2 \lambda^2}{8\pi^2 c^2 n_0 \epsilon_0 m_e} N_e \quad (4)$$

where e was the electron charge, c was the speed of light, ϵ_0 was the electric constant, m_e was the electron mass, and N_e was the concentration of excited electrons, which depends on the number of photons in the beam or the radiation intensity I .

Using Equation 4 to approximate the experimentally observed behavior of $\Delta n(I)$ (Figure 6b, blue dashed lines), we estimated that the concentration of optically excited electrons in Fe₃O₄ nanoparticles was approximately 10^{23} m⁻³, being the radiation intensity of less than 0.14 kW/cm².

The amplitude of the nanoparticle polarization is determined by $|E|$ of the external field and the nanoparticle susceptibility (χ) or polarizability (α) measured in cubic angstrom. In turn, the change in the refractive index induced by the radiation is associated with the change in nanoparticle polarizability $\Delta\alpha$ (Å³) by classical relations [48]. Therefore, we could calculate the values of $\Delta\alpha$ (Å³) for Fe₃O₄ nanoparticle using the experimental values of $\Delta n(I)$ and the following equations (SI):

$$\begin{cases} \epsilon = n^2(I) - k^2(I) = 1 + \chi \\ \Delta\chi = \Delta\alpha [\text{Å}^3] \cdot 10^{30} \cdot N [\text{m}^{-3}] \end{cases} \quad (5)$$

where ϵ was the real part of the dielectric constant, the composite refractive index $n(I) = n_0 + \Delta n(I)$, and n_0 was the refractive index of pure MMAS (approximately 1.5). The extinction coefficient $k = \alpha\lambda / 4\pi$ was significantly less than $n(I)$ and could be ignored; χ was the nanoparticle susceptibility, and N was the nanoparticle concentration (approximately 2.3×10^{19} m⁻³). Therefore, the values of $\Delta\alpha$ (Å³) for Fe₃O₄ nanoparticle were calculated using the formula $\Delta\alpha$ (Å³) $\approx 2n \times \Delta n(I) \times 10^{30} / N$ and are presented in Figure 6b.

The obtained values for the changes in nanoparticle polarizability are orders of magnitude greater than those for semiconductor nanoparticles and molecules [30,31] in extremely weak optical fields. In addition, the average nanoparticle volume was approximately 2.2×10^6 Å³, and the maximum value of $\Delta\alpha$ (Å³) was 9×10^6 Å³. Thus, we can conclude that the nanoparticle polarization should be formed by several optical intraband transitions of nanoparticle electrons in weak optical fields.

Conclusions

We used the developed co-precipitation method to synthesize spherical Fe₃O₄ nanoparticles covered with a monolayer of oleic acid that possessed a wide nonlinear absorption band of visible radiation 1.7 to 3.7 eV. The synthesized nanoparticles were dispersed in the optically transparent copolymer methyl methacrylate with styrene, and their optical properties were studied by optical spectroscopy and z-scan techniques. We report that the electric polarizability of Fe₃O₄ nanoparticles changes due to the effect of low-intensity visible radiation ($I \leq 0.2$ kW/cm²; $\lambda = 442$ and 561 nm) and reaches a relatively high value of 10^7 Å³. The change in polarizability is induced by the intraband phototransition of charge carriers and can be controlled by the intensity of the visible radiation used. This optical effect observed in magnetic nanoparticles may be employed to significantly improve the drug uptake properties of Fe₃O₄ nanoparticles.

Abbreviations

Abs: Absorbance; Cw: Continuous wave; MMAS: Methyl methacrylate with styrene.

Competing interests

The authors declare that they have no competing interests.

Authors' contributions

VM designed and performed the optical experiments (z-scan and spectroscopy), participated in the analysis and interpretation of data, and prepared the draft and final version of the manuscript. AN, VW, and VS designed and performed the chemical experiments, achieved that nanoparticle was covered with a monolayer of oleic acid, prepared the sections 'Synthesis of nanoparticle' and 'Composite preparation'. YK and VD conceived of the study, participated in the analysis and interpretation of data, helped to draft the final version of the manuscript. All the authors read and approved the final manuscript.

Acknowledgments

The work was supported by the Programs of Presidium of Russian Academy of Science (12-I-OFN-05, 12-I-P24-05, 12-II-UO-02-002) and by the Program of UB RAS (12-S-Z-1004).

Author details

¹Institute of Automation and Control Processes, FEB RAS, Radio 5, Vladivostok 690041, Russia. ²Far Eastern Federal University, Sukhanova 8, Vladivostok 690950, Russia. ³Institute of Technical Chemistry, UB RAS, Academician Korolyov 3, Perm 614013, Russia.

Received: 23 May 2013 Accepted: 1 July 2013

Published: 9 July 2013

References

- Gass J, Poddar P, Almand J, Srinath S, Srikanth H: Superparamagnetic polymer nanocomposites with uniform Fe₃O₄ nanoparticle dispersions. *Adv Funct Mater* 2006, **16**:71–75.
- Wan J, Tang G, Qian Y: Room temperature synthesis of single-crystal Fe₃O₄ nanoparticles with superparamagnetic property. *Appl Phys A* 2007, **86**:261–264.
- Mürbe J, Rechtenbach A, Töpfer J: Synthesis and physical characterization of magnetite nanoparticles for biomedical application. *Mater Chem Phys* 2008, **110**:426–433.
- Hashimoto H, Fujii T, Nakanishi M, Kusano Y, Ikeda Y, Takada J: Synthesis and magnetic properties of magnetite-silicate nanocomposites derived from iron oxide of bacterial origin. *Mater Chem Phys* 2012, **136**:1156–1161.
- Wang X, Zhao Z, Qu J, Wang Z, Qiu J: Fabrication and characterization of magnetic Fe₃O₄-CNT composites. *J Phys Chem Sol* 2010, **71**:673–676.
- Xie J, Chen K, Lee HY, Xu C, Hsu AR, Peng S, Chen X, Sun S: Ultrasmall c(RGDyK)-coated Fe₃O₄ nanoparticles and their specific targeting to integrin $\alpha_5\beta_1$ -rich tumor cells. *J Am Chem Soc* 2008, **130**:7542–7543.
- Mi C, Zhang J, Gao H, Wu X, Wang M, Wu Y, Di Y, Xu Z, Mao C, Xu S: Multifunctional nanocomposites of superparamagnetic (Fe₃O₄) and NIR-responsive rare earth-doped up-conversion fluorescent (NaYF₄:Yb, Er) nanoparticles and their applications in biolabeling and fluorescent imaging of cancer cells. *Nanoscale* 2010, **2**:1141–1148.
- Chen ZL, Sun Y, Huang P, Yang XX, Zhou XP: Studies on preparation of photosensitizer loaded magnetic silica nanoparticles and their anti-tumor effects for targeting photodynamic therapy. *Nanoscale Res Lett* 2009, **4**:400–408.
- Yang C, Wu J, Hou Y: Fe₃O₄ nanostructures: synthesis, growth mechanisms, properties and application. *Chem Commun* 2011, **47**:5130–5141.
- Wang X, Zhang R, Wu C, Dai Y, Song M, Gutmann S, Gao F, Lu G, Li J, Li X, Guan Z, Fu D, Chen B: The application of Fe₃O₄ nanoparticles in cancer research: a new strategy to inhibit drug resistance. *J Biomed Mater Res A* 2007, **80A**(4):852–860.
- Gong P, Li H, He X, Wang K, Hu J, Tan W, Zhang S, Yang X: Preparation and antibacterial activity of Fe₃O₄@Ag nanoparticles. *Nanotechnology* 2007, **18**:1–7. 285604.
- Liu X, Hu Q, Fang Z, Wu Q, Xie Q: Carboxyl enriched monodisperse porous Fe₃O₄ nanoparticles with extraordinary sustained-release property. *Langmuir Lett* 2009, **25**(13):7244–7248.
- Covaliu CI, Berger D, Matei C, Diamandescu L, Vasile E, Cristea C, Ionita V, Iovu H: Magnetic nanoparticles coated with polysaccharide polymers for potential biomedical applications. *J Nanopart Res* 2011, **13**:6169–6180.
- Wu KT, Kuo PC, Yao YD, Tsai EH: Magnetic and optical properties of Fe₃O₄ nanoparticle ferrofluids prepared by coprecipitation technique. *IEEE Trans Magn* 2001, **37**(4):2651–2653.
- Narsinga Rao G, Yao YD, Chen YL, Wu KT, Chen JW: Particle size and magnetic field-induced optical properties of magnetic fluid nanoparticles. *Phys Rev E* 2005, **72**:1–6.
- Liu T, Chen X, Di Z, Zhang J: Tunable magneto-optical wavelength filter of long-period fiber grating with magnetic fluids. *Appl Phys Lett* 2007, **91**:121116.
- Li J, Liu X, Lin Y, Bai L, Li Q, Chen X: Field modulation of light transmission through ferrofluid film. *Appl Phys Lett* 2007, **91**:1–3. 253108.
- Chieh JJ, Hong CY, Yang SY, Horng HE, Yang HC: Study on magnetic fluid optical fiber devices for optical logic operations by characteristics of superparamagnetic nanoparticles and magnetic fluids. *J Nanopart Res* 2010, **12**:293–300.
- Xia SH, Wang J, Lu ZX, Zhang F: Birefringence and magneto-optical properties in oleic acid coated Fe₃O₄ nanoparticles: application for optical switch. *Int J Nanoscience* 2011, **10**(3):515–520.
- Balberg I, Pankove JI: Optical measurements on magnetite single crystals. *Phys Rev Lett* 1971, **27**(9):596–599.
- Park JH, Tjeng LH, Allen JW, Metcalf P, Chen CT: Single-particle gap above the Verwey transition in Fe₃O₄. *Phys Rev B* 1997, **55**(19):813–817.
- Jordan K, Cazacu A, Manai G, Ceballos SF, Murphy S, Shvets IV: Scanning tunneling spectroscopy study of the electronic structure of Fe₃O₄ surface. *Phys Rev B* 2006, **74**:1–6. 085416.
- Buchenau U, Müller I: Optical properties of magnetite. *Solid State Commun* 1972, **11**:1291–1293.
- Muret P: Optical absorption in polycrystalline thin films of magnetite at room temperature. *Solid State Commun* 1974, **14**:1119–1122.
- Schlegel A, Alvarado SF, Wächter P: Optical properties of magnetite (Fe₃O₄). *J Phys C: Solid State Phys* 1979, **12**:1157–1164.
- Fontijn WFJ, van der Zaag PJ, Devillers MAC, Brabers VAM, Metselaar R: Optical and magneto-optical polar Kerr spectra of Fe₃O₄ and Mg²⁺- or Al³⁺-substituted Fe₃O₄. *Phys Rev B* 1997, **56**(9):5432–5442.
- Yasumori A, Matsumoto H, Hayashi S, Okada K: Magneto-optical properties of silica gel containing magnetite fine particles. *J Sol-gel Sci Tech* 2000, **18**:249–258.
- Barnakov YA, Scott BL, Golub V, Kelley L, Reddy V, Stokes KL: Spectral dependence of Faraday rotation in magnetite-polymer nanocomposites. *J Phys Chem Solids* 2004, **65**:1005–1010.
- Roychowdhury A, Pati SP, Mishra AK, Kumar S, Das D: Magnetically addressable fluorescent Fe₃O₄/ZnO nanocomposites: structural, optical and magnetization studies. *J Phys Chem Solids* 2013, **74**:811–818.
- Evlukhin AB, Reinhardt C, Seidel A, Lukyanchuk BS, Chichkov BN: Optical response features of Si-nanoparticle arrays. *Phys Rev B* 2010, **82**(4):1–12. 045404.
- Marenich AV, Cramer CJ, Truhlar DG: Reduced and quenched polarizabilities of interior atoms in molecules. *Chem Sci* 2013, **4**:2349–2356.
- Kang YS, Risbud S, Rabolt JF, Stroeve P: Synthesis and characterization of nanometer-size Fe₃O₄ and γ -Fe₂O₃ particles. *Chem Mater* 1996, **8**:2209–2211.
- Chen L, Yang WJ, Yang CZ: Preparation of nanoscale iron and Fe₃O₄ powders in a polymer matrix. *J Mater Sci* 1997, **32**:3571–3575.
- Long Y, Chen Z, Duvali JL, Zhang Z, Wan M: Electrical and magnetic properties of polyaniline/Fe₃O₄ nanostructures. *Physica B* 2005, **370**:121–130.
- Banert T, Peuker UA: Preparation of highly filled super-paramagnetic PMMA-magnetite nanocomposites using the solution method. *J Mater Sci* 2006, **41**:3051–3056.
- Li D, Jiang D, Chen M, Xie J, Wu Y, Dang S, Zhang J: An easy fabrication of monodisperse oleic acid-coated Fe₃O₄ nanoparticles. *Mater Lett* 2010, **64**:2462–2464.
- Gnanaprakash G, Mahadevan S, Jayakumar T, Kalyanasundaram P, Philip J, Raj B: Effect of initial pH and temperature of iron salt solutions on formation of magnetite nanoparticles. *Mater Chem Phys* 2007, **103**:168–175.
- Tural B, Özkan N, Volkan M: Preparation and characterization of polymer coated superparamagnetic magnetite nanoparticle agglomerates. *J Phys Chem Solids* 2009, **70**:860–866.
- Lan Q, Liu C, Yang F, Liu S, Xu J, Sun D: Synthesis of bilayer oleic acid-coated Fe₃O₄ nanoparticles and their application in pH-responsive Pickering emulsions. *J Coll Interf Sci* 2007, **310**:260–269.

40. Milichko VA, Dzyuba VP, Kulchin YN: **Unusual nonlinear optical properties of SiO₂ nanocomposite in weak optical fields.** *Appl Phys A* 2013, **11**(1):319–322.
41. Sheik-Bahae M, Said AA, Wei TH, Hagan DJ, Van Stryland EW: **Sensitive measurement of optical nonlinearities using a single beam.** *IEEE J Quantum Electron* 1990, **26**(4):760–769.
42. Liu X, Guo S, Wang H, Hou L: **Theoretical study on the closed-aperture Z-scan curves in the materials with nonlinear refraction and strong nonlinear absorption.** *Opt Commun* 2001, **197**:431–437.
43. Ganeev RA, Rysanyansky AI, Stepanov AL, Usmanov T: **Nonlinear optical response of silver and copper nanoparticles in the near-ultraviolet spectral range.** *Phys Sol State* 2004, **46**(2):351–356.
44. All E, Rosen M: **Quantum size level structure of narrow-gap semiconductor nanocrystals: effect of band coupling.** *Phys Rev B* 1998, **58**(11):7120–7135.
45. Bennett BR, Soref RA, Del Alamo J: **Carrier-induced change in refractive index of InP, GaAs, and InGaAsP.** *IEEE J Quantum Electron* 1990, **26**(1):113–122.
46. Veselago VG: **The electrodynamics of substances with simultaneously negative values of ϵ and μ .** *Physics-Uspokhi* 1968, **10**:509–514.
47. Yu ZG, Krishnamurthy S, Guha S: **Photoexcited-carrier-induced refractive index change in small bandgap semiconductors.** *J Opt Soc Am B* 2006, **23**(11):2356–2360.
48. Akhmanov A, Nikitin SY: *Physical Optics*. Oxford: Oxford University Press; 1997.

doi:10.1186/1556-276X-8-317

Cite this article as: Milichko et al.: Photo-induced electric polarizability of Fe₃O₄ nanoparticles in weak optical fields. *Nanoscale Research Letters* 2013 **8**:317.

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► springeropen.com
