

NANO EXPRESS

Open Access

Electrochemical characterization of TiO_2/WO_x nanotubes for photocatalytic application

Raman Vedarajan*, Shoto Ikeda and Noriyoshi Matsumi*

Abstract

TiO_2/WO_x nanotubes have unique photo-energy retention properties that have gathered scientific interest. Herein, we report the synthesis, morphological characterization, and the electrochemical characterization of TiO_2/WO_x nanotubes compared with pure TiO_2 nanotubes, prepared by anodization technique. Significant structural differences were not observed in TiO_2/WO_x nanotubes as observed by using scanning electron microscopy and transmission electron microscopy. The charge transfer resistance of TiO_2/WO_x before and after photo irradiation determined by using electrochemical impedance spectroscopy proves the inherent energy retention property which was not observed in pure TiO_2 nanotubes.

Keywords: TiO_2/WO_x nanotubes; Photoelectrochemical water splitting; Photocatalytic application

Background

Solar energy is clean, safe, and limitless; hence, tapping solar energy would be beneficial at global scale. In order to realize a solar-driven energy conversion device, semi-conducting materials are required that absorb sunlight and accomplish an unhindered electron injection from valence band to conduction band, enabling performance of electric work in the circuit. Photoelectrochemical (PEC) water splitting to generate hydrogen for its use as fuel is considered to be a feasible alternative and sustainable energy system. Ideal materials for photoelectrochemical water splitting are semiconductors, which Fujishima and Honda first demonstrated using TiO_2 . As a result, this field of research has gathered significant attention by the research fraternity to achieve a highly efficient system producing hydrogen and oxygen by splitting up of water using most of the solar spectrum supplemented by a little or no electrical energy. Metal oxides, in particular, TiO_2 and WO_3 , possess congenial electronic structure leading to good photoactivity and chemical stability. Further, their low cost and availability in abundance make them the chosen material for photoanodic reactions in aqueous electrolytes [1]. TiO_2 has been a material extensively studied for water photooxidation [2]. More recently, TiO_2 nanotubes (TNT) have

gained much attention due to its simple synthesis [3] and enhanced photoelectrochemical performance over its nanoparticle counterpart. Despite the improved performance of TiO_2 nanotubes, enhancing the visible light activity as well as reducing the charge recombination losses is required to increase water-splitting efficiency if practical applications are to be realized. On the other hand, tungsten trioxide (WO_3) is a visible light photoactive material [4] with a bandgap of approximately 2.7 eV. Although it is a promising material by itself, coupling it with TiO_2 has shown to be beneficial in many applications [5]. The formation of heterojunctions of two semiconductors is an appealing method to increase visible light activity while maintaining the properties of each component. Moreover, the incorporation of WO_3 is, in particular, ambient due to the nearly similar ionic radius of W^{+6} to that of Ti^{4+} . As a result of which WO_3 can be easily coupled into the TiO_2 lattice during anodization process. Titania nanotubes incorporated with tungsten oxide have been reported to possess enhanced optical and electronic properties compared to its pure form [6-14]. Further, this mixed oxide composite nanotube shows a unique photon energy retention feature, i.e., the photon to electrical energy conversion process does not cease immediately after curbing the photon influx but stops gradually. This feature in $\text{TiO}_2 + \text{WO}_x$ nanotubes has not been studied in depth. Investigations angled from the energy retention viewpoint of this metal

* Correspondence: raman@jaist.ac.jp; matsumi@jaist.ac.jp
Department of Materials Science, Japan Advanced Institute of Science and Technology, 1-1Asahidai, Nomi, Ishikawa 923-1292, Japan

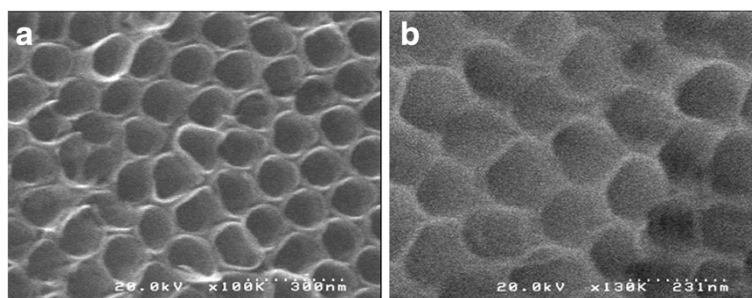


Figure 1 SEM image of TiO_2 and TiO_2/WO_x nanotubes. (a) SEM image of TiO_2 nanotubes (b) SEM image of TiO_2/WO_x nanotubes.

oxide composite and its effect over dye-sensitized solar cell and photoelectrochemical water splitting was conceptualized in this endeavor.

Hence, in this present work, we have attempted to employ electrochemical impedance spectroscopy in evaluating TiO_2/WO_x nanotubes as a candidate material for water splitting. The TiO_2/WO_3 nanotubular composite was prepared through a single-step anodization of titanium in an aqueous bath of NH_4F and $\text{H}_3\text{PW}_{12}\text{O}_{40}$ (phosphotungstic acid (PTA)). The morphology of the nanotubes was characterized using scanning electron microscopy (SEM), transmission electron microscopy (TEM), and energy dispersive X-ray (EDX) analysis. The nanotubes were tested for its charge transfer resistance in an electrolyte at pH approximately 6 under air mass (AM) 1.5 simulated solar irradiation. A time-oriented electrochemical impedance spectroscopy was carried out to assess the charge retention property of the mixed oxide nanotube and was compared with its pure counterpart.

Methods

Synthesis of TiO_2/WO_x nanotubes

Synthesis of TiO_2 nanotubes and TiO_2/WO_x was carried out similar to previously reported procedure. In short, cleaned, polished titanium metal strips were anodized at DC voltage of 50 V for two and a half hour in an aqueous solution containing 0.5 wt.% NH_4F for TNT synthesis and 0.5 wt.% NH_4F with 2.4 wt.% PTA (Kanto Chemicals, Tokyo, Japan) for TNT- WO_x synthesis. Preliminary studies indicated an amount of 2.4 wt.% of PTA to be the optimal loading [6].

Characterization of TNT and TNT/ WO_x

Firstly, the synthesized TiO_2 and TiO_2/WO_x nanotubes were characterized by using scanning electron microscope (SEM; Hitachi Model H-4600, Tokyo, Japan) and transmission electron microscope (TEM; Hitachi Model H-7100, Tokyo, Japan) for its morphology. Secondly, the elemental analysis was carried out using energy dispersive X-ray (EDX; Horiba, Kyoto, Japan) analysis. Finally, the electrochemical experiments were carried out in a

conventional three-electrode setup in which the TiO_2 or TiO_2/WO_x served as the photoanode, Pt as the cathode, and Ag/AgCl as the reference electrode. The electrolyte used was 0.1 M NaOH (Kanto chemicals, Tokyo, Japan). A computer-controlled potentiostat coupled with a frequency response analyzer was used to control the potential and record the electrochemical impedance spectra (VersaStat-3, Princeton Applied Research, Oak Ridge, TN, USA). The photoanodes were illuminated by a 300 W solar simulator with an AM 1.5 at one sun intensity (Peccell Technologies, Inc., Yokohama, Japan) (approximately $87 \text{ mW}/\text{cm}^2$).

Results and discussion

Morphological and elemental analysis

Scanning electron micrographs of TiO_2 and TiO_2/WO_x nanotubes showed that the morphology of both types were similar (Figure 1a,b). The honeycomb-like arrangement of


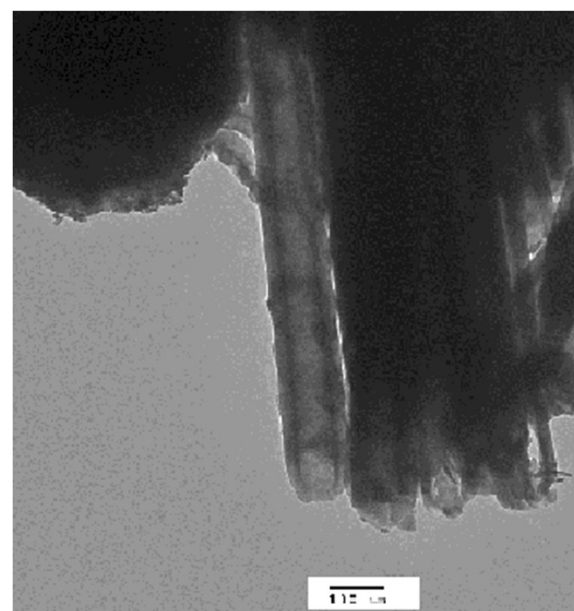


Figure 2 TEM image of TiO_2/WO_x nanotubes.

the nanotubes remained unaffected by the presence of PTA during the anodization of Ti for the formation of TiO_2/WO_x . The pores were well formed and appeared uniformly circular. In both, the pure TiO_2 nanotubes and one with WO_x , the pore size was found to be in a range of 90 to 120 nm. Further, the same was confirmed from transmission electron micrographs (Figure 2). Also, in the case of the TEM micrographs, the samples anodized in the presence of PTA showed intermittent dark spots which can be attributed to the presence of a heavier element compared to Ti indicating the incorporation of WO_x . Energy dispersive X-ray analysis was carried out to determine the elemental composition of the nanotubes and to confirm the incorporation of the W in the nanotubes. Peaks at around 2.5 eV and at 9 eV confirmed the presence of W. WO_x being the most stable form of W in an oxidizing medium, such as the one used in this study, and the presence of W can be ascribed to WO_x .


Electrochemical characterization



A Nyquist plot at open-circuit potential condition of TiO_2/WO_x and TiO_2 in 0.1 M NaOH under AM 1.5 solar-simulated irradiation is given in Figure 3a,b. The

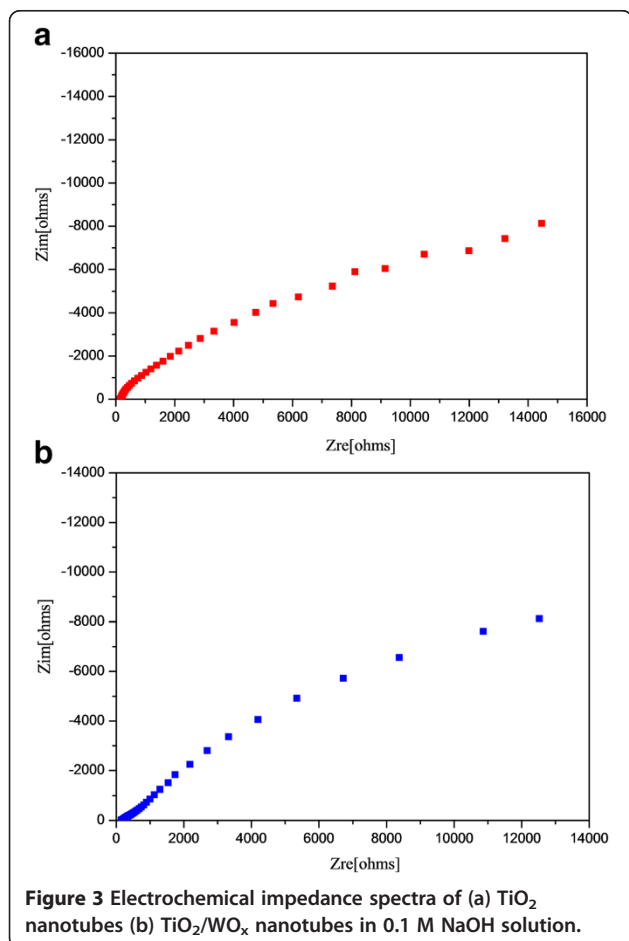

nonlinear regression fitting using a conventional Randle's circuit (R(QR)); routine gave R_{ct} values of 1.48×10^4 and $6.22 \times 10^4 \Omega$ for TiO_2/WO_x nanotubes and TiO_2 nanotubes, respectively. A lower charge transfer resistance is indicative of recombination suppression by improved charge transport to the electrolyte. The improvement of the TiO_2/WO_x system over TiO_2 could be due to the formation of localized TiO_2/WO_x heterojunctions or through the formation of W^{6+} surface states which act as mediators for charge transfer to the electrolyte.

In order to determine the photovoltage of the semiconductor material, the open-circuit potential (V_{oc}) of TiO_2/WO_x electrodes were determined under photoirradiated condition as well as dark by constructing a conventional dye-sensitized solar cell in a sandwich-type configuration. The dye employed for this study was a commercially available N719 dye. As depicted in Figure 4, the photovoltage increased steeply with photoirradiation to a value of 0.73 V and later steadied at 0.71 V. However, on cutting photon influx by switching off the light source, the photovoltage initially dropped drastically to a value of 0.093 V. This was followed by an anomalous trend in the photovoltage, wherein the voltage showed an increasing trend for a few seconds and reached a plateau at 0.12 V and stayed at this potential for approximately 100 s before starting to fall continuously to 0 V. This behavior in TiO_2/WO_x dye-sensitized electrode provoked further analysis to validate this behavior for other photocatalytic activity. Hence, a time-oriented electrochemical impedance spectroscopy was carried for both, the pure TiO_2 nanotube electrode as well as the TiO_2/WO_x nanotube electrode. The impedance measurements were carried out before the photoirradiation and at regular intervals for 12 h after photoirradiating the electrodes for 15 min under one sun condition. The results of the impedance measurements are presented in Figure 5a,b. All spectra were fitted with

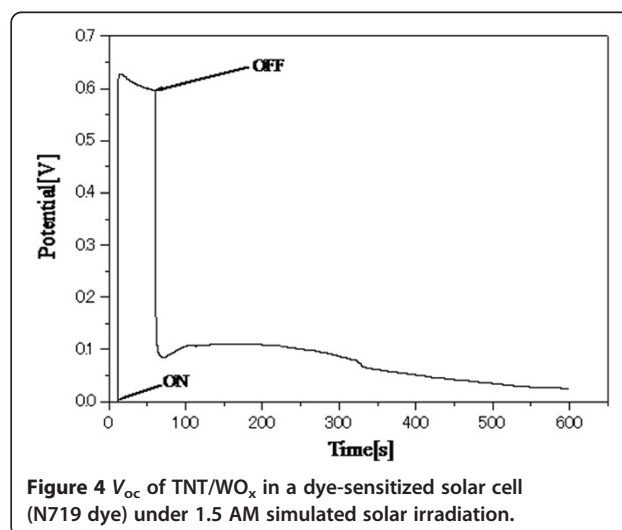

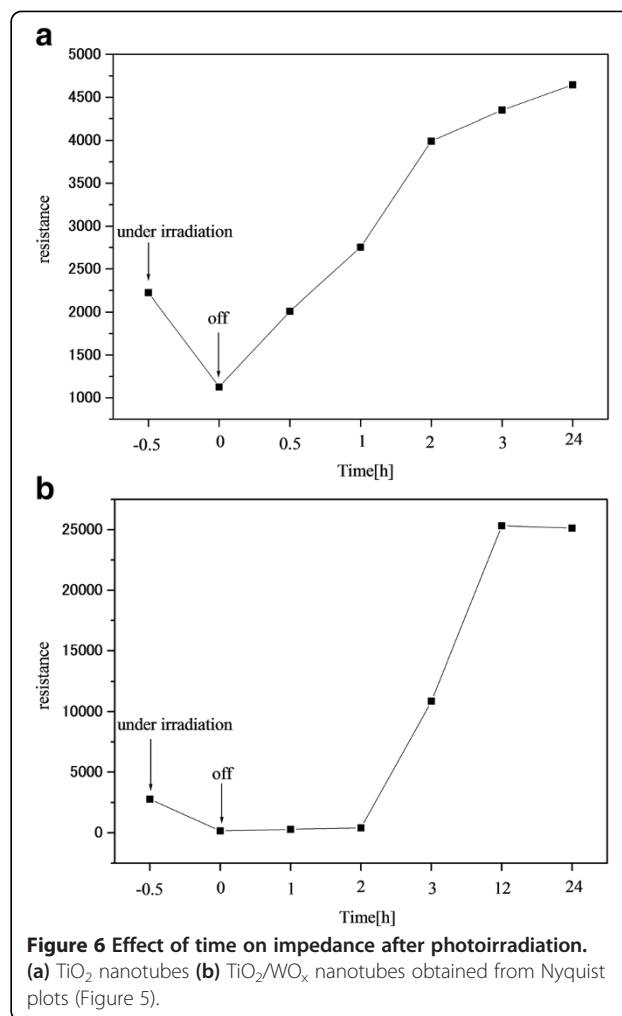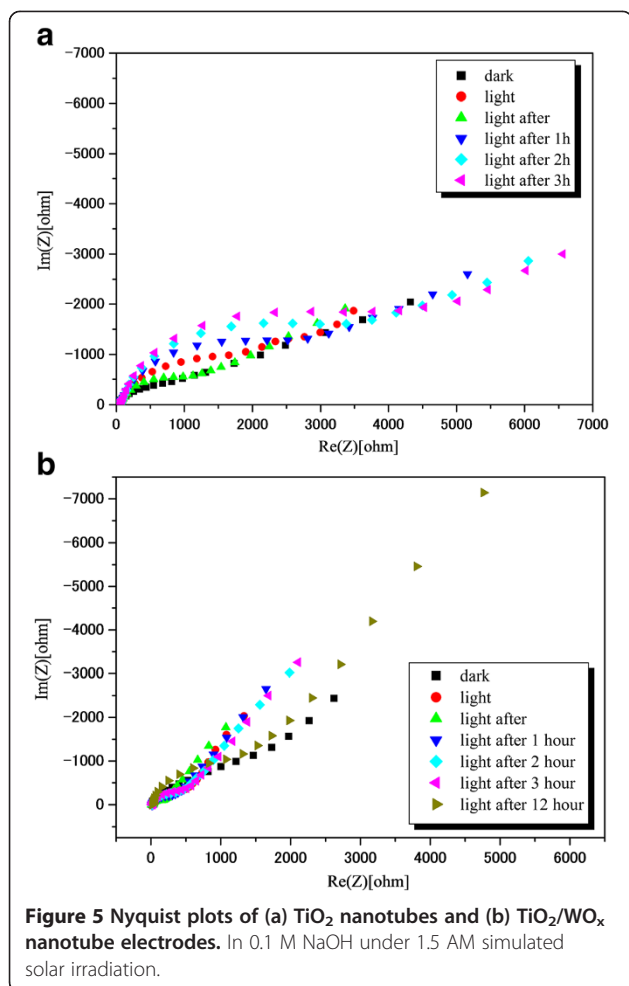

appropriate equivalent circuits. Although complicated systems like the present one are fitted with transmission-type circuits, in order to understand the overall impedance behavior of the material, the simpler Randle's circuit (R(QR)) or the modified Randle's circuit (R(Q(RW))) with diffusion parameter was used. However, the charge transfer resistance of the material will remain unaffected. All the charge transfer resistances are plotted against time as shown in Figure 6. Both the TiO_2 nanotubes as well as the TiO_2/WO_x electrodes exhibited decreased charge transfer resistance immediately after irradiation compared to the charge transfer resistance during irradiation. This can be attributed to the time lag involved in the excitation of the electron in to the conduction band, subsequent charge transfer from the electrolyte and the impedance measurement equilibrating time period. However, considering the constant error involved for both the systems, more significant observations were that the charge transfer resistance increased sharply under dark condition and attained a maximum within 3 h of curbing the photon influx in the case of the TiO_2 nanotubes. On the other hand, in the case

of TiO_2/WO_x nanotubes, the increase in charge transfer resistance after cutoff of photoirradiation was not evident and the resistance remained unchanged at a very low value for a period of 3 h before showing an increasing trend. Further, the maximum resistance value was not attained before 12 h after curbing the photoirradiation. This phenomenon in the mixed oxide nanotube electrode can be attributed to the retention of energy by WO_x during high photon influx and releasing it during photon starvation condition. This attribute of TiO_2/WO_x nanotubes could find potential application in photoelectrochemical water splitting.

Conclusions

The morphological and elemental analyses were carried out by scanning electron microscopy and transmission electron microscopy. No significant structural difference was observed in TiO_2/WO_x nanotubes compared to TiO_2 nanotubes revealing honeycomb structure. Electrochemical impedance spectroscopy exhibited a high photoactivity

from TiO₂/WO_x nanotubes compared to TiO₂ nanotubes. A time-dependent impedance analysis evinced the charge retention property of the mixed oxide, indicating its possible use in many photocatalytic applications.

Competing interests

The authors declare that they have no competing interests.

Authors' contributions

RV carried out the morphological studies, helped MO in performing electrochemical studies, and drafted the manuscript. SI carried out the electrochemical studies. NM conceived the study and helped to draft the manuscript. All authors read and approved the final manuscript.

Received: 21 July 2014 Accepted: 2 October 2014

Published: 14 October 2014

References

1. Reyes-Gil KR, David BR: Comparison between the quantum yields of compact and porous WO₃ photoanodes. *J Amer Chem Soc* 2013, **5**:12400–12410.
2. Rajeshwar K, Singh P, DuBow J: Energy conversion in photoelectrochemical systems —a review. *Electrochim Acta* 1978, **23**:1117.
3. Gong D, Grimes CA, Varghese OK, Hu W, Singh RS, Chen Z, Dickey EC: Titanium oxide nanotube arrays prepared by anodic oxidation. *J Mat Res* 2001, **16**:3331–3334.
4. Li L, Krissanasaeranee M, Pattinson SW, Stefik M, Wiesner U, Steiner U, Eder D: Enhanced photocatalytic properties in well-ordered mesoporous WO₃. *Chem Comm* 2010, **46**:7620.
5. Li Q, Kako T, Ye J: WO₃ modified titanate network film: highly efficient photo-mineralization of 2-propanol under visible light irradiation. *Chem Comm* 2010, **46**:5352–5354.
6. Smith YR, Sarma B, Mohanty SK, Misra M: Formation of TiO₂-WO₃ nanotubular composite via single-step anodization and its application in photoelectrochemical hydrogen generation. *Electrochem Comm* 2012, **19**:131–134.
7. Lai CW, Sreekantan S: Discovery of WO₃/TiO₂ nanostructure transformation by controlling content of NH₄F to enhance photoelectrochemical response. *Adv Mat Res* 2012, **620**:173.
8. Lai CW, Sreekantan S: Effect of heat treatment on WO₃-loaded TiO₂ nanotubes for hydrogen generation via enhanced water splitting. *Mat Sci Semicond Proc* 2013, **16**:947.
9. Lai CW, Sreekantan S: Preparation of hybrid WO₃-TiO₂ nanotube photoelectrodes using anodization and wet impregnation: improved water-splitting hydrogen generation performance. *Int J Hyd Energy* 2013, **38**:2156.
10. Lai CW, Sreekantan S: Study of WO₃ incorporated C-TiO₂ nanotubes for efficient visible light driven water splitting performance. *J Alloys Comp* 2013, **547**:43.
11. Lai CW, Sreekantan S: Photoelectrochemical response studies of W deposited TiO₂ nanotubes via thermal evaporation technique. *J Expt Nano Sci* 2014, **9**:728.
12. Lai CW, Sreekantan S: Visible light photoelectrochemical performance of W-loaded TiO₂ nanotube arrays: structural properties. *J Nanosci Nanotech* 2012, **12**:3170.
13. Paramasivam I, Nah Y, Das C, Shrestha NK, Schmuki P: WO₃/TiO₂ nanotubes with strongly enhanced photocatalytic activity. *Chem-Eur J* 2010, **16**:8993.
14. Nah YC, Ghicov A, Kim D, Berger S, Schmuki P: TiO₂-WO₃ composite nanotubes by alloy anodization: growth and enhanced electrochromic properties. *J Am Chem Soc* 2008, **130**:16154.

doi:10.1186/1556-276X-9-573

Cite this article as: Vedarajan et al.: Electrochemical characterization of TiO₂/WO_x nanotubes for photocatalytic application. *Nanoscale Research Letters* 2014 **9**:573.

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► springeropen.com