

REVIEW

Open Access



Sustainable approaches for the synthesis of biogenic platinum nanoparticles

Ulka Malode¹, Yamini S. Patil², Yajurved Narhari Selokar³, Pratima R. Yadav³, Rupali Patil Bhagat⁴, Vibha M. Nikose⁵, Rakesh U. Thakare^{6*} and Seema Nimbar^{7*}

Abstract

Background The era of nanotechnology become widespread for research and human resource development due to its functionalized tuning with economical, eco-friendly, effective and sustainable end-products. Hence, the present review illustrates the biogenic fabrication of platinum nanoparticles (PtNPs) through the different sustainable and cheaper approaches.

Main body of the abstract Over the physicochemical-based nanotechnology, the biogenic active substances-based synthesis displayed the more promising candidature due to its non-toxic, Broad-spectrum applicability and defendable type character. The biogenic synthesis method is capable with and without capping and highly motif of reducing agents. The morphology and stability of synthesized PtNPs are mostly mediated by various experimental conditions such as pH, temperature, incubation time, concentrations of biomaterials and salts or enzymes used. Hence, the review is aiming to discuss the methodology of biogenic synthesis of PtNPs by plant stem, root, leaf, flower, fruit, extracts, algae, fungi and egg yolk. Also, we have illustrated the pharmaceutical drug model application and its adverse effect.

Short conclusion Synthesized PtNPs are open a new trend in catalyst, drug and its carrier and in cancer treatment. PtNPs are utilized as a new therapeutic agent for inhibiting the microbial pathogens with non-toxic behavior. The characterization of PtNPs could estimate the bio-sensitized properties which leads the commercial applications.

Keywords PtNPs, Biogenic synthesis, Toxicity, Bioactive product, Pharmaceutical applications

*Correspondence:

Rakesh U. Thakare
rakeshthakare1983@gmail.com
Seema Nimbar
nimbartes@rediffmail.com

¹ Bajaj College of Science Autonomous Wardha, Wardha, Maharashtra 442001, India

² Shri Dnyaneshwar Maskuji Burungale Science and Arts College, Shegaon, Maharashtra 442003, India

³ Post Graduation Teaching Department of Microbiology, Rashtrasant Tukadoji Maharaj Nagpur University, Nagpur 440033, India

⁴ Department of Zoology, Shri Shivaji Science College, Congress Nagar, Nagpur 440012, India

⁵ Dr. R.G. Bhoyar Arts, Commerce and Science College Seloo, Wardha 442104, India

⁶ Department of Microbiology, Y. C. College Lakhandur, Bhandara, Maharashtra 441803, India

⁷ Sevadal Mahila Mahavidyalaya Nagpur, Nagpur, Maharashtra 440024, India

Background

Nanomaterials influence and cover the multivariate areas like catalytical, electrical, mechanical, photo-electrical, medicinal, paint, chemical application, food industry, etc., due to their surface property, material combination, size variants, electron configuration, surface area to volume ratio, energy variation, etc. (Sana et al. 2020; Singh et al. 2023). Among it, the interest in Platinum nanoparticles (PtNPs) is its unique structural, optical and catalytic properties that make it expeditious and a promising catalyst endowed with biomedical properties (Yerpude et al. 2023).

Platinum (Pt), a priceless transition metal which has exceptional results likes, electrical and catalytic unique features and superior resistance corrosion mechanisms have been commonly applied in atomic, pharmaceutical,

petrochemical, electronica and energy sector. Platinum component, as well as its Alloys have distinctive potential in dehydrogenation hydrogenation and limited oxidation catalysis, of a range of significant molecules, extremely important in several industrial processes. The different crystal surfaces of Pt may have substantially different atomic arrangements and electronic structures which lead to dramatically different response toward same reaction (Zhou et al. 2009). Pt, in a particular concentration, nanoparticles may behave as antioxidants (Zhang et al. 2010). Products that had properties like multiple anticancer activities, are being sought recently. Some studies suggested that the usage of nanoparticles in anticancer treatments produces a synergistic impact, very significant, decreases the possibility of side effects and affects patients increase in long-term prognosis (Manthe et al. 2010). The PtNPs however have a detrimental impact on cancer cells. Because of this, researchers have partly abandoned studies on the use of platinum as anticancer agent (Gu et al. 2019; Wang et al. 2022).

There are different kinds of methods like physical and chemical are employed to the synthesis of PtNPs preparation; however, eco-friendly approach is the promising approach and in now day's interest is due to the toxic behavior of nanoparticles (Agarwal et al. 2019).

Biological methods can reduce the toxic effect of the particle. Biological processes are well known to have a good efficiency for generating spherical morphology, compact size and stable chemical nanoparticles (Jeyaraj et al. 2019; Gholami-Shabani et al. 2023). The plants and biological lichens are used as an option for the formulation of nanomaterials rather than dangerous chemicals by researchers because they are non-toxic, inexpensive and easily available. The plant's phytochemicals play a significant part in the production of nano-pharmaceuticals (Sana et al. 2021; Singh et al. 2022). Unlike other inorganic nanoparticles, bioactive molecules in plants help produce PtNPs. In addition, the organic PtNPs are competing with chemically synthesized nanoparticles in order to ensure adequate shape and size that the regulated reaction conditions provide better stability and it is right time to unveil the use of PtNPs as nanomedicine for vegetables. Nanoparticles synthesis for microorganisms, plants or its extracts and enzymes, proposed as possible environmentally friendly alternatives to physicochemical methods, systematic paradigm shown in Fig. 1 (Song et al. 2010; Singh et al. 2020; Muñoz-Diaz et al. 2022). Green-biogenic approaches of preparation of the platinum particle is the major aspects of this review. The current progress in biogenesis of PtNPs have been mentioned in the Table 1.

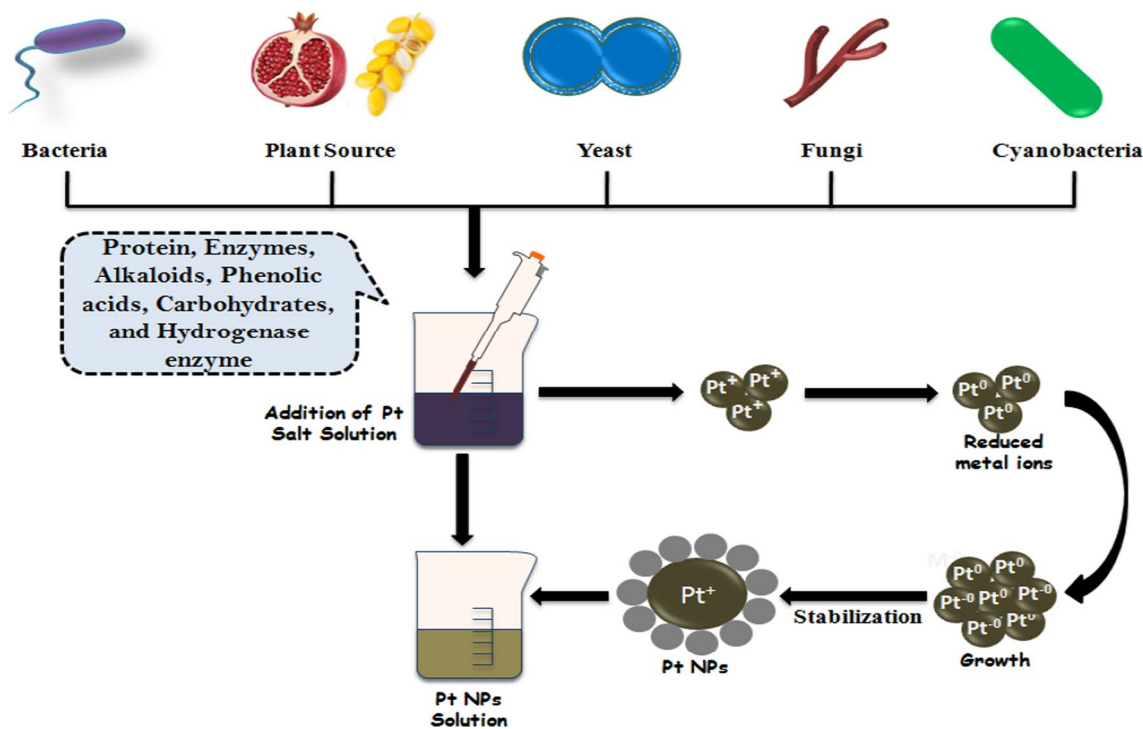


Fig. 1 A general process for the nanoparticle synthesis for algae, fungi, bacteria and Enzymes

Table 1 Biogenesis of PtNPs by various types of biomaterials

S. No.	Plant	Part used	Size (nm)	Shape	References
1.	<i>Azadirachta indica</i>	Leaves	5–50	Small and large spheres	Thirumurugan et al. (2016)
2.	<i>Phoenix dactylifera</i>	Fruit	1.3–2.6	Spherical	Sadalage et al. (2022)
3.	<i>Lantana camara</i>	Leaf	35	Spherical	Latif et al. (2019)
4.	<i>Prunus x yedoensis</i>	Gum	10–20	Circular	Guleria et al. (2022)
5.	<i>Camellia sinensis</i>	Leaf	30–60	Flower	Göl et al. (2020)
6.	<i>Antigonon leptopus</i>	Whole plant	5–190	Spherical	Ganaie et al. (2018)
7.	<i>Barleria prionitis</i>	Leaf	1–2	Spherical	Rokade et al. (2017)
8.	<i>B. prionitis</i>	Leaf	1–2	Monodispersed	Rokade et al. (2017)
9.	<i>Ocimum sanctum</i>	Leaves	23	Irregular	Soundarrajan et al. (2012)
10.	<i>Pinus resinosa</i>	Bark	6–8	Irregular	Jeyaraj et al. (2019)
11.	<i>Cacumen platycladi</i>	Whole biomass	2.4 ± 0.8	Spherical	Zheng et al. (2013)
12.	<i>Anacardium occidentale</i>	Leaf		Irregular and rod shaped	Sheny et al. (2013)
13.	<i>Diospyros kaki</i>	Leaf	2–20	Spheres and plates	Song et al. (2010)
14.	<i>Fumariae herba</i>	Whole herb	30	Hexagonal and pentagonal	Dobrucka (2015)
15.	<i>Punica granatum</i>	Peel	16–23	Spherical	Jha et al. (2018)
16.	<i>Piper betle L</i>	Leaf	2.1 ± 0.4	Spherical	Rajasekharreddy and Rani (2014)
17.	<i>Dioscorea bulbifera</i>	Tuber	2–5	Spherical	Ghosh et al. (2015)
18.	<i>Gloriosa superb</i>	Tuber	0.83–3	Spherical	Rokade et al. (2018)
19.	<i>Eichhornia crassipes</i>	Leaf	3.74	Spherical	Oluwafemi et al. (2016)
20.	<i>Quercus glauca</i>	Leaf	5–15	Spherical	Karthik et al. (2016)
21.	<i>Bacopa Monnieri</i>	Leaf	5–20	Spherical	Nellore et al. (2013)
22.	<i>Cochlospermum gossypium</i>	Tree Gum	2.4	Spherical	Vinod et al. (2011)
<i>Bacteria</i>					
1.	<i>Acinetobacter calcoaceticus</i>	Intracellular	2–3.5	Cuboidal	Gaidhani et al. (2014)
2.	<i>Saccharomyces boulardii</i>	Intracellular	80–150		Borse et al. (2015)
3.	<i>Plectonema boryanum</i> UTEX 485	Cell extract	< 300	Spherical	Brayner et al. (2007)
4.	<i>Calothrix cyanobacteria</i>	Intracellular and extracellular	3.2		Jeyaraj et al. (2019)
5.	<i>Acetobacter xylinum</i>	bacterial cellulose (BC) matrix	6.3–9.3	Granulated	Aritonang et al. (2014)
6.	<i>Escherichia coli</i> MC4100	Cells biomass	2.3 ± 0.7	Spherical	Attard et al. (2012)
<i>Fungi</i>					
1.	<i>F. oxysporum</i>	Extracellular	10–50	triangle, hexagons, square, rectangles	Riddin et al. (2006)
2.	<i>Neurospora Crassa</i>	Intracellular	2–3, 4–35, 7–76 and 20–110	Quasi spherical, single crystalline and round nano-aggregates	Castro-Longoria et al. (2012)
3.	<i>Cordyceps sp.</i>	Whole fruiting body	13.34 ± 4.06 nm	spherical	Liu et al. (2022)
<i>Algae</i>					
1.	<i>Padina gymnospora</i>	–	25	Octahedral	Ramkumar et al. (2017)
2.	<i>Plectonemaboryanum</i> UTEX 485	Cell extract	< 300	Spherical	Lengke et al. (2006)
3.	<i>Halymenia dilatata</i>	Aqueous cell extract	15 ± 1.7	spherical	Sathiyaraj et al. (2021)

Main text

Phytochemicals approaches for green synthesis of PtNPs

Plant biomolecules-based synthesis has increased quality attention of the researcher for the synthesis of PtNPs. It is due to the seamless advantage cheaper, simple, speedy, facile, green, non-toxic and efficient. Moreover, the required form, shape and size can be generated easily by altering the parameters such as reducing agent, time, temperature and pH (Naseer et al. 2020). Plants are the richest sources of potential and novel biomolecules which make it a perfect candidate in nanotechnology application (Rawat et al. 2020; Li et al. 2022; Wu et al. 2023). Moreover, phytochemical-based PtNPs are in need to be discovered for multivariate uses and hence a critical review needs to be done for the green synthesis of PtNPs. Remarkable studies of the synthesis of *Ocimum sanctum* (Tulsi) leaf extract mediated PtNPs synthesis was reported by Fahmy et al. (2020) which was accomplished at 100 °C for 1 h. Moreover, a successful PtNPs was achieved at room temperature by continuous stirring for 20 min. of the plant extract to Pt(IV) ions with the ratio of 1:9 (Fahmy et al. (2020). Similarly, Nellore et al. (2013) had reported the PtNPs by the interaction of leaf extract of *Bacopa monnieri* and Pt(IV) ions at room temperature, though the ratio was 1:4. Song et al. (2010) have described the *Diospyros kaki* (Persimmon) leaf extract-based green synthesis of PtNPs and achieved the >90% of Pt(IV) ions reduction into PtNPs at 95 °C for 2–3 h. At same temperature (95 °C) Shen et al. (2013) have synthesized the PtNPs by mixing the leaf powder of *Anacardium occidentale* with Pt(IV) ions.

Antimicrobial potential of green PtNPs

For PtNPs synthesis *Taraxacum laevigatum* was used to improve the bio-activity of nanoparticles. The resonance peak of the surface plasmon was seen the structure of platinum nanoparticles clearly represents 283 nm. The findings show that the genomics-synthesized particles were compatible, small and spherical in shape, dispersed (Tahir et al. 2017). These nanoparticles have been tested for the inhibition of 'gram positive' bacteria and 'gram-negative' bacteria (as *Pseudomonas aeruginosa* and *Bacillus subtilis*). The findings showed that 15 ± 0.5 mm and 18 ± 0.8 mm zone of inhibition were formed by PtNPs for *P. aeruginosa* and *B. subtilis*, respectively. The relevant consequence of this study is based on the strongest antibacterial activity of PtNPs against the multidrug resistant pathogenic bacterium *P. aeruginosa* and *B. subtilis*. It revealed the wide application of PtNPs as a good antibiotic against antibiotic defense mechanism (Hosny et al. 2022). The plant's phytochemicals play a significant role in the NPs synthesis. Organic water-soluble moieties of plants not only used to reduce but also stabilize the

nanoparticles that prepared (Kharisov et al. 2014). The latest findings show that the extract of plants is more useful for metal NPs preparation over the conventional approaches because of its consistent particles with high bio-molecular concentrations, e.g., flavonoids, terpenoids, tannins, phenols, alkaloids, quinines, etc. These were accountable for metal nanoparticles reduction and stabilization (Botha et al. 2019; Gour and Jain 2019). The plant-based PtNPs have been manufactured from *Azadirachta indica* (Thirumurugan et al. 2016), *Antigonon leptopus* (Selvi et al. 2020), Orange Peel extract (Karim et al. 2019) and Ajwa and Bardni dates (Aygün et al. 2020), which are used to decrease, cap and stabilize the plant growth and inhibits the phytopathogens. These synthesis are basically depending on the polyphenol mediated reduction of Pt ions which is present in the plant leaf, fruits or peel extract (Kumar et al. 2013).

Smaller and spherical nanoparticles are more successful for antimicrobial activity than the uneven formed NPs (Raza et al. 2016). Metal nanoparticles have been suggested to inhibit various mechanisms for bacteria. Prior studies indicate that released nano-particular metals within pathogenic bacteria creates OH• and O₂-• superoxide radicals. If these reactive species are more than bacterial cell scavenging capacity, causes damage to the cell (Dahiya et al. 2013). High PtNPs activity can be directly accredited to its smallest size and the uniform distribution. Current research effort reveals that the PtNPs could be an environmentally friendly, more economical solution and active antibacterial agent for bacterial pathogen inactivation (Ye et al. 2022).

Clinical potentials of green PtNPs

Developing an economically viable and environmentally friendly technique for the production of NPs is also important in the Nanobiotechnology branch. Biological synthetic method of novel PtNPs have been investigated through *neem* extract in the present study and characterized (Thirumurugan et al. 2016). A green bio-synthetic path to PtNPs synthesis with *Xanthium strumarium* extract leaf is pointed out. The synthetic methodology is very straight forward and one step rather than using a capping and removal agent. The nanoparticles also have potent cytotoxic effect on HeLa, the cancer cell lines with an IC₅₀ were also investigated by the MTT assay as well as other biological profiles, such as *In vitro* antibacterial activity and *In vitro* antifungal activity, and show significant activity (Kumar et al. 2019). Plant crude extracts are the source of such special secondary metabolites as flavonoids and terpenoids, and these compounds play an important role in reducing ionic to bulk metallic nanoparticles formation. Biosynthesized nanoparticles tested successfully changes involving

apoptosis, genotoxicity and oxidative stress (Khan et al. 2021). Furthermore, nanoparticles are widely used in the agricultural, plant sciences and used in managing food waste (Singh et al. 2021). Plant related NPs in different areas have gained a lot of attention since, plant manufactured NPs can easily be produced without help of any special agent for capping/stabilizing and reducing agent. Metabolites of plants likes terpenoids, phenols, alkaloids, flavonoids, quinines etc. used for NPs. Material which acts as a reduction and stabilization agent and produces the Metal-NPs in an environmentally friendly manner as seen in Fig. 2.

Broad application of PtNPs

Because of the cytotoxic activity of platinum nanoparticles would be very precious in the field study of the biomedical applications and biosynthesis of PtNPs. PtNPs are also reported recently as an anticancer agent from *Punica granatum crusts* on human breast cancer cell lines (Sahin et al. 2018). The redox process to metabolize eco-friendly nano-sized particles is continuously correlated with certain primary and secondary metabolites. Different work carried out on the breast cancer cell line in human, MCF-7 has confirmed the cytotoxic effects of *Punica granatum crusts* biosynthesized PtNPs and acts as anti-tumor compound. Sphere-shaped PtNPs with size

20 nm were grown through this green synthesis method. Anti-microbial activity of synthesized PtNPs have been studied by several researchers. Keeping the same in mind, it has been revealed that PtNPs is in contrast to the bacterial negative zeta potentials which have been enhanced the antibacterial properties. Researches also indicated the potential application of PtNPs against the cancer. Membrane potential studies of PtNPs against cancer have been shown via cancer cell lines and were found significantly triggered by the increased concentration of the sample (Noah and Ndangili 2022). In all test concentrations of HeLa cell line displayed more proliferative effect in 24 h. In general, the inhibition of bacteria in combination with β -lactam drug class against antibiotic aminoglycosides class may be infringed. In this main sense, it may propose that the nanoparticles serve as an agent to use to damage the bacteria’s cell wall and transmit streptomycin to the cells, and then operate upon the protein synthesizer that destroys bacteria shown in Fig. 3.

Colloidal platinum nano-structures adsorbent with organic capping agents plays key roles in many ways in the process management. Long organic capsulating chains have a hydrophobic and stereo obstacle effect, thus, stabilizing PtNPs to avoid direct contact with relatively high energy platinum surfaces (Lin et al. 2019). Because of the adsorption of capping agents, the

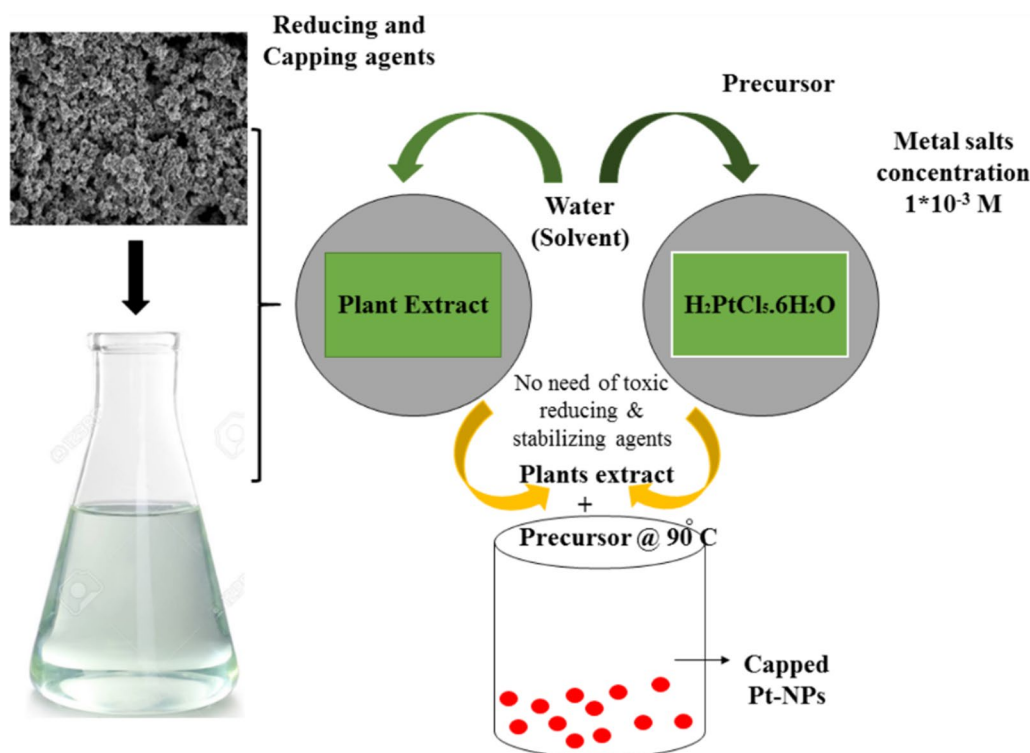


Fig. 2 Illustration of process of production of PtNPs by using the plant extract and platinum salt via environmentally friendly manner

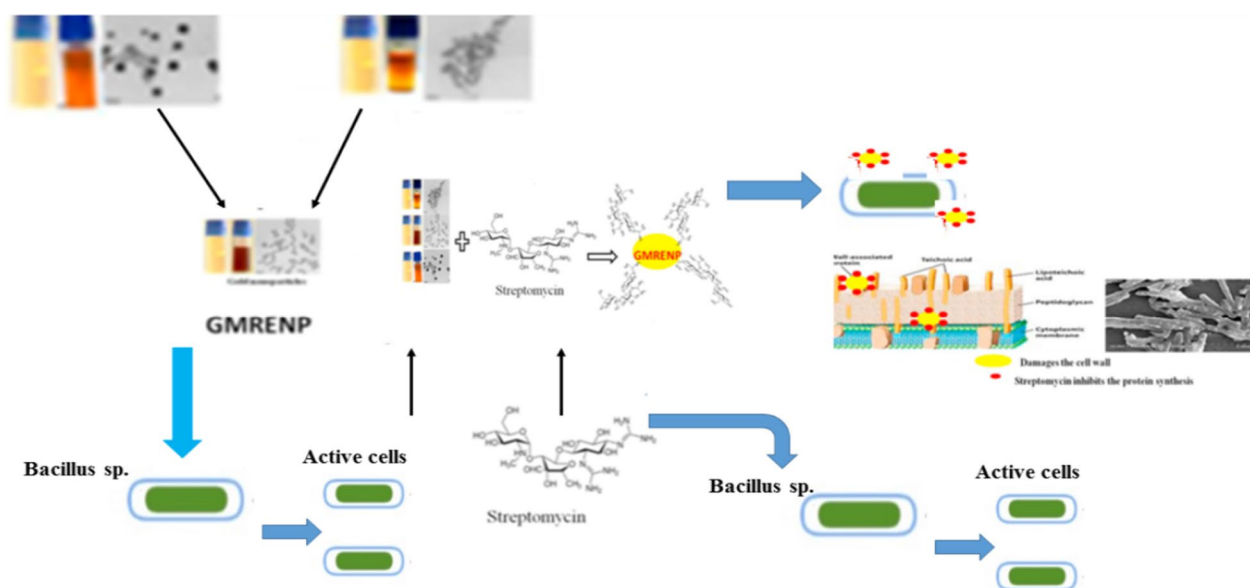


Fig. 3 Schematic description of the synergies of metal nanoparticles tagged with the antibiotics

reduction in total excess energy free prevents PtNPs from further growth and Ostwald maturation. Therefore, the morphology of the nano-crystals can be tested when capping agents adsorb very selectively on given platinum particles surfaces (Kuhn et al. 2008).

The platinum nano-crystals contain diverse electronic structures as well as nuclear configurations with different dimensions; one can assume that these surfaces absorb capping agents separately. The favored adsorption of one surface over another will lead to various development levels along different lenses. The solvent atoms will probably be more vulnerable to anisotropic growth in the less covered platinum surface region. The proper reactive interaction of guest molecules with different platinum faces, which must be balanced however choosy in desorption and adsorption, is a key criterion in choosing the right capping agent for both the shape regulation. The processing of PtNPs by plants has proved to be a feasible way to ensure the environment.

Aygun et al. (2020) have successfully synthesized the PtNPs by using the *Nigella sativa L.* (black cumin seed) extract as a reducing agent. Moreover, the results revealed its cytotoxic potential through the MDA-MB-231 breast (IC₅₀: 36.86 µg/mL) and HeLa cervical cancer lines (19.83 µg/mL) and antibacterial potential against gram[±] and gram⁻ bacteria at the concentrations of 100 and 500 µg/mL. This inhibition was obtained by the proliferation of tested NPs. In addition, the microscopic analysis displayed that the cells morphology has been changed after 24 h during the treatment with synthetic nanoparticles with different concentrations. These

findings revealed the PtNPs pharmaceutical potentials and indicating its eco-enterprising. Several researchers displayed the PtNPs synthesis by using the pomegranate and dates and indicated its impact on MCF-7 breast cancer cell line. Interestingly, the date extract PtNPs was found effective against the HepG-2 hepatocellular carcinoma cell lines which is a common cancer of the colon. Previous studies have also shown that cytotoxic activity of biosynthesized PtNPs against the A549 human pulmonary adenocarcinoma (PA-1), ovarian teratocarcinoma, cell lines of Mia-Pa-Ca-2 and cell induction arrest of stage. Furthermore, the microscopic visualization of cell proliferation and morphological alteration in cytotoxic lines have proven the end application of it. Gurunathan et al. (2019) have visualize the PtNPs (conc. of 25–150 µg/mL) effect on Human Monocytic THP-1 Cell Line after the 24 h exposure and found a unique solution for the treatment of augmented oxidative DNA damage and impaired DNA integrity.

With the modernization of NPs studies, the plant derived specified compound coated PtNPs nanozymes displayed the impressive accomplishments in nanotechnology. Ma et al. (2021) developed the portable mini-drainage device with real-time monitoring assay powered by the VitaminC-coated PtNPs (AA-PtNPs) which can perform as a catalase to catalyze the breakdown of H₂O₂ to O₂. Apo-ferritin encapsulated PtNPs are also a good example of PtNPs powered nanozymes which exhibit super oxide dismutase (SOD) enzyme-like activities and also it retains the SOD derivative activity in cell culture models (Jawaid et al. 2014).

The green synthesized NPs are well known for their antimicrobial activity toward a broad range of gram negative as well as gram-positive pathogenic bacteria. Interestingly, the antimicrobial activity of PtNPs has been found massively effective on drug resistance as well as multidrug resistance (MDR) bacteria such as *Pseudomonas aeruginosa* ATCC13048, *E. coli* K12, *Enterobacter aerogenes*, etc. It is due to their unique features such as high surface area and stability against the broad range of chemicals, as well as rapid biocidal outcome toward the gram positive and gram-negative bacteria, viruses, molds, fungi and algae. It may enhance the production of “reactive oxygen species” (ROS), leading to accumulation and then loss of integrity of the cell membranes. Additionally, it can induce DNA protein kinase down-regulation, leading to oxidative stress and finally apoptosis (Fig. 4).

Though, only few of investigation has been done for the PtNPs antibacterial activity as compared to silver and copper (Zain et al. 2014). A baseline work was reported by the Gopal et al. (2013) and indicated that PtNPs with sizes less than 3 nm displayed efficient bactericidal activity against *P. aeruginosa*. The efficacy of green At-PtNPs against the gram-negative (*E. coli* and *Klebsiella pneumonia*) and gram-positive (*Bacillus subtilis* and *Staphylococcus aureus*) bacteria was determined by the zone of inhibition with the NPs concentration of concentration of 1 mg/L (Eltaweil et al. 2022). The findings showed that the zone of inhibition for *K. pneumonia* was 17 mm and zero growth was observed in *E. coli* plate which is

indicating that At-PtNPs are extremely effective against *E. coli* as it completely prohibited the bacterial growth.

Platinum nanoparticles through egg yolk

With the advancement of nanoscience’s and virtue-full results of Pt derived nanoparticles for clinical and commercial application. Hence, it emphasized the researches to propose the more controlled way of PtNPs synthesis with required composition, form, shapes and size for various proposes and from different higher organisms. The green synthesis of PtNPs using the quail egg yolk and a reducing agent peroxidase enzyme as well as without any reducing agents provided an eco-friendly way that has the reactive medium enriched with the high protein and vitamins content.

The pH, temperature, time and concentration of the reaction situation were optimized with the aid of quail egg yolk. The results demonstrated that at 20 °C (pH 6.0) for 4 h, the maximum PtNPs were synthesized within the size range 7–50 nm. A schematic methodology of egg yolk-based PtNPs synthesis is shown in Fig. 5.

Briefly, to prepare white, and yolk reaction medium, eggs of the quail were divided. 1.0 mL of egg yolk were added to 99 mL of distilled water and stirring at high-speed by magnetic stirrer for 30 min to obtain the homogeneous medium for reaction. Then medium was filtered which allowed the homogeneous components to be leached. Further, the egg yolk homogenate was stirred at 100 rpm with 10.0 mM of H₂PtCl₆ solution at normal atmospheric pressure and temperature. Formation of the

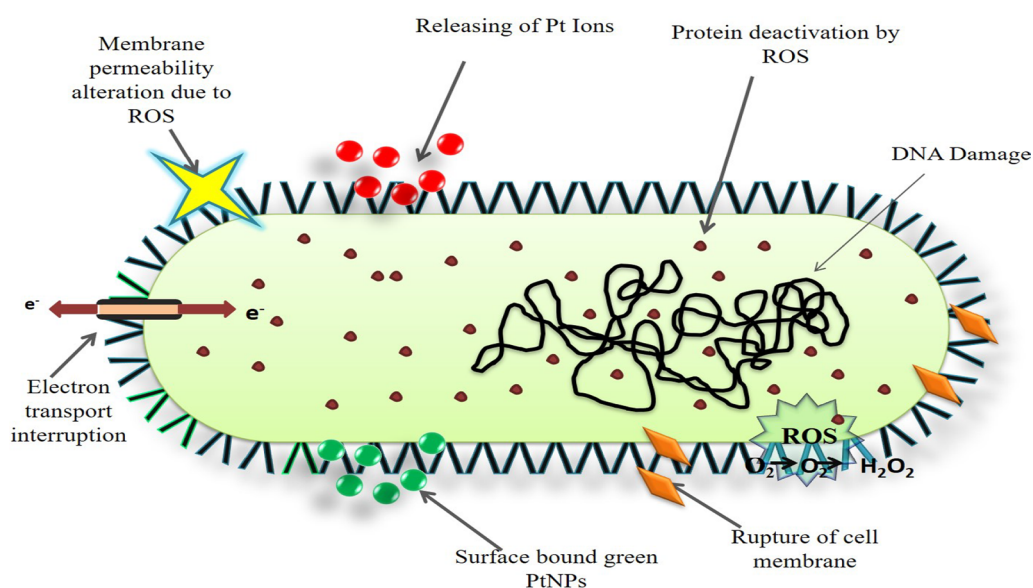


Fig. 4 ROS activity of PtNPs and interaction as well as inhibition of bacterial cell

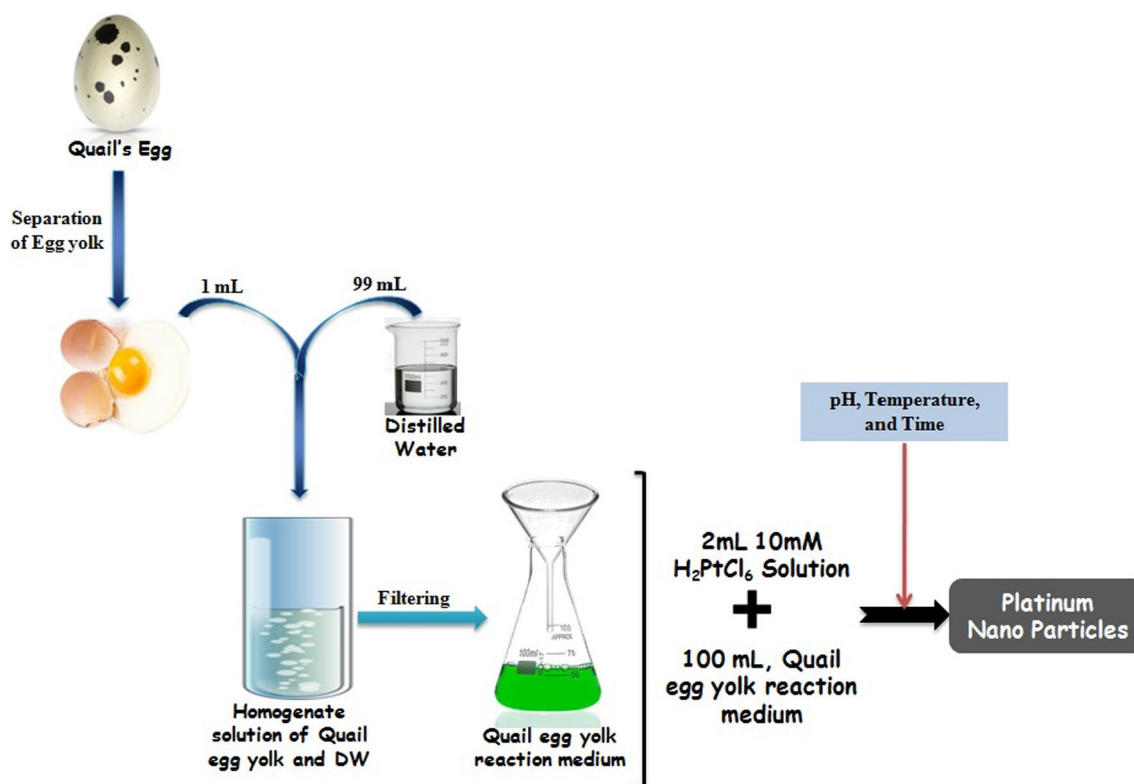


Fig. 5 Process of PtNPs synthesis through egg yolk and platinum salt

PtNPs was monitored with the scanning of reaction mixture by spectrophotometer.

The optimum reactive conditions such as metal ion concentration, reaction time, pH, temperature, etc., have determined to get maximum PtNPs by controlling the reaction parameter. Resultantly, cubic shape and sizes (7–50 nm) were observed by next generation microscopy of PtNPs that originated from quail egg yolk medium (Nadaroglu et al. 2017).

Platinum nanoparticles deposition with bio-reductive effect on algae

Algae have an exceptional aptitude to understand the metals and facilitate its uptake and accumulation and convert into more flexible forms through the hyper accumulations of heavy metal ions (Priyadarshini et al. 2019). Due to these potentials, algae are considered to be a model organism for bio-nanomaterial processing. Moreover, the algal extracts comprise of the mixture of bioactive compounds such as polyphenols, tocopherols, carotene, chlorophyll, phycocyanin, phycoerythrin, fatty acids, carbohydrates, vitamins, proteins, minerals, fats, and polyunsaturated fatty acids. Anju et al. (2020) have indicated that algal extracts are investigated for a wide

number of biomolecules and metabolites that have the capability to reduce the metal ions and capped them to improve their cellular biocompatibility.

Previous research described the main active compounds of reduction and stabilizing agents for algae-based PtNPs synthesis and basically focused on the algae-mediated nanomaterial synthesis, solution of metal precursor, and metal-algae extracts reaction mixture incubation. The reaction is started when the liquid type algal extract is combined with the targeted metal precursor molar solution. Usually, the color shift in the reaction mix defines as a visible monitoring for reaction initiation and indicating the nucleation, accompanied by evolution of NPs with neighboring nucleonic particles cluster together. Resultantly, thermodynamically stable with various sized and shaped PtNPs obtained. The algal extract's bioactive portion facilitates the NPs synthesis cascade, and the regulatory factors that involved are concentration, time, temperature, and pH. Overall synthesis is accomplished by two roots, i.e., intracellular and extracellular, that keep a side the control factors. Initially the synthesis of nanoparticles was reported to be intracellular and later algae were oppressed for an extracellular synthesis mode (Fig. 6).

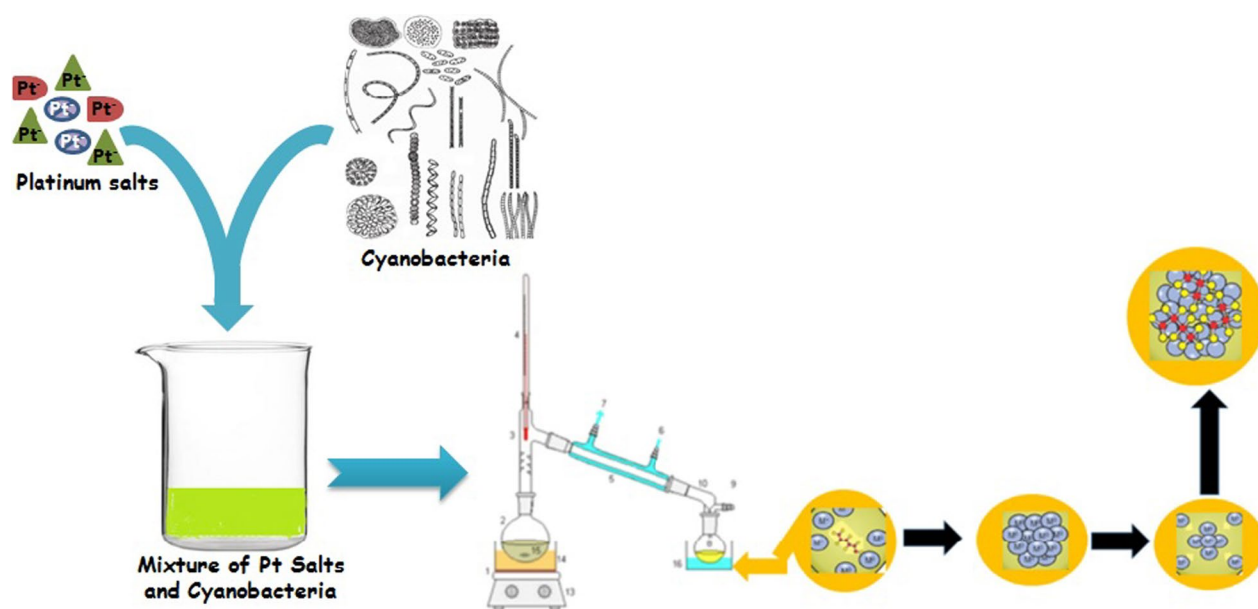


Fig. 6 Illustration of Cyanobacterial species and platinum salt based Synthesis of PtNPs

Fungal mediated PtNPs synthesis

Fungi can be used with various way to synthesize the NPs such as total fungal biomass debris, cultured liquids, intracellular extracts, protein fractions, total metabolome, individual fungal metabolites. Though, biomass-based NPs needs to need to separate the synthesized NPs from the bio-objects of fungi. Other dis-advantages of this methodology are the long-time process. Interestingly, the materials derived from fungal biomass, such as cultured liquids, intracellular extract, proteins or individual metabolites can give us a perfect option for green synthesis of nanoparticles. This technique is reproducible, time saving and there is no need to destroy the fungal cells or to separate NPs from them. Though, only Ascomycota species are profoundly reported for the synthesis of Pt-based NPs nanoparticles and has been done with intracellularly as well extracellularly with the support of some enzymes or bioactive molecules. An intra- and extracellular synthesis of PtNPs from fungal cell is described in Fig. 7.

Biosynthesis of PtNPs is studied well in the Ascomycetes fungi *Fusarium oxysporum*. *F. oxysporum* mycelium biomass was used to produce the various shaped PtNPs such as circular, square, pentagon, hexagon, and rectangle within the size range of 10–100 nm (Riddin et al. 2006). Though, extracellular bioactive-based synthesized NPs found to be more significant. Syed and Ahmad (2012) done the reduction of platinum salt by Pt(IV)-reductase enzyme of *F. oxysporum*. The synthesized PtNPs of fungal hyphae extract and hydrogenase

are showing different characteristics in the sense of size as well as in shape. The irregular shape and size range of 30–40 nm was obtained with extract and triangular, circular, pentagonal and hexagonal PtNPs with the size range of 40–60 nm were obtained with the enzyme, respectively. Further, Gupta and Chundawat (2019) synthesized the face-centered cubical shaped PtNPs (25 nm) by the using *F. oxysporum* culture filtrate which is endowed with the antimicrobial and photocatalytic potentials. Castro-Longoria (2012) has target the *Neurospora crassa* to synthesize the PtNPs by incubating the mycelium biomass with H_2PtCl_6 and obtained the extracellular PtNPs of size range 4–35 nm with spherical as well as nanoaggregates of size 20–110 nm. Sarkar and Acharya (2017) were formulated the Nano-platinum by using the fungal cultured filtrate of *Alternaria alternata* which is a common phytopathogen. The synthesized PtNPs are variable in size (50–315 nm) with irregular shape such as quasi-spherical, polygonal, rectangular, tetrahedral as well as hexagonal in morphology. The culture filtrate of model organism. *Penicillium chrysogenum* has shown the remarkable synthesis of vastly discrete non-aggregating Pt nanospheres with size range of 5–40 nm (Subramaniyan et al. 2018). Similarly, Pt nanospheres from *Saccharomyces boulardii* extract were obtained by Borse et al. (2015). It revealed that yeast cell biomass (500 mg/mL) and 0.5 mM chloroplatinic acid with the temperature 35 °C, pH 7.0 and 200 rpm needs to incubate for 36 h to achieve the significant concentration of PtNPs.

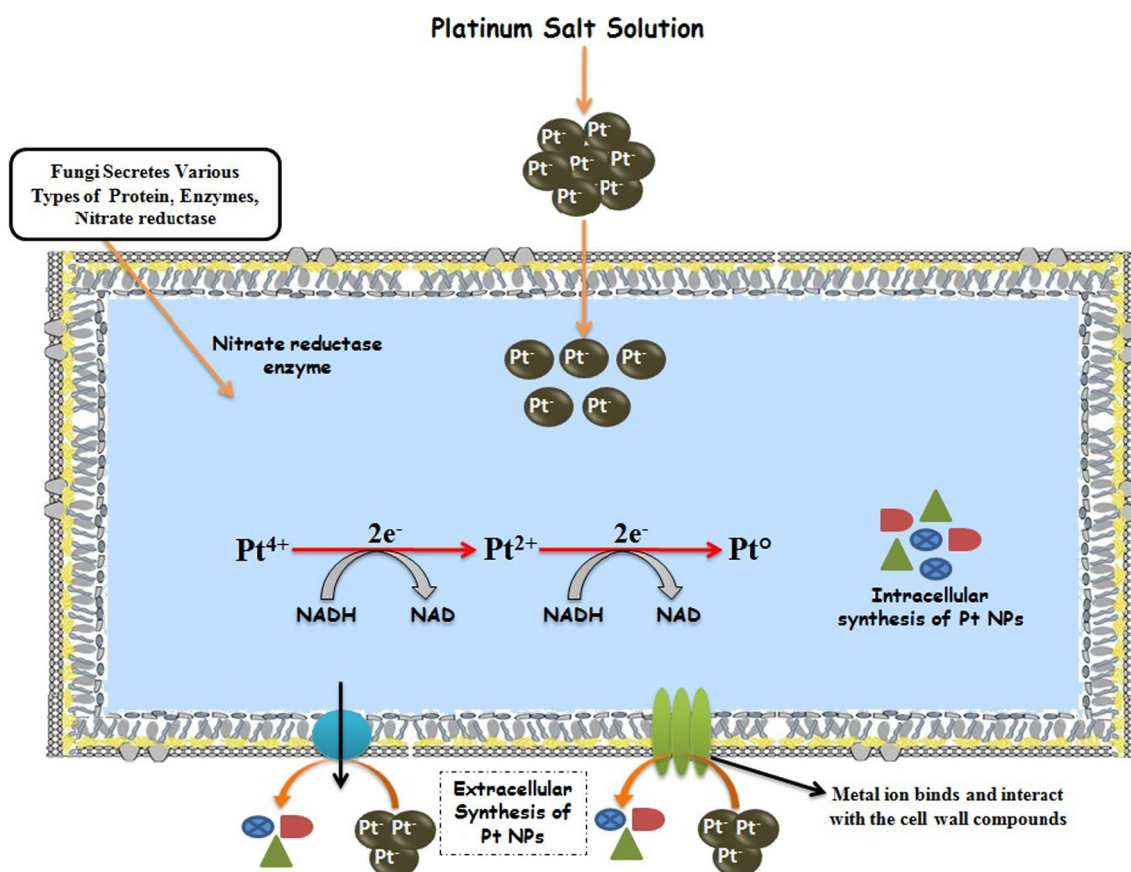


Fig. 7 Detailed process for the intracellular interaction of platinum ion and fungal metabolome and the mechanism of PtNPs synthesis

Toxicity of PtNPs

Due to the greater neoplastic patient population in recent years, substantial amounts of antineoplastic drugs based on Pt are discharged into the circumference through hospital effluents, urine patients and pharmaceuticals. Moreover, the widespread application of PtNPs in gas neutralizers for automobile drain has abruptly increased the amount of PtNPs pollution in the environment. Several species have recorded for toxic effect of cisplatin in marine organisms, such as microalgae (*Pseudokirchneriella subcapitata*), protozoans (*Tetrahymena pyriformis*), rotifers (*Brachionus calyciflorus*), crustaceans (*Daphnia magna*; *Ceriodaphnia dubia*), and fish (*Danio rerio*), which have shown their response on both inhibition in reproduction and growth (Asharani et al. 2011; Sørensen et al. 2016; Adeyemi et al. 2018; Hlavkova et al. 2018).

Koltan and Czaja (2014) have indicated that 2.5 mg/kg dose of PtNPs abridged the total count of bacteria in soil and inhibited the nitrogen fixation. A recent study has revealed that PtNPs of doses 10 and 100 mg/kg has significant negative impact on the radish crops seed germination as well as root length (Kolesnikov et al. 2023).

Phytoplankton such as *C. vulgaris* are first marine food chain links which make it significant to assess the toxicity of various agents based on toxic on these species. Findings revealed that Cisplatin does have the highest rank of environmental toxicity among Platinum-based antineoplastic drugs PBADs according to a classification for chemical toxicity to the environment. *C. Vulgaris* has toxicity on all other cytotoxic agents. This has been studied in several previous research. Higher 'IC50' values of the PBADs to the algal cells as opposed to herbicides, engineered herbicides destroy the plant cells and they inhibit photosynthetic plant mechanisms (Das 2013). Microalgae are photosynthetic cells, and are highly susceptible to herbicide toxic effects compared to PBADs. Drugs based on platinum are designed to kill animal cancer cells, and their IC50s were below 1 mg/L in all the animal cell lines tested.

Different mechanisms of toxicity of PBADs in algae, human and *C. vulgaris* can occur in stable cell walls in IC50s. The results of this study have exposed that PBADs inhibit photosynthetic pigment production, cell

photosynthesis and algal cell proliferation (Safi et al. 2014). Those toxic effects depended on dosage and time.

More strongly, compared with carboplatin and oxaliplatin, Cisplatin inhibited the production of photosynthetic pigments in algal cells. From the photosynthetic stains, carotenoid reduction was suggestively greater than that of chlorophylls. The intracellular mechanisms related to this are not been cleared and it needs further study. Increased MDA production was consistent with predictable toxicity of PBADs (alkylation agents). Possible methods of action PBADs contrary to human cells and are DNA and DNA impairment via cross-link formation between DNA to atoms by the add-on alkyl groups (Dasari and Tchounwou 2014). There is no proof that cytotoxic drugs, like by photosynthetic enzymes, inhibit the process of photosynthesis from algal chloroplast; in literature, the prevailing mechanism by which PBADs prevent algal cell proliferation is likely to occur. Further studies on the possible toxic mechanism of PBADs in algal cells are necessary. Several experiments have shown that cytotoxicity causing PBADs is closely linked to ROS and additional free radicals. ROS is the outgrowth of normal cell metabolism; but excessive levels of cells with adverse effects can cause oxidative stress. Reducing the antioxidant capacity (as observed in this study) in algal cells confirmed the oxidative stress induction (Choi et al. 2015).

Interestingly, size of synthesized PtNPs is the key factors on significant cytotoxicity. The PtNPs sizes ranging from to 21 nm tested on to the neural cell line displayed the cyto-compatible nature with size 5–6 nm but other sizes causes cell damage (Manikandan et al. 2013),

Depending on sizes PtNPs of size 8 nm showed no harmful effects but the PtNPs of size 1 nm in culture induced cytotoxicity to renal cells in a dose dependent manner with the same concentration range (Buchtelova et al. 2017). Alternatively, polyvinylpyrrolidone PVP PtNPs of size 6 nm caused a decline in genotoxic effects and metabolic activity and did not change primary keratinocyte morphology, and migration capacity while PtNPs of size 57 nm are less hazardous to keratinocytes than the minor ones (Konieczny et al. 2013). Hence, the reviewed research made clear that it can control or reduce the toxicity offered by PtNPs by controlling their size during their preparation, which will in turn effect their possible applications for biomedical purposes.

Conclusions

The bio-synthetic NP pathway is a reliable, environmentally friendly and more specifically on the green aspect synthetic tackle. Huge attempts are being made in the last few decades for green NP development approach. In addition, microbes and plants are efficient producers of

biologically active alkaloids and useful compounds which are found to have a broad range biological-based activity, like those of antimicrobial, anticancer, antibiofueling, antimalarial, antiparasitic, and antioxidant, etc. Platinum is the most rare and costly metals. This has highest corrosion resistivity and various catalytic applications include catalytic converters for catalysts for petrochemical cracking and automotive use. The PtNPs however have a detrimental impact on cancer cells. Because of this, researchers have partly abandoned studies on the use of platinum as an agent on anticancer. This is unclear since, according to other reports, PtNPs are in very low concentration: Biological stability and tolerance. These kinds of not established part can be the forthcoming challenges will be covered. The challenging recoveries of the toxicity of the NPs with greeno-biogenic inventory part of nanotech will be the suspicious event. Through this significant focus of discussed the upcoming pharmaceutical bioactive product PtNPs through the greeno-biogenic approach with different approaches like plant products, algae, fungi, and egg yolk, etc. This greeno-biogenic PtNPs scrutiny can help the rate of the upcoming pharmacological advances. In addition, the organic PtNPs are competing with chemically synthesized nanoparticles in order to ensure adequate shape and size that the regulated reaction conditions provide better stability and it is highly important to unveil the use PtNPs as nanomedicine in biological applications. The very less studies shows, it can be great evolution in the pharmacology and nanoscience. Mainly antioxidant, antibacterial, anticancer and catalytic action are the promising studied part which needs to explore in commercial prospectives.

Acknowledgements

Authors are thankful to management committee Bajaj College of Science Autonomous Wardha, Maharashtra for required support in above mentioned work.

Author contributions

UM, SN and RUT conceptualize and designed the work, YSP collected the materials, VN has revised the MS, helps in fig. designing and did the language editing, YNS, PRY and RPB has written and manuscript. All authors have read and approved the manuscript.

Funding

No funding was obtained for this study.

Availability of data and materials

The authors confirm that the data supporting the findings of this study are available within the article.

Declarations

Ethics approval and consent to participate

Not applicable.

Consent for publication

Not required.

Competing interests

The authors declare that they have no competing interests.

Received: 26 May 2023 Accepted: 13 August 2023

Published online: 24 August 2023

References

- Adeyemi OS, Molefe NI, Awakan OJ, Nwonuma CO, Alejelowo OO, Olaolu T, Maimako RF, Suganuma K, Han Y, Kato K (2018) Metal nanoparticles restrict the growth of protozoan parasites. *Artif Cells Nanomed Biotechnol* 46(sup3):86–94
- Agarwal H, Nakara A, Menon S, Shanmugam V (2019) Eco-friendly synthesis of zinc oxide nanoparticles using *Cinnamomum Tamala* leaf extract and its promising effect towards the antibacterial activity. *J Drug Deliv Sci Technol* 53:101212
- Anju AR, Gupta K, Chundawat TS (2020) In vitro antimicrobial and antioxidant activity of biogenically synthesized palladium and platinum nanoparticles using *Botryococcus braunii*. *Turk J Pharm Sci* 17(3):299
- Aritonang HF, Onggo D, Ciptati C, Radiman CL (2014) Synthesis of platinum nanoparticles from K2PtCl4 solution using bacterial cellulose matrix. *J Nanopart* 2014:85954
- Asharani PV, Lianwu YI, Gong Z, Valiyaveetil S (2011) Comparison of the toxicity of silver, gold and platinum nanoparticles in developing zebrafish embryos. *Nanotoxicology* 5(1):43–54
- Attard G, Casadesús M, Macaskie LE, Deplanche K (2012) Biosynthesis of platinum nanoparticles by *Escherichia coli* MC4100: can such nanoparticles exhibit intrinsic surface enantioselectivity? *Langmuir* 28(11):5267–5274
- Aygun A, Gülbagca F, Ozer LY, Ustaoglu B, Altunoglu YC, Baloglu MC, Atalar MN, Alma MH, Sen F (2020) Biogenic platinum nanoparticles using black cumin seed and their potential usage as antimicrobial and anticancer agent. *J Pharm Biomed Anal* 179:112961
- Borse V, Kaler A, Banerjee UC (2015) Microbial synthesis of platinum nanoparticles and evaluation of their anticancer activity. *Int J Emerg Trends Electr Electron* 11(2):26–31.
- Botha TL, Elemike EE, Horn S, Onwudiwe DC, Giesy JP, Wepener V (2019) Cytotoxicity of Ag, Au and Ag-Au bimetallic nanoparticles prepared using golden rod (*Solidago canadensis*) plant extract. *Sci Rep* 9(1):1–8
- Brayner R, Barberousse H, Hemadi M, Djedjat C, Yéprémian C, Coradin T, Livage J, Fiévet F, Couté A (2007) Cyanobacteria as bioreactors for the synthesis of Au, Ag, Pd, and Pt nanoparticles via an enzyme-mediated route. *J Nanosci Nanotechnol* 7(8):2696–2708
- Buchtelova H, Dostalova H, Michalek P, Krizkova S, Strmiska V, Kopel P, Hynek D, Richtera L, Ridoskova A, Adam P, Kynicky J (2017) Size-related cytotoxicological aspects of polyvinylpyrrolidone-capped platinum nanoparticles. *Food Chem Toxicol* 105:337–346
- Choi YM, Kim HK, Shim W, Anwar MA, Kwon JW, Kwon HK, Kim HJ, Jeong H, Kim HM, Hwang D, Kim HS (2015) Mechanism of cisplatin-induced cytotoxicity is correlated to impaired metabolism due to mitochondrial ROS generation. *PLoS ONE* 10(8):e0135083
- Dahiya P, Kamal R, Gupta R, Bhardwaj R, Chaudhary K, Kaur S (2013) Reactive oxygen species in periodontitis. *J Indian Soc Periodontol* 17(4):411–416
- Das SK (2013) Mode of action of pesticides and the novel trends—a critical review. *Int Res J Agric Sci Soil Sci* 3(11):393–401
- Dasari S, Tchounwou PB (2014) Cisplatin in cancer therapy: molecular mechanisms of action. *Eur J Pharmacol* 740:364–378
- Eltaweil AS, Fawzy M, Hosny M, Abd El-Monaem EM, Tamer TM, Omer AM (2022) Green synthesis of platinum nanoparticles using *Atriplex halimus* leaves for potential antimicrobial, antioxidant, and catalytic applications. *Arab J Chem* 15(1):103517
- Fahmy SA, Preis E, Bakowsky U, Azzazy HME (2020) Platinum nanoparticles: green synthesis and biomedical applications. *Molecules* 25(21):4981. <https://doi.org/10.3390/molecules25214981>
- Gaidhani SV, Yeshvekar RK, Shedbalkar UU, Bellare JH, Chopade BA (2014) Bio-reduction of hexachloroplatinic acid to platinum nanoparticles employing *Acinetobacter calcoaceticus*. *Process Biochem* 49(12):2313–2319
- Ganaie SU, Abbasi T, Abbasi SA (2018) Biomimetic synthesis of platinum nanoparticles utilizing a terrestrial weed *Antigonon leptopus*. *Part Sci Technol* 36(6):681–688
- Gholami-Shabani M, Sotoodehnejadnematalahi F, Shams-Ghahfarokhi M, Eslamifar A, Razzaghi-Abyaneh M (2023) Platinum nanoparticles as potent anticancer and antimicrobial agent: green synthesis, physical characterization, and in-vitro biological activity. *J Cluster Sci* 34(1):501–516
- Ghosh S, Nitnavare R, Dewle A, Tomar GB, Chippalkatti R, More P, Kitture R, Kale S, Bellare J, Chopade BA (2015) Novel platinum–palladium bimetallic nanoparticles synthesized by *Dioscorea bulbifera*: anticancer and antioxidant activities. *Int J Nanomed* 10:7477
- Göl F, Aygün A, Seyrankaya A, Gür T, Yenikaya C, Şen F (2020) Green synthesis and characterization of *Camellia sinensis* mediated silver nanoparticles for antibacterial ceramic applications. *Mater Chem Phys* 250:123037
- Gopal J, Hasan N, Manikandan M, Wu HF (2013) Bacterial toxicity/compatibility of platinum nanospheres, nanocuboids and nanoflowers. *Sci Rep* 3:1260
- Gour A, Jain NK (2019) Advances in green synthesis of nanoparticles. *Artif Cells Nanomed Biotechnol* 47(1):844–851
- Gu T, Wang Y, Lu Y, Cheng L, Feng L, Zhang H, Li X, Han G, Liu Z (2019) Platinum nanoparticles to enable electrodynamic therapy for effective cancer treatment. *Adv Mater* 31(14):1806803
- Guleria A, Sachdeva H, Saini K, Gupta K, Mathur J (2022) Recent trends and advancements in synthesis and applications of plant-based green metal nanoparticles: a critical review. *Appl Organomet Chem* 36(9):e6778
- Gupta K, Chundawat TS (2019) Bio-inspired synthesis of platinum nanoparticles from fungus *Fusarium oxysporum*: its characteristics, potential antimicrobial, antioxidant and photocatalytic activities. *Mater Res Express* 6(10):10506
- Hlavkova D, Beklova M, Kopel P, Havelkova B (2018) Evaluation of platinum nanoparticles ecotoxicity using representatives of distinct trophic levels of aquatic biocenosis. *Neuroendocrinol Lett* 39:465–472
- Hosny M, Fawzy M, El-Fakharany EM, Omer AM, Abd El-Monaem EM, Khalifa RE, Eltaweil AS (2022) Biogenic synthesis, characterization, antimicrobial, antioxidant, antidiabetic, and catalytic applications of platinum nanoparticles synthesized from Polygonum salicifolium leaves. *J Environ Chem Eng* 10(1):106806
- Jawaid P, Rehman MU, Yoshihisa Y, Li P, Zhao QL, Hassan MA, Miyamoto Y, Shimizu T, Kondo T (2014) Effects of SOD/catalase mimetic platinum nanoparticles on radiation-induced apoptosis in human lymphoma U937 cells. *Apoptosis* 19:1006–1016
- Jeyaraj M, Gurunathan S, Qasim M, Kang MH, Kim JH (2019) A comprehensive review on the synthesis, characterization, and biomedical application of platinum nanoparticles. *Nanomaterials* 9(12):1719
- Jha B, Rao M, Chattopadhyay A, Bandyopadhyay A, Prasad K, Jha AK. Punic granatum fabricated platinum nanoparticles: a therapeutic pill for breast cancer. In: AIP Conference Proceedings 2018, Vol. 1953, No. 1, p. 030087. AIP Publishing LLC.
- Karim NA, Rubinsin NJ, Burukan MA, Kamarudin SK (2019) Sustainable route of synthesis platinum nanoparticles using orange peel extract. *Int J Green Energy* 16(15):1518–1526
- Karthik R, Sasikumar R, Chen SM, Govindasamy M, Kumar JV, Muthuraj V (2016) Green synthesis of platinum nanoparticles using *Quercus glauca* extract and its electrochemical oxidation of hydrazine in water samples. *Int J Electrochem Sci* 11:8245–8255
- Khan MA, Al Mamun MS, Ara MH (2021) Review on platinum nanoparticles: synthesis, characterization, and applications. *Microchem J* 171:106840
- Kharisov BI, Dias HR, Kharissova OV, Vázquez A, Pena Y, Gomez I (2014) Solubilization, dispersion and stabilization of magnetic nanoparticles in water and non-aqueous solvents: recent trends. *RSC Adv* 4(85):45354–45381
- Kolesnikov S, Timoshenko A, Kabakova V, Minnikova T, Tsepina N, Kazeev K, Minkina TM, Shende SS, Mandzhieva SS, Tsitsushvili V, Sushkova SN (2023) Effect of platinum nanoparticles (PtNPs) pollution on the biological properties of Haplic Cambisols Eutric of the Caucasus forests. *Forests* 14(1):54
- Kolton A, Czaja MA (2014) Influence of platinum ions on the germination and seedling root growth of different plant species. *Geol Geophys Environ* 40:343–348
- Konieczny P, Goralczyk AG, Szmyd R, Skalniak L, Koziel J, Filon FL, Crosera M, Cierniak A, Zuba-Surma EK, Borowczyk J, Laczna E (2013) Effects triggered by platinum nanoparticles on primary keratinocytes. *Int J Nanomed* 8:3963–3975
- Kuhn JN, Huang W, Tsung CK, Zhang Y, Somorjai GA (2008) Structure sensitivity of carbon–nitrogen ring opening: impact of platinum particle size from

- below 1 to 5 nm upon pyrrole hydrogenation product selectivity over monodisperse platinum nanoparticles loaded onto mesoporous silica. *J Am Chem Soc* 130(43):14026–14027
- Kumar KM, Mandal BK, Tammina SK (2013) Green synthesis of nano platinum using naturally occurring polyphenols. *RSC Adv* 3(12):4033–4039
- Kumar PV, Kala SM, Prakash KS (2019) Green synthesis derived Pt-nanoparticles using *Xanthium strumarium* leaf extract and their biological studies. *J Environ Chem Eng* 7(3):103146
- Latif MS, Abbas S, Kormin F, Mustafa MK (2020) Green synthesis of plant-mediated metal nanoparticles: the role of polyphenols. *Asian J Pharm Clin Res* 2019:75–84
- Li RW, Smith PN, Lin GD (2022). Variation of biomolecules in plant species. In: *Herbal biomolecules in healthcare applications*, pp. 81–99. Academic Press
- Liu X, Zhu Z, Zhao C, Li S, Liu Q, Liu A, Lin L, Lin X (2019) Robust oxidase mimicking activity of protamine-stabilized platinum nanoparticles units and applied for colorimetric sensor of trypsin and inhibitor. *Sens Actuators B Chem* 284:346–353
- Liu L, Jing Y, Guo A, Li X, Li Q, Liu W, Zhang X (2022) Biosynthesis of platinum nanoparticles with *Cordyceps* flower extract: characterization, antioxidant activity and antibacterial activity. *Nanomaterials* 12(11):1904
- Longoria EC, Velasquez SM, Nestor AV, Berumen EA, Borja MA (2012) Production of platinum nanoparticles and nanoaggregates using *Neurospora crassa*. *J Microbiol Biotechnol* 22(7):1000–1004
- Ma X, Wang Z, Hu X, Chen J, Zhang H, Li X, Xie F, Xu J (2021) Nanozyme catalysis-powered portable mini-drainage device enables real-time and universal weighing analysis of silver ions and silver nanoparticles. *J Hazard Mater* 415:125689
- Manikandan M, Hasan N, Wu HF (2013) Platinum nanoparticles for the photothermal treatment of Neuro 2A cancer cells. *Biomaterials* 34(23):5833–5842
- Manthe RL, Foy SP, Krishnamurthy N, Sharma B, Labhasetwar V (2010) Tumor ablation and nanotechnology. *Mol Pharm* 7(6):1880–1898
- Muñiz-Díaz R, Gutiérrez de la Rosa SY, Gutiérrez Coronado Ó, Patakfalvi R (2022) Biogenic synthesis of platinum nanoparticles. *Chem Pap* 76(5):2573–2594
- Nadaroglu H, Gungor AA, Ince S, Babagil A (2017) Green synthesis and characterisation of platinum nanoparticles using quail egg yolk. *Spectrochim Acta Part A Mol Biomol Spectrosc* 172:43–47
- Naseer A, Ali A, Ali S, Mahmood A, Kusuma HS, Nazir A et al (2020) Biogenic and eco-benign synthesis of platinum nanoparticles (Pt NPs) using plants aqueous extracts and biological derivatives: environmental, biological and catalytic applications. *J Mater Res Technol* 9(4):9093–9107. <https://doi.org/10.1016/j.jmrt.2020.06.013>
- Nellore J, Pauline C, Amarnath K (2013) *Bacopa monnieri* phytochemicals mediated synthesis of platinum nanoparticles and its neurorescue effect on 1-methyl 4-phenyl 1, 2, 3, 6 tetrahydropyridine-induced experimental parkinsonism in zebrafish. *J Neurodegener Dis* 2013:972391
- Noah NM, Ndagili PM (2022) Green synthesis of nanomaterials from sustainable materials for biosensors and drug delivery. *Sens Int* 3:100166
- Oluwafemi OS, Mochochoko T, Leo AJ, Mohan S, Jumbam DN, Songca SP (2016) Microwave irradiation synthesis of silver nanoparticles using cellulose from *Eichhornia crassipes* plant shoot. *Mater Lett* 185:576–579
- Priyadarshini E, Priyadarshini SS, Pradhan N (2019) Heavy metal resistance in algae and its application for metal nanoparticle synthesis. *Appl Microbiol Biotechnol* 103(8):3297–3316
- Rajasekharreddy P, Rani PU (2014) Biosynthesis and characterization of Pd and Pt nanoparticles using *Piper betle* L. plant in a photoreduction method. *J Clust Sci* 25:1377–1388
- Rawat V, Sharma A, Bhatt VP, Singh RP, Maurya IK (2020) Sunlight mediated green synthesis of silver nanoparticles using *Polygonatum graminifolium* leaf extract and their antibacterial activity. *Mater Today Proc* 29:911–916
- Raza MA, Kanwal Z, Rauf A, Sabri AN, Riaz S, Naseem S (2016) Size- and shape-dependent antibacterial studies of silver nanoparticles synthesized by wet chemical routes. *Nanomaterials* 6(4):74
- Riddin TL, Gericke M, Whiteley CG (2006) Analysis of the inter- and extracellular formation of platinum nanoparticles by *Fusarium oxysporum* f. sp. *lycopersici* using response surface methodology. *Nanotechnology* 17(14):3482
- Rokade SS, Joshi KA, Mahajan K, Tomar G, Dubal DS, Singh V, Kitture R, Bellare J, Ghosh S (2017) Novel anticancer platinum and palladium nanoparticles from *Barleria prionitis*. *Glob J Nanomed* 2(5):555600
- Rokade SS, Joshi KA, Mahajan K, Patil S, Tomar G, Dubal DS, Parihar VS, Kitture R, Bellare JR, Ghosh S (2018) *Gloriosa superba* mediated synthesis of platinum and palladium nanoparticles for induction of apoptosis in breast cancer. *Bioinorg Chem Appl*. <https://doi.org/10.1155/2018/4924186>
- Sadalage PS, Dar MA, Bhor RD, Bhalerao BM, Kamble PN, Paiva-Santos AC, Nimbalkar MS, Sonawane KD, Pai K, Patil PS, Pawar KD (2022) Optimization of biogenic synthesis of biocompatible platinum nanoparticles with catalytic, enzyme mimetic and antioxidant activities. *Food Biosci* 50:102024
- Safi C, Zebib B, Merah O, Pontalier PY, Vaca-Garcia C (2014) Morphology, composition, production, processing and applications of *Chlorella vulgaris*: a review. *Renew Sustain Energy Rev* 35:265–278
- Şahin B, Aygün A, Gündüz H, Şahin K, Demir E, Akocak S, Şen F (2018) Cytotoxic effects of platinum nanoparticles obtained from pomegranate extract by the green synthesis method on the MCF-7 cell line. *Colloids Surf B Biointerfaces* 163:119–124
- Sana SS, Kumbhakar DV, Pasha A, Pawar SC, Grace AN, Singh RP, Nguyen VH, Le QV, Peng W (2020) *Crotalaria verrucosa* leaf extract mediated synthesis of zinc oxide nanoparticles: assessment of antimicrobial and anticancer activity. *Molecules* 25(21):4896
- Sana SS, Singh RP, Sharma M, Srivastava AK, Manchanda G, Rai AR, Zhang ZJ (2021) Biogenesis and application of nickel nanoparticles: a review. *Curr Pharm Biotechnol* 22(6):808–822
- Sarkar J, Acharya K (2017) *Alternaria alternata* culture filtrate mediated bioreduction of chloroplatinum to platinum nanoparticles. *Inorg Nano-Met Chem* 47(3):365–369
- Sathiyaraj G, Vinosha M, Sangeetha D, Manikandakrishnan M, Palanisamy S, Sonaimuthu M, Manikandan R, You S, Prabhu NM (2021) Bio-directed synthesis of Pt-nanoparticles from aqueous extract of red algae *Halymenia dilatata* and their biomedical applications. *Colloids Surf A Physicochem Eng Asp* 618:126434
- Selvi AM, Palanisamy S, Jeyanthi S, Vinosha M, Mohandoss S, Tabarsa M, You S, Kannapiran E, Prabhu NM (2020) Synthesis of *Tragia involucrata* mediated platinum nanoparticles for comprehensive therapeutic applications: antioxidant, antibacterial and mitochondria-associated apoptosis in HeLa cells. *Process Biochem* 98:21–33
- Sheny DS, Philip D, Mathew J (2013) Synthesis of platinum nanoparticles using dried *Anacardium occidentale* leaf and its catalytic and thermal applications. *Spectrochim Acta Part A Mol Biomol Spectrosc* 114:267–271
- Singh RP, Handa R, Manchanda G (2021) Nanoparticles in sustainable agriculture: an emerging opportunity. *J Control Release* 329:1234–1248
- Singh RP, Srivastava AK, Yang YJ, Manchanda G, Kumar A, Yerpude ST, Rai AR, Dubey RC (2023) Nucleic acid nanotechnology: trends, opportunities and challenges. *Curr Pharm Biotechnol* 24(1):50–60
- Song JY, Kwon EY, Kim BS (2010) Biological synthesis of platinum nanoparticles using *Diopyros kaki* leaf extract. *Bioprocess Biosyst Eng* 33:159–164
- Sørensen SN, Engelbrekt C, Lützhøft HC, Jiménez-Lamana J, Noori JS, Alatrakchi FA, Delgado CG, Slaveykova VI, Baun A (2016) A multimethod approach for investigating algal toxicity of platinum nanoparticles. *Environ Sci Technol* 50(19):10635–10643
- Soundararajan C, Sankari A, Dhandapani P, Maruthamuthu S, Ravichandran S, Sozhan G, Palaniswamy N (2012) Rapid biological synthesis of platinum nanoparticles using *Ocimum sanctum* for water electrolysis applications. *Bioprocess Biosyst Eng* 35:827–833
- Subramaniyan SA, Sheet S, Vinothkannan M, Yoo DJ, Lee YS, Belal SA, Shim KS (2018) One-pot facile synthesis of Pt nanoparticles using cultural filtrate of microgravity simulated grown *P. chrysogenum* and their activity on bacteria and cancer cells. *J Nanosci Nanotechnol* 18(5):3110–2125
- Syed A, Ahmad A (2012) Extracellular biosynthesis of platinum nanoparticles using the fungus *Fusarium oxysporum*. *Colloids Surf B Biointerfaces* 97:27–31
- Tahir K, Nazir S, Ahmad A, Li B, Khan AU, Khan ZU, Khan FU, Khan QU, Khan A, Rahman AU (2017) Facile and green synthesis of phytochemicals capped platinum nanoparticles and in vitro their superior antibacterial activity. *J Photochem Photobiol B Biol* 166:246–251
- Thirumurugan A, Aswitha P, Kiruthika C, Nagarajan S, Christy AN (2016) Green synthesis of platinum nanoparticles using *Azadirachta indica*—an eco-friendly approach. *Mater Lett* 170:175–178
- Vinod VT, Saravanan P, Sreedhar B, Devi DK, Sashidhar RB (2011) A facile synthesis and characterization of Ag, Au and Pt nanoparticles using a natural hydrocolloid gum kondagogu (*Cochlospermum gossypium*). *Colloids Surf B Biointerfaces* 83(2):291–298

- Wang DP, Shen J, Qin CY, Li YM, Gao LJ, Zheng J, Feng YL, Yan Z, Zhou X, Cao JM (2022) Platinum nanoparticles promote breast cancer cell metastasis by disrupting endothelial barrier and inducing intravasation and extravasation. *Nano Res* 15(8):7366–7377
- Wu J, Gao T, Guo H, Zhao L, Lv S, Lv J, Yao R, Yu Y, Ma F (2023) Application of molecular dynamics simulation for exploring the roles of plant biomolecules in promoting environmental health. *Sci Total Environ* 869:161871
- Ye L, Cao Z, Liu X, Cui Z, Li Z, Liang Y, Zhu S, Wu S (2022) Noble metal-based nanomaterials as antibacterial agents. *J Alloys Compd* 904:164091
- Yerpude ST, Potbhare AK, Bhilkar P, Rai AR, Singh RP, Abdala AA, Adhikari R, Sharma R, Chaudhary RG (2023) Biomedical and clinical applications of platinum-based nanohybrids: an update review. *Environ Res* 231:116148
- Zain NM, Stapley AG, Shama GJ (2014) Green synthesis of silver and copper nanoparticles using ascorbic acid and chitosan for antimicrobial applications. *Carbohydr Polym* 112:195–202
- Zhang L, Laug L, Munchgesang W, Pippel E, Gösele U, Brandsch M, Knez M (2010) Reducing stress on cells with apoferritin-encapsulated platinum nanoparticles. *Nano Lett* 10(1):219–223
- Zheng B, Kong T, Jing X, Odoom-Wubah T, Li X, Sun D, Lu F, Zheng Y, Huang J, Li Q (2013) Plant-mediated synthesis of platinum nanoparticles and its bioreductive mechanism. *J Colloid Interface Sci* 396:138–145
- Zhou G, Wong WY, Poon SY, Ye C, Lin Z (2009) Symmetric versus unsymmetric platinum (II) bis (aryleneethynylene) s with distinct electronic structures for optical power limiting/optical transparency trade-off optimization. *Adv Func Mater* 19(4):531–544

Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Submit your manuscript to a SpringerOpen® journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► [springeropen.com](https://www.springeropen.com)
