

Construction Materials: From Innovation to Conservation

Karen Scrivener and Henri Van Damme,
Guest Editors

Abstract

This article serves to introduce the May 2004 issue of *MRS Bulletin* on Construction Materials: From Innovation to Conservation. By volume, building materials are by far the most widely used type of materials. The most common construction materials—concrete and wood—are paradigms of complex and hierarchical materials, with a microstructure extending quasi-continuously down to the nanoscale. In the past, most improvements have been obtained by modifying the microstructure at the largest scales, for instance, by reducing the macroporosity. Recent advances in our understanding of the interactions and microstructure development show that the major levers for improvement from now on will rely on surface and colloid science and the science of complex materials, often at the nanoscale. This can lead to remarkable properties, such as self-compaction and ultrahigh strength, and even new functionality, such as self-cleaning through photocatalysis. Construction materials face a wide range of challenges today, many of which are linked to the need for more sustainable development: reducing the consumption of raw materials, reducing the energy used in processing, and increasing service life. In many parts of the world, there is also an increasing need to repair, rehabilitate, and conserve old buildings. The articles in this issue touch on these challenges as well as the advances being made in construction materials through materials research.

Keywords: cement, cohesion, concrete, construction materials, flow modeling, granular materials, photocatalysis, raw earth, self-cleaning materials, rheology, wood.

By volume, construction materials are by far the most widely used type of materials. Buildings, bridges, roads, dams, and other parts of our infrastructure can be made of concrete, wood, earth, glass, steel, or a variety of other materials, ranging from low-tech to advanced. At first glance, these materials have little in common, except their final use. Glass is a transparent, amorphous, and brittle dielectric material, while steel is a polycrystalline metallic conductor. Concrete is composed of aggregates (essentially, crushed rock or gravel) bound together with cement, while wood is a natural polymeric multiscale organic composite (an unsurpassed example for the present biomimetic approach in materials science).

Yet, a closer look shows that from a materials science perspective, two unifying themes emerge in this heterogeneous landscape. The first covers glass, steel, and cement, all of which require a knowledge of high-temperature phase equilibria and microstructure formation. Understanding these materials also draws on knowledge from the geological sciences.

A second point of commonality brings concrete, earth, and wood together. All three are porous materials, with a broad range of microstructural length scales. All three bear a special relationship with water and swell or shrink depending on moisture conditions. All three benefit from current research and development in the fields of

granular and soft matter, porous media, and foam physics. However, they have still a long way to go before their complexity can be molded into a conceptual framework as elegant as that of metals or polymers, for instance. In spite of and because of that, it is this area of materials for construction that we choose to explore in this issue of *MRS Bulletin*.

Construction materials provide the essential fabric for modern civilization; they must be cheap and readily available. This is one of the primary reasons for the overwhelming dominance of concrete as a construction material. Nearly ten times more concrete is used in construction annually—around one cubic meter per person—than all other materials combined. These large volumes are essentially determined by the human scale of construction.

The five major elements that make up the cement portion of concrete—O, Si, Ca, Al, and Fe—are the five most abundant in the Earth's crust, together constituting over 91% of the crust (Table I).¹ The other factor in the success of concrete as a building material is the astounding ability of cement to transform from a fine powder to a rigid solid of almost any form with the simple addition of water at ambient temperatures and with minimal change in dimension. For these reasons, the use of concrete has transformed the built environment over the last century.

Despite its omnipresence in construction, the application of concrete is largely based on empirical knowledge acquired through macroscopic testing, and the depth of our understanding of the chemical and physical processes that deliver the performance of concrete on a macroscopic scale is quite limited. Concrete is, in fact, an extremely complex material,² comprising tens of chemical species reacting to form hierarchical structures ranging from nanometers to meters, undergoing change from the moment it is mixed with water, and continuing to mature and alter over centuries. The lack of understanding of concrete is a major obstacle to improvement and innovation in the use of this material. Four of the articles that follow in this issue show how new approaches based on materials science are starting to emerge and have a significant impact on applications. It is interesting to note that many of the authors of these articles work for industrial companies.

The basic variable underlying the performance of concrete is the amount of water added to it. More water increases the space between the cement grains, which must subsequently be filled with the products of the reaction between the cement grains and water (known as hydration).

Table I: Comparison of the Abundance of Principal Elements in the Earth's Crust and in Portland Cement.

Element	% in Earth's Crust	Typical % in Portland Cement
Oxygen	46.71	34
Silicon	27.69	9
Aluminum	8.07	3
Iron	5.05	3
Calcium ^a	3.65	46
Total	91.17	95

^a Despite the low overall abundance of calcium in the Earth's crust relative to Portland cement, it is widely available in the relatively pure form of limestone.

Space not filled by the hydration products remains as porosity, which limits both the mechanical performance and durability of the concrete. Therefore, theoretically, the best properties are obtained when the amount of water is minimized. On the other hand, the minimum quantity of water is determined in practice by the need to produce a mixable fluid paste that can flow into a form. This minimum amount is determined by the size and packing of the granular materials and by the forces between them. This is covered in the first article, by Flatt et al., describing the science behind the development of organic admixtures for concrete that deflocculate the cement grains during mixing and allow much lower quantities of water to be used. Such organic admixtures have been the major factor in the development of high-strength concrete over the past few decades. High-strength concretes can be routinely produced with compressive strengths of 100 MPa or more, as compared with ~20–40 MPa for “standard” concrete.

Although the process of strength development in concrete can be described simplistically as filling the space originally occupied by water with hydration products, there must nevertheless be some cohesion between these hydration products. The origin of this cohesion is one of the basic mysteries of the science of concrete. Recent molecular simulation studies, discussed in the article by Pellenq and Van Damme, provide new insights into the possible origin of these cohesive forces.

Several recent developments—improved flow through the use of organic admixtures, optimization of particle packing, and the use of fiber reinforcing—have been brought together to produce ultrahigh-performance concretes, as described in the article by Vernet. These materials have exceptional mechanical performance, similar to steel, allowing lighter structures to be built with less material. They also have outstanding durability. In terms of architectural design, these developments will allow

further progress toward more elegant concrete structures, as illustrated in Figure 1.

Nowhere are construction materials under greater attack from pollution than in big cities. Dirt deposits and biodegradation from colonization by algae, fungi, and lichens, favored by the presence of moisture, are responsible for the accelerated aging of concrete structures. Photocatalysis may well prove to be a solution for “stay-clean” buildings, as discussed in the article by Cassar. Glass coated with a thin, transparent (in the visible range) layer of titanium dioxide is self-cleaning in daylight, thanks to the strong oxidizing power of the electron holes generated by near-UV-bandgap light, which are able to decompose almost any organic compound. Concrete or cement mortar doped with

TiO₂ behaves similarly, and several self-cleaning buildings have already been constructed. Furthermore, this concrete can be used to reduce environmental pollutants such as NO_x. Building facades and roads offer huge unexploited areas for this application. Preliminary tests performed on actual roads with heavy traffic show that this is not a dream.³ Remarkably, the composite TiO₂/concrete material appears to be more effective at self-cleaning and NO_x breakdown than the photocatalyst alone.

After concrete, we chose to illustrate a recent development with wood. The use of wood in construction is substantial and its rate of consumption is probably close to the limit that sustainable forests can support. The availability of timber also imposes geographical limits on its use. Wood has excellent strength for its weight and can be easily cut; however, most of the use of timber in construction is unsophisticated and involves minimal processing. The interaction of wood with moisture, leading to dimensional change and degradation, is the main disadvantage of its use. The article by Navi and Heger describes research on novel processing techniques for wood that aim to overcome this moisture sensitivity.

Finally, we have chosen to include an article on construction with the most basic and ancient material of all: raw earth. This material, whose importance in this field is often overlooked, continues to provide a

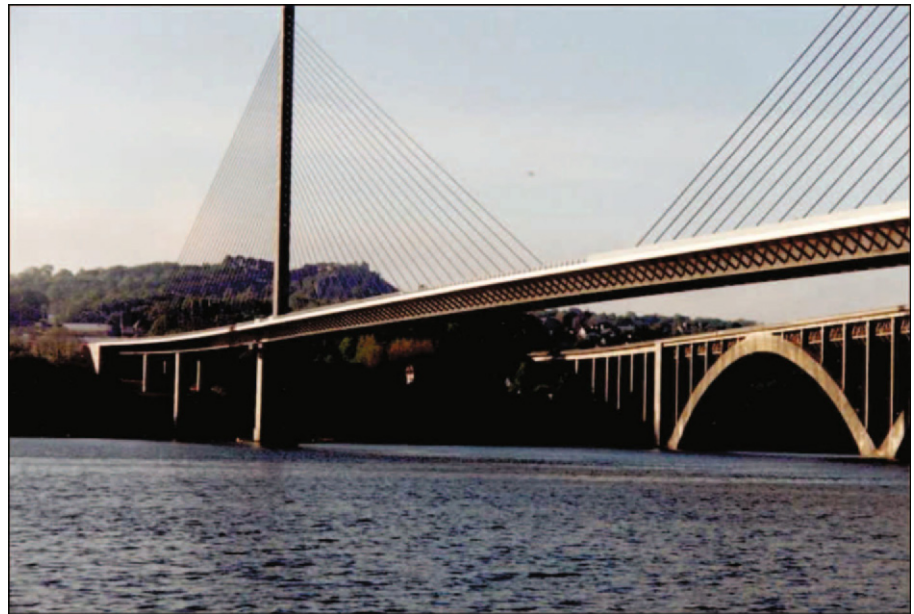


Figure 1. Two bridges built 50 years apart, spanning the Elorn River in Brittany on the west coast of France. The lighter structure of the more recent bridge (foreground) demonstrates progress in concrete construction, compared with the older bridge (background): modern concretes are ten times stronger than those of the beginning of the 20th century.

major part of the construction needs in many developing countries. Earthen construction has evolved toward well-controlled procedures that make it, with the proper architectural design, a very flexible, cost-effective, and environmentally friendly solution in a wide range of possible applications, including in developed countries. As discussed in the article by Houben et al., the problem of conservation of our huge but fragile earthen architectural and artistic heritage, which represents at least 17% of UNESCO's "World Cultural Heritage" list, still remains. Only progress through materials science will allow us to find reliable long-term solutions.

Together, the articles in this issue show a small part of the range of research currently being carried out on construction materials. We believe that it is important to pursue research based on disciplines such as materials science that seek to relate macroscopic performance to mechanisms occurring on the micro- and nanoscale. Improvements in these materials are needed to respond to the increasing demand of society and especially to the key issues of environmental impact and sustainable development. In developed countries, over half the capital investment is in buildings and infrastructure and about half of the materials extracted from the earth each year is destined for use in construction. The materials described here are all low-energy materials. Earth and wood only require energy for collection, transport, and forming. Surprisingly, despite the high-temperature firing needed to produce cement, the energy content, by weight, of concrete is today only slightly more than that of cut wood (which has to be dried), and even less than that of processed wood like plywood (Table II).

Table II: Comparative Energy Costs of Materials.

Material	Energy Cost to Manufacture/Process (MJ per metric ton)
Concrete	600–800
Wood	
Cut wood	~500
Plywood	~4000
Glass	15,700
Steel	21,000
From scrap	11,000
Aluminum	164,000
Recycled	18,000
Plastics (high-density polyethylene)	81,000

Source: Reference 5.

What are the next challenges? One of them is certainly to reduce further the carbon dioxide production involved in the use of concrete. A cement kiln generates carbon dioxide in two ways: through the combustion of fuel and by decarbonation of the most abundant raw material, limestone. However, similarly to the energy content, the carbon dioxide balance of concrete is much lower than that of pure cement. The processing of sand and other aggregates used to make concrete produces little CO₂. Furthermore, the lime (portlandite) in hardened cement reacts slowly, year after year, with atmospheric CO₂, reabsorbing some of the CO₂ produced during cement production. Everything considered, concrete is much more "eco-friendly" than is generally thought.⁴ With photocatalysis, it even deserves the "green material" label. Yet, progress can still be made by increasing what may be called the mechanical yield

of the hydration products, by producing more durable strength with less cement. We can also imagine the better exploitation of the other functionalities of building materials, such as heat and moisture transfer and resistance to degradation. No doubt this will require a broad materials science approach, extending from crystal growth to molecular engineering, from granular materials physics to hybrid materials chemistry, and from the physics of surface forces to the mechanics of porous media.

References

1. Israel Science and Technology home page, <http://www.science.co.il>. On the home page, enter "earth's crust" in the "search" box (accessed April 2004).
2. See the theme "Advanced Cement-Based Materials," *MRS Bull.*, XVIII (3) (March 1993) p. 33.
3. F. Vallée, B. Ruot, L. Bonafous, L. Guillot, N. Pimpinelli, L. Cassar, A. Strini, E. Mapelli, L. Schiavi, C. Gobin, H. André, N. Moussiopoulos, A. Papadopoulos, J. Bartzis, T. Maggos, R. McIntyre, C. Lehaut-Burnouf, A. Henrichsen, P. Laugesen, R. Amadelli, D. Kotzias, and P. Pichat, "Innovative Self-Cleaning and Depolluting Facade Surfaces," presented at CIB World Building Congress 2004, May 2–7, 2004, Toronto, Canada.
4. "Why Concrete?" Environmental Council of Concrete Organizations Web site, <http://www.ecco.org/> (accessed April 2004).
5. Comparative energy costs from P. Eyerer and H.-W. Reinhardt, *Ökologische Bilanzierung von Baustoffen und Gebäuden* (GaBi-Projekt final report) (Birkhäuser-Verlag, Basel, 2000); *Ökobilanzen Holz* (Deustchen Gesellschaft für Holzforschung, Munich, April 1997); H.-W. Reinhardt et al., *Sachstandbericht Nachhaltig Bauen mit Beton*, Deutscher Ausschuss für Stahlbeton Schriftenreihe 521 (Beuth, Berlin, 2001); H. Glässer, H.K. Gründler, and H.J.-F. Heitz, *Ökologische Betrachtung und Bilanzierung von Wärmedämmglas*, Ergebnisbetrachtung (internal study) (Vegla GmbH, Aachen, Germany, 1996). □

Karen Scrivener, Guest Editor for this issue of *MRS Bulletin*, is a professor and head of the Laboratory of Construction Materials within the Department of Materials at the Swiss Federal Institute of Technology Lausanne (EPFL, Ecole Polytechnique Fédérale de Lausanne), Switzerland. Currently, she is coordinating a network of academic research groups and industry to support fundamental research on the mechanisms

operating in cementitious materials. Scrivener graduated from the University of Cambridge in 1979 in materials science. She went on to complete a PhD degree on microstructure development during the hydration of portland cement at Imperial College London in 1984. She remained at Imperial College until 1995 as Royal Society Research Fellow and then lecturer, heading the Cement and Concrete Group

in the Department of Materials. From 1995 to 2001, she worked at the Central Research Laboratories of Lafarge near Lyon in France as head of research on calcium aluminate cements and expert on concrete durability in general. She is the author of more than 80 publications on cement and concrete.

Scrivener can be reached at the Laboratory of Construction Materials (LMC),



Karen Scrivener

EPFL, 1015 Lausanne, Switzerland; tel. 41-21-693-5843 and e-mail karen.scrivener@epfl.ch.



Henri Van Damme

Henri Van Damme, Guest Editor for this issue of *MRS Bulletin*, has been a professor at



**Alejandro Alva
Balderrama**




Lennart Bergström



Luigi Cassar



Robert J. Flatt

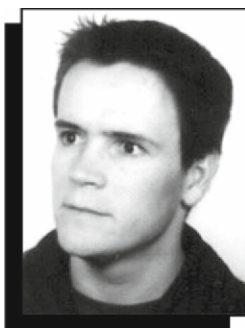

Frédéric Heger



Hugo Houben

ESPCI (Ecole Supérieure de Physique et Chimie Industrielles) in Paris since 1999. He is primarily interested in the chemomechanics of cement- and clay-based materials and in their interactions with polymers.

Van Damme received his undergraduate degree in agricultural and chemical engineering in 1969 and his PhD degree in materials science in 1973, both from the University of Louvain, Belgium. His thesis work was on diffusion in glasses and in adsorbed fluids. He then moved to the CNRS in Orléans, France, where, after a two-year post-doctoral position researching adsorption of dye molecules and metal clusters, he was appointed to a research scientist position. From 1976 through 1985, including a sabbatical year at the University of Wisconsin, Milwau-

kee, Van Damme worked on heterogeneous photocatalysis and on the photochemical conversion of solar energy in colloidal systems. From 1985 through 1999, he was director of the CNRS Research Center on Divided Matter and his interest shifted to porous and dispersed materials, complex fluids, and the physics of fractals, with a growing interest in cement-based materials. He is the author of approximately 140 papers and book chapters.

Van Damme can be reached at Ecole Supérieure de Physique et Chimie Industrielles, 753231 Paris Cedex 05, France; tel. 33-1-50-79-44-19 and e-mail henri.vandamme@espci.fr.

Alejandro Alva Balderrama is an architect and director of the Architecture and Ar-

chaeological Sites Unit at ICCROM, the International Center for the Study of the Preservation and Restoration of Cultural Property, located in Rome. He has dedicated more than 33 years to issues of architectural conservation, with a particular emphasis on earthen construction. During these years, Balderrama been concerned with conservation practice in a number of positions, including as chief resident architect of regional restoration works of the COPESCO Plan, Peru, sponsored by UNESCO (1970–1973); conservation inspector for the Peruvian National Institute of Culture (1973–1975); head of the Planning Office and national project coordinator for the National Center for Conservation, Restoration, and Research of the Peruvian National Institute of Culture

(1975–1978); and since 1978, a Professional Staff member at ICCROM, in the positions of coordinator of the International Architectural Conservation Courses, co-director of the Gaia Project, and co-director of the Terra Project.

He graduated from the School of Architecture at the Universidad Ricardo Palma in Lima, Peru, in 1970. He is the author of numerous publications.

Balderrama can be reached at ICCROM, 13 via di San Michele, 00153 Rome, Italy; tel. 39-06-5855-331, fax 39-06-5855-3349, and e-mail aa@iccrom.org.

Lennart Bergström is a manager of the Materials and Coatings section at the Institute for Surface Chemistry (YKI) in Stockholm, Sweden. He is also the director of The Brinell Centre—Inorganic Interfacial Engineering, a center of excellence at the Royal Institute of Technology (KTH). His current research interests include the rheology and stability of concentrated suspensions; the development of novel processing methods for particulate materials; calculation and direct measurements of interparticle forces between inorganic and polymeric materials; and the synthesis, functionalization, and self-assembly of nanoporous colloids for biomedical and sensor applications.


Bergström received an MSc degree in chemical engineering (1984) and a PhD degree in physical chemistry (1992) at the Royal Institute of Technology. He has been a visiting scientist at the University of Washington in Seattle and at the

Tokyo Institute of Technology. He is the author of more than 90 papers.

Bergström will soon leave YKI to take up a position as professor of materials chemistry at Stockholm University; until then, he can be reached at the Institute for Surface Chemistry, YKI, Box 5607, SE-114 86 Stockholm, Sweden; tel. 46-8-50106030, fax 46-8-208998, and e-mail lennart.bergstrom@surfchem.kth.se.

Luigi Cassar is the director of Corporate Research and Development for the Italcementi Group in Bergamo, Italy. His main research interests are catalysis and photocatalysis, materials science, industrial processes, and cement and concrete. He holds a degree in chemistry from the University of Rome and worked several years at Montedison and at the University of Chicago before being appointed vice director of Istituto Guido Donegani in Novara, Italy. From 1979 to 1982, he was vice director of Pigment Research and Development at Ciba Geigy in Basel, Switzerland. From 1983 to 1991, he held several managerial positions in the R&D organization of Enichem, and in 1991, he joined Italcementi.

Cassar has also served as a professor at the Universities of Sassari, Parma, and Bologna. He is a member of the Steering Committee of AIRI (the Italian Association for Industrial Research), the National Research Council's Register of Referees, and several Italian and European committees in the field of construction materials

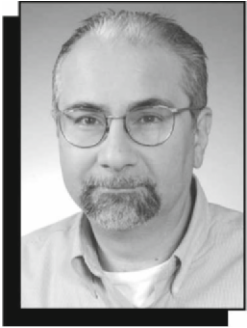

Nicos Martys



Parviz Navi



Roland J.-M. Pellenq



Stefan Simon



Christian P. Vernet

standardization. He is the author of 60 patents and 72 scientific publications.

Cassar can be reached at Italcementi Group, R&D Division, Via G. Camozzi 124, 24121 Bergamo, Italy; tel. 39-035-4126-111, fax 39-035-4126-013, and e-mail l.cassar@italcementi.net.

Robert J. Flatt is currently heading basic research on mineral-organic interactions in the Corporate Research department of Sika Technology (Zurich, Switzerland), after spending two-and-a-half years as a postdoc at Princeton University. Before that, he obtained a PhD degree (1999) in the materials science department of the Swiss Federal Institute of Technology Lausanne (EPFL) and a diploma in chemical engineering (1994) at the same institution. His past research involved the study of

dispersion and rheology of hydraulic binders, salt crystallization in porous materials, particle-modified consolidants for the restoration of weathered stone, and the tailoring of mortars for the conservation of Roman mosaics.

In 2003, Flatt was awarded the 2003 RILEM Robert L'Hermite Medal in recognition of his contribution to cement and concrete technology, with a particular mention for his contributions to the basic understanding of the mechanisms of dispersants in concrete.

Flatt can be reached at Sika Technology AG, Corp. Research & Analytics, Tuffenwies 16, 8048 Zurich, Switzerland; tel. 41-1-436-42-15, fax 41-1-436-44-44, and e-mail flatt.robert@ch.sika.com.

Frédéric Heger is a PhD student at the Swiss Federal Institute of Tech-

nology Lausanne (EPFL) in the Laboratory for Construction Materials. He received an engineering diploma in materials science in 2000.

Heger can be reached at the Swiss Federal Institute of Technology, Laboratory for Construction Materials, MX-G, Ecublens, 1015 Lausanne, Switzerland; tel. 41-21-693-46-73, fax 41-21-693-58-00, and e-mail frederic.heger@epfl.ch.

Hugo Houben is a co-founder of CRATERre, the International Center for Earth Construction, a scientific organization within the School of Architecture of Grenoble, France. He is also responsible for the UNESCO Chair for Earthen Architecture (Constructive Cultures and Sustainable Development) and is co-director of the Terra Project, a joint venture of CRATERre, the International Center for the Study of the Preservation and Restoration of Cultural Property (ICCROM), and the Getty Conservation Institute (GCI).

Houben has been specializing in earth construction since 1972. He realized his first project in Algeria and has made many contributions to scientific knowledge

about earthen building materials and their use in construction and conservation. He has published many scientific, technical, and architectural articles in the specialized and general press and is the co-author of several reference books in the field. He is an expert for international organizations such as the World Bank, ILO (the International Labor Organization), UNCHS-Habitat (the U.N. Human Settlements Program), UNIDO (the U.N. Industrial Development Organization), UNESCO (the U.N. Educational, Scientific, and Cultural Organization), and CDE/EU-ACP (the Center for the Development of Enterprise, a cooperative venture of the European Union and the African, Caribbean, and Pacific countries).

Houben graduated in 1960 from the Royal Nuclear Industry Institute in Brussels with an engineering degree in nuclear science and electronics.

Houben can be reached at CRATERre-EAG, BP rue de la Buthiere, Maison Levrat, Parc Fallavier, F-38092, Villefontaine Cedex, France; tel. 33-4-74-95-43-91, fax 33-4-74-95-64-21, and e-mail craterre@club-internet.fr.

Nicos Martys is a staff physicist in the Building and Fire Research Laboratory at the National Institute of Standards and Technology (NIST) in Gaithersburg, Md. His research interests include moisture and diffusive transport in porous media, single- and multicomponent flow in porous media, hydrodynamic dispersion, the application of

percolation theory to understanding transport in porous media, the dynamics and stability of fluid systems in confined geometries and under shear, and the rheology of suspensions. He is also involved in the development and advancement of computational methods for modeling fluid systems using conventional CFD, lattice Boltzmann, and dissipative particle dynamics methods. The main goal of this research is prediction of the rheological properties of concrete as a function of composition.

Martys received a PhD degree in condensed-matter physics from the Johns Hopkins University in 1990. He was awarded an ASEE postdoctoral fellowship at NIST from 1990 to 1992 and then accepted a permanent position there. Martys serves as an editor of the *NIST Journal of Research*.

Martys can be reached at NIST, Materials and Construction Research Division, 100 Bureau Drive, Stop 8615, Gaithersburg, MD 20899-8615, USA; tel. 301-975-5915, fax 301-975-4032, and e-mail nicos.martys@nist.gov.

Parviz Navi has been a research associate at the Swiss Federal Institute of Technology Lausanne (EPFL) in the Laboratory of Construction Materials since 1989. His scientific interests include the micromechanics of heterogeneous materials, fundamental problems of fracture in concrete and wood, and the development of synthetic-free materials made from wood. He obtained his PhD degree in engineering, studying

wave propagation in heterogeneous materials, from University of California–Los Angeles in 1973, also serving as a postdoctoral fellow at UCLA. In 1975, he returned to Iran. In 1982, he joined the Ecole Nationale des Ponts et Chaussées in Paris as a research associate and member of the teaching staff. There, he developed a homogenization method using wave-dispersion curves for both elastic and viscoelastic heterogeneous materials.

Navi can be reached at the Swiss Federal Institute of Technology, Laboratory of Construction Materials, MX-G, Ecublens, 1015 Lausanne, Switzerland; tel. 41-21-693-28-38, fax 41-21-693-5800, and e-mail parviz.navi@epfl.ch.

Roland J.-M. Pellenq is a research scientist at the CNRS (Centre National de la Recherche Scientifique) in Marseille, France. His research interests are focused on the thermodynamic properties of molecular and covalent fluids in porous materials (e.g., zeolites, microporous carbons, mesoporous materials, cement) using atomistic simulation techniques integrating realistic adsorption intermolecular potentials and textural descriptions of disordered porous materials. He obtained his PhD degree at Imperial College London in 1994 and then spent two years as a postdoctoral assistant in the Physical Chemistry Department at the University of Paris XI, Orsay. In 1995, he joined the Centre de Recherche sur la Matière Divisée in Orléans. He was head of the Complex Fluids and

Porous Systems group there from 2000 to 2003. He then moved to the Centre de Recherche en Matière Condensée et Nanosciences in Marseille.

He is the author or co-author of more than 50 papers and was the recipient in 2002 of the Young Researcher Prize from the French Physical Chemistry Society. In 2003, he also received the Young Researcher Award at the Festival of Sciences and Technologies.

Roland Pellenq can be reached by e-mail at pellenq@crmcn.univ-mrs.fr.

Stefan Simon heads the Building Materials section of the Getty Conservation Institute (GCI) in Los Angeles, where he is collaborating within the Terra Project, a joint venture of CRAterre (the International Center for Earth Construction, a scientific organization within the School of Architecture of Grenoble, France), ICCROM (the Center for the Study of the Preservation and Restoration of Cultural Property), and GCI.

Simon has specialized in deterioration diagnostics, microanalytics, nondestructive testing, physicochemical analysis, testing, and evaluation of conservation products and the control of treatment efficacy and durability of murals and monuments of natural stone, adobe, and mortar. He also has managed stone conservation projects in Eastern Europe, the Middle East, and China. He is founder and director of the private laboratory KDC (Konservierung und Denkmalpflege Consulting in Olching,

Germany), created in 1992. He also teaches conservation science at Munich Technical University and is the official U.S. representative to the ICOMOS (International Council on Monuments and Sites) scientific committee on stone. Simon graduated in 1987 with a degree in chemistry from the Ludwig Maximilians University in Munich.

Simon can be reached at the Getty Conservation Institute, 1200 Getty Center Drive, Suite 700, Los Angeles, CA 90049, USA; tel. 310-440-7300, fax 310-440-7711, and e-mail ssimon@getty.edu.

Christian P. Vernet has worked in industrial cement and concrete research since 1967 and is the author of more than 60 publications in the area. He is best known for his work on the development of high-performance and ultrahigh-performance concretes, a major contribution to the development of the commercial ultrahigh-performance concrete Ductal. Additional areas of expertise include cement chemistry, crystallography, and microstructure; the design of admixtures and the improvement of the flow properties of concrete; and scientific tools and software for concrete-mix design.

Vernet can be reached at Lafarge, Laboratoire Central de Recherche, L'Isle d'Abbeau, Parc des Chesnes, 95 rue Montmurier, BP15, 38291 Saint Quentin Fallavier Cedex, France; tel. 33-4-74-82-16-16, fax 33-4-74-95-56-08, and e-mail christian.vernet@pole-technologique.lafarge.com. □

See us at SAMPE 2004

S 3D MODELING solutions

that you thought did not exist...


S3D Modeling software is a unique scientific tool for 3-dimensional modeling of granular media. S3D Modeling product family provides comprehensive visual analysis and wide range of quantitative characteristics of the granular structures.

Nanofilms
Coatings
Powders
Ceramics
Composites
Refractories

Grain structure
Pore structure


Packing
Sintering

and more...




S3D SpheroPack

Modeling of oil-bearing rock



S3D Evolution

Modeling zonal segregation during the disperse powders sintering



S3D SpheroPolyhedra

Multiphase polydisperse central packing of particles with varied morphology

www.smartimtech.com

SMART IMAGING TECHNOLOGIES
Tel: US: (877) 280.11.00 (toll-free)
Tel: International +1 (713) 589.32.16
E-mail: info@smartimtech.com

For more information, see <http://advertisers.mrs.org>